



The moulds from Velebit and European Bronze Age metal anvils

Barbara Armbruster, Albrecht Jockenhövel, Aleksandar Kapuran, Raško Ramadanski

► To cite this version:

Barbara Armbruster, Albrecht Jockenhövel, Aleksandar Kapuran, Raško Ramadanski. The moulds from Velebit and European Bronze Age metal anvils. *Starinar*, 2019, 69, pp.139-182. 10.2298/STA1969139A . hal-02425589

HAL Id: hal-02425589

<https://univ-tlse2.hal.science/hal-02425589>

Submitted on 7 Jun 2021

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

СТАРИНАР



На корицама: Преслица од ћилибара, Виминацијум, крај II – почетак III века
фото: Горан Стојић

Sur la couverture: La quenouille en ambre, Viminacium,
fin du II^e – commencement du III^e siècle
Photo: Goran Stojić



BARBARA ARMBRUSTER, Université de Toulouse-Jean Jaurès
 ALBRECHT JOCKENHÖVEL, Westfälische Wilhelms-Universität, Münster
 ALEKSANDAR KAPURAN, Institute of Archaeology, Belgrade
 RAŠKO RAMADANSKI, Town Museum, Bečej*

THE MOULDS FROM VELEBIT AND EUROPEAN BRONZE AGE METAL ANVILS

e-mail: barbara.armbruster@univ-tlse2.fr

Abstract – During the first excavations of the cemetery dating from the Bronze Age and Early Antiquity in the village of Velebit near Kanjiža (Northern Serbia) one of the excavated artefacts was found to belong to a used and broken stone mould for casting anvils. However, without an expert archaeologist to supervise the recovery of this find, which remained unknown for decades after its discovery, as a starting point, the authors of this article present a synthesis that takes into account several aspects of this significant class of metalcraft object. This proceeds from the history of the excavation to the general role of European Bronze Age anvils in gold and bronze metalworking, and then further on to their typological, terminological, chronological and functional analysis and to their long-range distribution as a sign of an interregional network of craftsmen, including their social context and symbolism.

Key words – Bronze Age, Carpathian Basin, Tumulus Culture, anvils, moulds, jewellery, metallurgy

THE CONTEXT OF THE MOULDS FROM VELEBIT

During the Middle Bronze Age, according to N. Tasić,¹ or Br B-C according to R. Vasić,² or developed Bronze Age according to A. Bulatović, V. Filipović and R. Gligorić,³ the first finds of the Tumulus culture (*Hügelgräberkultur*) appeared in the territory of Northern and North-Western Serbia. The process of the spread of these influences began from the Carpathian Basin and developed in two geographical areas (groups), the first being northern Bačka and Banat, whereas the second extended to the Danube Basin,⁴ The Drina and the Western Morava river valleys (Map 1).⁵ Cemeteries of the first group are characterised exclusively by flat graves without barrows, while in the territory of the second group barrows occur regularly. In relative terms, the necropolis at the modern village of Velebit, near (ca. 14 km NNW) the town of Kanjiža (Senta county, Vojvodina Province), represents the best investigated

cemetery site of the Tumulus culture in the territory of Serbia, bordering the influence zone of the Belegiš culture and sharing certain traits and elements with better investigated cemeteries under the barrows, which are usually in The Drina and the Western Morava river valleys (Western Serbia).

* During the research and writing of this topic, Raško Ramadanski was working as an archaeologist in the Town Museum in Senta, and provided the archaeological material from the Velebit site, with the support of Rastko Vasić, to Albrecht Jockenhövel and Aleksandar Kapuran, after the finds had spent forty years in relative obscurity. Jockenhövel was then able to persuade Barbara Armbruster to collaborate on this study.

¹ Tasić 2004: 31.


² Vasić 2003: 3.

³ Булатовић, Филиповић, Глигорић 2017: 53.

⁴ Tasić 1974: 234

⁵ Tasić 1974: 234

The paper represents a result of the OI 177020 project *Arheologija Srbije: Kulturni identitet, integracioni faktori, tehnološki procesi i uloga centralnog Balkana u razvoju evropske praistorije* (Archeology of Serbia: Cultural Identity, Integration Factors and the Role of the Mid-Balkans in the Development of European Prehistory).

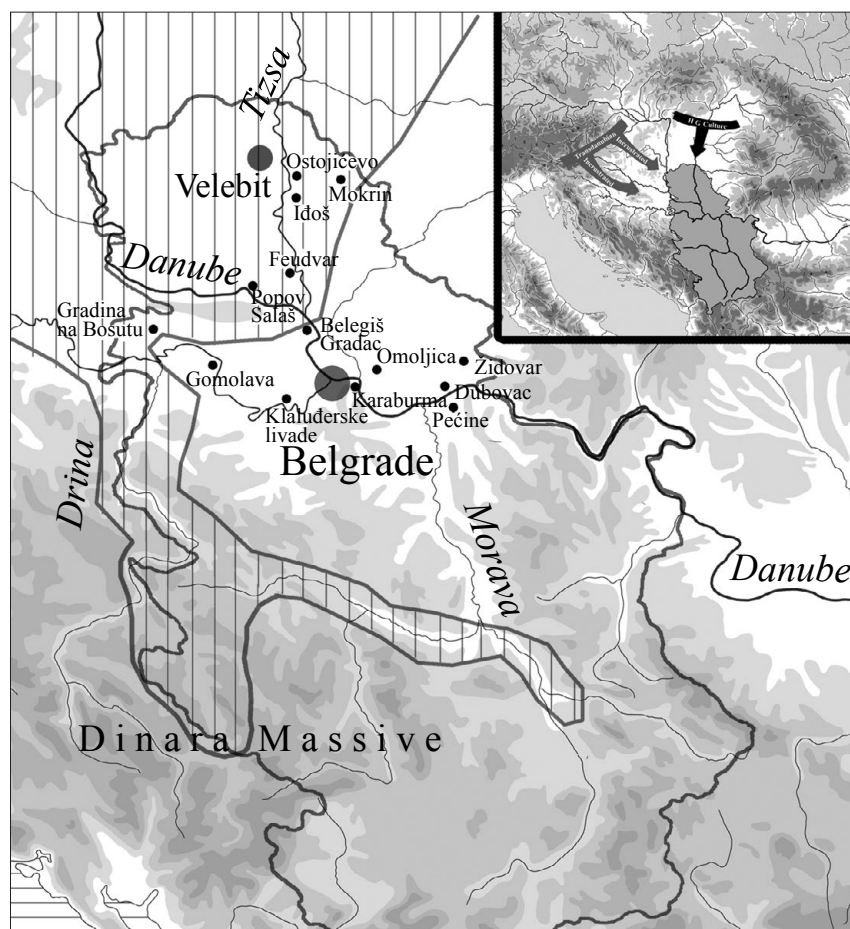

Map 1. Tumulus culture (Hügelgräberkultur) penetration into the Central Balkans

Карта 1. Прогор културе гробних хумки на простор централној Балкана

The site of the Velebit cemetery

During construction of a major road in the village of Velebit, small scale archaeological excavations were carried out in the mid-1950s that, despite their limited extent, provided significant finds. The further need for extending the road infrastructure in the village, as well as financial support from the Smithsonian Institute (Washington D. C, USA),⁶ led to systematic archaeological excavations in 1970 when the site was investigated to the fullest possible extent. During the Bronze Age, a biritual burial rite (inhumation and cremation) was practiced at the Velebit cemetery⁷ (Fig. 1; 2). During these excavations in 1970, a total of 108 graves were discovered, of which 77 are from the Bronze Age, including 43 cremation and 34 inhumation burials. The remaining 31 graves are from Late Antiquity and described as Sarmatian from the 4th century AD (Plan 1).⁸

The most representative of Bronze Age inhumation burials at the site is grave No 7 with rich bronze objects (Fig. 1) (Plate 1). Grave 7 is also interesting because of two large pottery vessels that typologically correspond

to the Tumulus culture. Another representative example of a Bronze Age skeletal burial at the Velebit site is grave No. 80,⁹ where a pair of *Regelsbrunn* type greaves (Plates 2/12.13), a typical Belegiš culture beaker, two lunular pendants (Plate 1/6), bronze sheet metal applications (Plate 1/10) and three spirally bent wires, most likely rings, were found (Plate 1/3).¹⁰ Inhumation grave No. 94 contains two *Petschaftkopfnadeln* type pins (Plates 2/8.9) and a large belt made of thin hammered bronze sheet metal.¹¹

A characteristic example of a cremation grave at the Velebit site is grave No 14 (Fig. 3) (Plate 1/12; 3/5.6), (Plate 1/12; 2/2). Cremation grave No 33 is also

⁶ Tasić 1974: 235; Tasić 1983: 87; Sekereš 1971; Kapuran 2018.


⁷ Tasić 1974: 235.

⁸ Sekereš 1971; Kapuran 2018.

⁹ Kapuran 2018.

¹⁰ Ibid.

¹¹ Ibid.

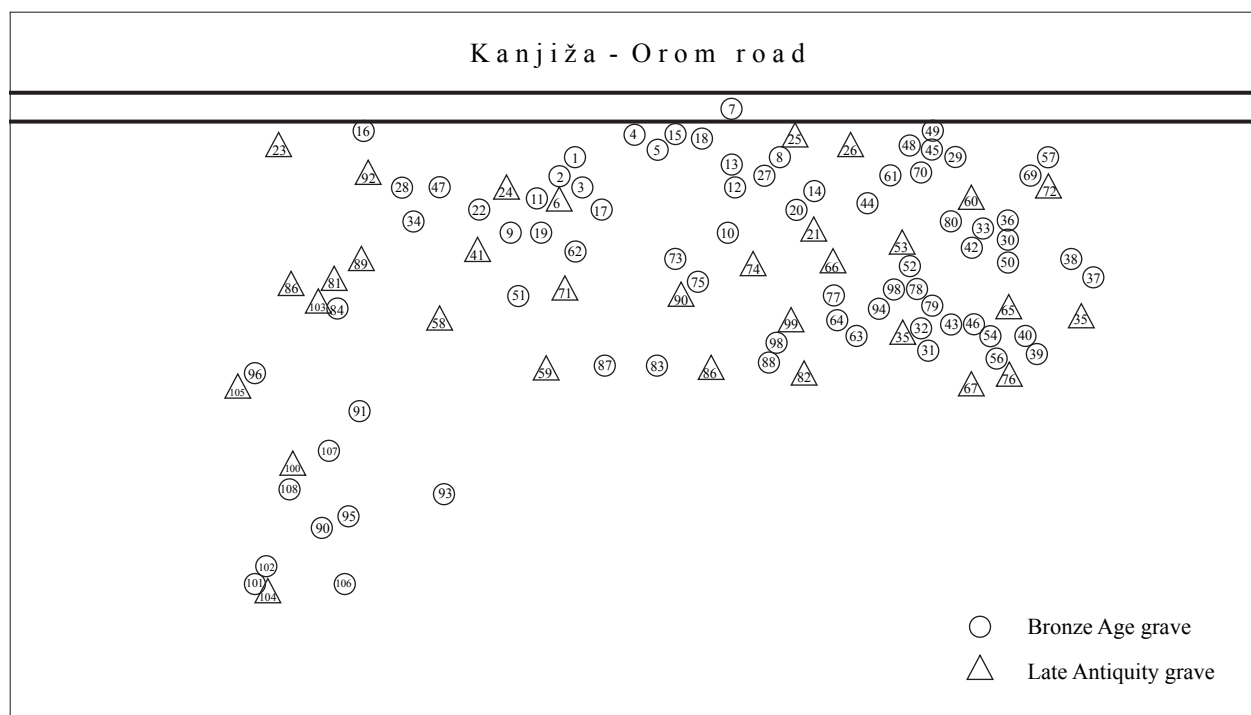

Plan 1. Velebit. Plan of the cemetery

План 1. Расположение гробов на некрополи Велебит

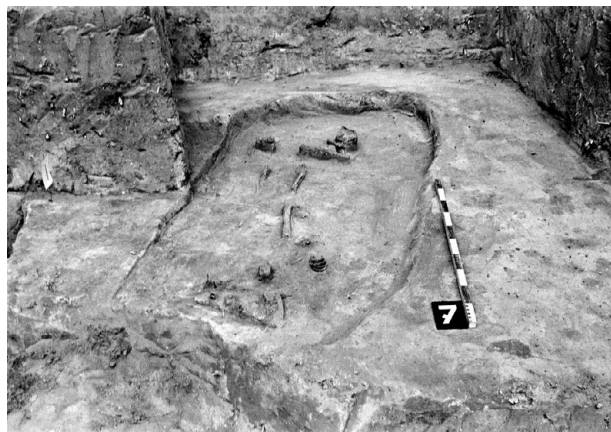


Fig. 1. Velebit. Inhumation grave No. 7. Extended body

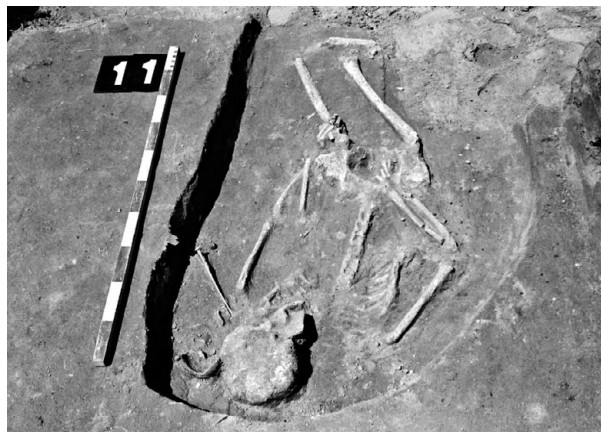


Fig. 2. Velebit. Inhumation grave No. 11. Contracted body

Сл. 1. Велебит, гроб бр. 7:

скелетно сахрањен ђокојник у исђруженом ђоложају

Сл. 2. Велебит, гроб бр. 11:

скелетно сахрањен ђокојник у зђрченом ђоложају



Fig. 3. Velebit. Cremation grave No. 14

Сл. 3. Велебит, гроб бр. 14: гроб сђаљеној ђокојника

interesting, mostly due to the fact that three typologically different beakers were discovered. While the first two are characteristic of the *Hügelgräber* culture (Plates 3/3.4), the third is a typical example of a so called „Pannonian” beaker and is part of the Belegiš culture (Plate 3/2). In contrast, the cremated remains were put in a rustic shaped urn of a relatively rough surface (Plate 3/7).

While the pottery production discovered at the Velebit necropolis manifests characteristics of the „Carpathian” variant of the Tumulus culture, which spread along the Tisza River towards the south of Pannonia, the assemblage of bronze products shows characteristics of the Kozsider bronze production from the Middle Bronze Age.¹² The same can be stated for the jewellery used to adorn the bodies at the Velebit cemetery, which differ only slightly from the usual assemblage of jewellery from the graves of similar Tumulus culture cemeteries in the Carpathian basin.

The moulds

Besides the attractive finds of jewellery and pottery discovered at the Velebit cemetery, one of the most significant finds are certainly a group of sandstone moulds (Plate 5), for which the context of finding still remains unclear, since they were discovered in the summer of 1954 when small scale excavations by the Senta Town Museum (Gradski muzej) were conducted, but without the supervision of an expert archaeologist. Consequently, it was never clear whether they represent grave goods, or belong to a hoard (perhaps to a so called „grave-hoard”) or belong to an as yet undiscovered settlement in the vicinity of the site that existed at the time as the cemetery. All the moulds were made of sandstone, which is suitable for the engraving of negatives that were cast. Sandstone is a very common material for casting and easy accessible in various geological formations and locations, also in the Pannonian and Carpathian regions.¹³ Some specimens have burnt edges around the negatives caused by high temperatures during the direct casting of molten bronze (Fig. 4/1–3). Most of the moulds of the Velebit complex are damaged and they could not be used for further castings.

Mould 1 a. b: a two part (bivalve) mould with negatives for the simultaneous casting of two lunular pendants (Fig. 4/2; 5/2–4; Fig. 4/1; 5/1. 2; Pl. 4/6a, 6b) that are typologically close but not the same as the pendants from grave No 80 (Plate 1/6).¹⁴ The first part of this bivalve mould (Plate 4/6a) measuring 12 x 7 x 2 cm, was bifacial, or had a dual function, since its

reverse side contained another, very damaged negative, for which we can only assume the shape of a socketed axe (Plate 4/1). Besides the pendant negatives, it contains two dowel-holes. The other part of the mould (Plate 4/6b) measuring 11.5 x 8.5 x 2 cm, also contained two dowel-holes. This stone mould, used to cast three lunular pendants that would have been typologically identical to pendants from Velebit grave 80, is almost identical to the double Mould 1 from the Velebit necropolis, and is kept today in the Museum of Subotica (Fig. 5/3).¹⁵ From the territory of Eastern Serbia comes one more mould, discovered on the banks of The Danube in 1971, in the course of archaeological surveys at the Velesnica site (Fig. 5/1).¹⁶ Lunular and heart-shaped pendants had an important role in the costume fashion of the Bronze Age, besides the large number of these pendant finds, they can also be indirectly observed on examples of the numerous anthropomorphic clay idols from that time.

Mould 2: The fragmented mould (Plate 4/5; Fig. 5/4) measuring 8.5 x 7 x 3 cm, seems to have served for the casting of bronze sickles. We assume this on the basis of the negative shape, which shows an elongated banded form of a handle of thin cross-section and a ribbed pattern. This assumption is strengthened by another fragmented mould (Plate 4/4) measuring 5.5 x 8 x 3 cm, in which the negative has an arched shape with a rib along the sharp edge. It also has the same thickness as the previously described mould, so we assume that they could together represent part of a larger mould for casting sickles, as indicated by one specimen discovered in Romania.¹⁷

Mould 3: An elongated mould measuring 7 x 3.5 x 3 cm, has a negative in the form of a pin with a seal shaped head or broadening (Fig. 4/3; Plate 4/1). The second oval broadening located below the first one may have been decorated with a sequence of parallel canelures. Perhaps a mould like this could have served for the casting of a pin found in the Belciug hoard in Romania.¹⁸

¹² Kovács 1975: 43,44.

¹³ See Soltvaldkert (Bács-Kiskun, Hungary) hoard: Gazdapusztai 1959.

¹⁴ Bader 1978: pl. LXXXVI/5.

¹⁵ Tasić 1974: 239/146.

¹⁶ Васић, Ерцеговић-Павловић, Минић 1984: Сл. 110/4.

¹⁷ Bader 1978: pl. LXIII/12.

¹⁸ Bader 1978: 120, pl. LXXVII/15.



Fig. 4. Velebit. Sandstone moulds from an unknown area of the cemetery

Сл. 4. Велебӣй, калуӣи од камена йеишчара са некройоле

Mould 4: Mould 4 has an elongated form measuring 12.5 x 3 x 3 cm, for which we assume that it also served for casting some kind of pin shaped objects, containing three additional grooves that intersect the negatives at a 90° angle (Plate 4//5; Fig. 4/5). It is possible that this kind of mould was also used for the casting of the body of the *Blattbügel* type of fibulae dating in the Early Hallstatt (Ha A) period.¹⁹ One mould from the Soltvaldkert (Bács–Kiskun, Hungary) hoard, has a negative that shows two pins connected with a channel at a 90° angle.²⁰

Mould 5: This mould (Plate 4/3; Fig. 4/4) is small (measurement: 3.5 x 4 x 2.5 cm), and could have served for the casting of objects in the form of nails. It is possible that this mould was used as an auxiliary tool in a further metallurgic process, in the course of casting certain complex objects, or that it represented a small tool for decorating other bronze objects.

Mould 6: The last example from this group of moulds and the most interesting one measures 9 x 8 x 4 cm, and served for casting an anvil (Fig. 4/2; 5/4.5; 12/7). The negative shows that the anvil had a spike on one side probably not for fixing into a wooden support

but for banding wire-shaped jewellery,²¹ as seen on the specimen discovered in Fresné-la Mère (Fig. 13/10). The upper part of the Velebit anvil has a triangular shape. Moulds for casting anvils belong to rare finds of Bronze Age mould assemblages. Additionally, anvils are not easy to identify, especially when the moulds in which they were cast are fragmented. Anvils had a major role in various crafts and were necessary for plastic shaping techniques and the final treatment of objects after their casting. Without them, the processing of ingots into sheet metal shaped jewellery would hardly be possible, as a strong and flat support is necessary for forging. We assume that the belt from grave 94 could not have been properly made without such a small anvil, necessary for forging and decoration.

As stated earlier, during the Kozsider horizon in the Middle Bronze Age there was a significant expansion in jewellery and weapon production, especially those of

¹⁹ Kytlicová 2007: 38, 256, pl. 178/B2.

²⁰ Gazdapusztai 1959: pl. IV/6–7.

²¹ Tylecote 1987: 265, Fig. 7.19.

copper and tin alloys. Such a need for bronze products must have driven a certain social stratification based on metal smith crafts performed by Middle Bronze Age societies in Europe. Numerous sites have been found in the Alps, Carpathians, Eastern Serbia, and Western Bulgaria, at which traces of copper, and more rarely tin, were discovered. All tin ore deposits in Europe have been known to geologists for a long time, as well as in vicinities of the Cer and Bukulja mountains in Western

Serbia.²² It is assumed that the trade and exchange of tin and antimony led to the integration of the Tumulus culture during the Kozsider period.²³ Although animal husbandry and farming were still dominant in the economy, the rise of certain societies specialised in mining and metallurgy for the purpose of metal production is evident. Such societies are, among others, identified thanks to several decades of archaeological research conducted through the project „Research of



Fig. 5. Bronze Age stone moulds: 1) Velesnica; 2, 4, 5) Velebit; 3) Subotica

Сл. 5. Калуји од камена: 1) Велесница; 2, 4, 5) Велебић; 3) Суботица

ancient mining and metallurgy in the Timok eruptive basin” in the area of north-eastern Serbia, in the vicinity of Bor.²⁴

In the territory of South-eastern Europe, moulds for bronze casting were found in the context of settlements, hoards, and rarely in burials.²⁵ Indirect evidence for the separation of metalworking as a specialised branch of the economy during the Middle and Late Bronze Age, beside burials with metalworking tools, is also provided by hoards containing moulds. B. Nessel assumed upon her analysis of burial assemblages tied to metallurgy in Central Europe, that there is no evidence that metalworkers enjoyed special social status in these communities, but rather they were fully integrated and respective members of the communities.²⁶ This was perhaps the case because of the fact that many members of these societies participated in the metalworking process, so it was not felt necessary to specially accentuate their role in funeral rites.²⁷

The closest analogies to the mould hoard from the site of the Velebit necropolis is the site of Soltvaldkert (Bács-Kiskun) in Hungary, where 41 sandstone moulds for the casting of bronze objects were discovered in a pit, about 0.9 m deep.²⁸ Also, close to the Velebit necropolis, identical hoards of clay and stone moulds were discovered at the site of Şagu Site „A1–1” in Western Romania (Lower Mureş valley), although that context is chronologically somewhat younger, and corresponds to the Br D–Ha A1 period.²⁹ In the vicinity there is one more chronologically younger hoard of casting moulds from the Early Iron Age (8th–7th century BC) discovered at the site of St. Peter of Ludberg in Croatia.³⁰

Relative and absolute chronology of the site

B. Hänsel and T. Kovács assume that finds of the Tumulus culture in the Carpathian Basin appear over a large time span from Br B1 to Br D (or during the phases MD II, MD III/SD I).³¹ In the „Prehistory of Vojvodina”, published nearly half a century ago, N. Tasić proposed that the sites of *Hügelgräberkultur* in the surroundings of Subotica should be put a in chronological framework from the end of 14th to the beginning of the 13th century BC.³² Vasić assumes that the same culture in Serbian territory can be determined in the Middle Bronze Age, or Br B and Br C,³³ which chronologically corresponds to the period between 1600/1500–1200 BC, and its second phase, as suggested by Tasić.³⁴ There are certain divisions of the Bronze Age according to which the Tumulus *Hügelgräber*

culture in the Danube Basin is simultaneous to MD III, and does not start before the end of Br B1, or lasts between 1500–1300 BC,³⁵ with which F. Falkenstein also agrees.³⁶

Turning to recent absolute dates obtained for sites in Serbia, we can say that previously stated relative chronologies did not diverge much from the results obtained by absolute dating. The first result is related to an AMS date from the central grave of mound XVIII at the site of Paulje, which shows the span of 1415–1278 cal BC with 95.4% confidence.³⁷ It means that the grave from Paulje certainly belongs to the mid-14th century BC.³⁸ Another absolute date is from the Velebit necropolis. An acquired date of 3061±25, with a modelled span of 1407–1236 cal BC, with 95.4% confidence³⁹ means that the incineration grave from grave 107 at the Velebit cemetery most certainly belongs to the 14th–13th century BC, similar to the grave from mound XVIII at Paulje. This tells us that the relative dates for *Hügelgräberkultur* in the north of Vojvodina, proposed by Tasić, were closest to the absolute dates obtained at the sites of Velebit and Paulje.

²² Powell et al. 2018; Durman 1997; Valera, Valera 2003.

²³ Sánta 2013: 82.

²⁴ Kapuran 2014: 64–66.

²⁵ Jockenhövel 2017: 53.

²⁶ Nessel 2013: 144, 145; with differentiation Jockenhövel 2018: 276–277; 313.

²⁷ Nessel 2013: 144.

²⁸ Gazdapusztai 1959: Taf. IV/6–7; Hänsel 1968: 233; Mozsolics 1973: 80.

²⁹ Sava and Andreica 2013: 69.

³⁰ Šimek 2004: 92, 96.

³¹ Hänsel and Kovács 1986: 69.

³² Tasić 1974: 240.

³³ Vasić 2003: 3; Vasić 2010: 3.

³⁴ Tasić 2004: 31.

³⁵ Hänsel 1968: 143, 170.

³⁶ Falkenstein 1998: fig. 10.

³⁷ Gligorić, Filipović, Bulatović 2016: 105.

³⁸ Gligorić, Filipović, Bulatović 2016: 105.

³⁹ Kapuran 2018; The team engaged in the AMS dating procedure was comprised of: Molnár M, Riny L, Veres M, Seiler M, Synal H-A, Environ MICADAS: a mini 14C AMS with enhanced Gas Ion Source Interface in the Hertelendi Laboratory on Environmental Studies (HEKAL) Hungary. Radiocarbon Vol 55, Nr 2–3 2013, p. 338–344. Molnár M, Janovic R, Major I, Orsovski J, Gönczi R, Veres M, Leonard AG, Castle SM, Lange TE, Wacker L, Hajdas I, Jull AJT. Status report of the new AMS C14 sample preparation lab of the Hertelendi Laboratory of Environmental studies (Debrecen, Hungary) Radiocarbon, Vol 55, Nr 2–3 2013, p. 665–676.

THE ANVIL MOULD FROM VELEBIT AND EUROPEAN BRONZE AGE METAL ANVILS

History of research

From the second half of the 19th century, Bronze Age metal anvils were discovered and published.⁴⁰ V. G. Childe published a short study on the anvil of Inshoch Wood (Scotland) (no. 121; Fig. 11/2) including metal analysis.⁴¹ In 1975 J. Nicolardot and G. Gaucher provided a variant-rich typology based on French anvils, which was simplified by M. R. Ehrenberg (1981).⁴² Namely, she listed a total of 36 Bronze Age anvils from Europe. On the basis of ca. 60 anvils, D. Jantzen (2008) classified them by physical and functional criteria.⁴³ Recently, regional studies on anvils have been published in Italy, including Sardinian anvils, as well as Moravia and Romania.⁴⁴

Remarks on stone anvils

More than fifty years ago, J. J. Butler and J. D. van der Waals identified several small rectangular flat stones as metalworking tools, mostly dated as early as the Bell Beaker Culture and the Early Bronze Age of Central and Western Europe.⁴⁵ Such stone anvils gradually became significant elements in tool kits of gold, silver and coppersmiths. The anvils of the Amesbury Archer (or „King of Stonehenge”) (Wessex, England) and of the „Chief of Leubingen” (Saxony-Anhalt, Germany) became well known as so called „cushion stones” (German: *Kissensteine*).⁴⁶ Several recent studies provided evidence for stone tools in the context of metalworking during the Bell Beaker period but also during the rest of the European Bronze Age when bronze tools were predominantly in use.⁴⁷ Some specimens of stone tools featuring flat or flat and curved sides and working faces or with prominent and slightly rounded edges and corners are supposed to have been anvils of the Middle and Late Bronze Age. A small stone anvil made of serpentine, embedded in a wooden stump, was found in the Late Bronze Age lake village of Möriken (Switzerland), where bronze socketed hammerheads were also discovered.⁴⁸ Another combination of bronze and stone tools for metalworking appears in the Late Bronze Age hoard of fine metalworking tools from G  nelard (Burgundy, France). It consists of several bronze socketed hammerheads and anvils (no. 28–31) and includes a hammer shaped like a stone axe head (Fig. 18).⁴⁹ Large and heavy stones were presumably also used as anvils.⁵⁰ In that regard, B. Armbruster observed West

African blacksmiths of the Dogon community constructing their smithy around an *in-situ* rock which they used as an anvil.⁵¹ A forging tool set consisting of a stone anvil and hammer, associated with moulds and scrap metal, is known from House 1 at the Early Bronze Age settlement of   kuri  i H  y  k (Western Anatolia).⁵² It is possible that hardwood blocks were also used as anvils. It is additionally possible that such „archaic” installations were also common in Bronze Age Europe. However, by the Late Bronze Age, „cushion stones” disappeared from the inventory of metalworkers.

List of Bronze Age metal anvils

Abbreviations: E = Ehrenberg 1981; J = Jantzen 2008; N/G = Nicolardot/Gaucher 1975; G = grave; H = hoard; R = river find; S = settlement; W = wetland find

Austria (A)

1. Augsdorf (H), Carinthia (M  ller-Karpe 1959: 278 [no. 21], pl. 129, 21) (Fig. 16/1)
2. Hallstatt (G; Grave 283) (G), Upper Austria (Kromer 1959: 82, Fig. 50, pl. 44, 8 [*iron*]) (Fig. 7/8)
3. Sipbachzell (H), Upper Austria (H  glinger 1996: 111, pl. 1, 2 (Fig. 14/7)

Bosnia and Herzegovina (BiH)

- 4–6. Boljani   1–3 (H), Doboj (K  nig 2004: 191, no. 3 [39. 40. 41], pl. 17, 39–41) (Fig. 12/3; 15/6. 7)

Czechia (CZ)

Bohemia

7. Jarpice (H), okr. Kladno (Kytlicov   2007: 267 no. 66 [5], pl. 145, B 5) (Fig. 16/2)
8.   jezd (H), okr. Pisek (Kytlicov   2007: 311 no. 345, pl. 1, B 12) (Fig. 7/1)

⁴⁰ Chantre 1875; Evans 1881; Gross 1883; Hampel 1886; von Miske 1908; Coutil 1912; M  ller 1920; Ohlhaver 1939.

⁴¹ Childe 1945/46.

⁴² Nicolardot/Gaucher 1975; Ehrenberg 1981.

⁴³ Jantzen 2008: 253–259. 326–333.

⁴⁴ Iaia 2014; Lo Schiavo 2018; Sala   2014; Medele   1995; Gog  ltan 2005.

⁴⁵ Butler/van der Waals 1966.

⁴⁶ Fitzpatrick 2011; Bertemes 2004.

⁴⁷ B  tora 2002; Armbruster 2006; idem 2010; idem 2012; Brandherm 2010.

⁴⁸ Gross 1883: 45, pl. 27, 17.

⁴⁹ Thevenot 1998; Armbruster 2008.

⁵⁰ A. M  ller-Karpe 1994: 159.

⁵¹ Armbruster 1995: 120, fig. 2; idem 2001, 13.

⁵² Horejs/Mehofer/Pernicka 2010.

9. Velim (H), okr. Kolín (Kytlicová 2007: 312 no. 251, pl. 159, A 8) (Fig. 10/4)

Moravia

10. Blučina (H 4), okr. Brno-venkov (Salaš 2014: 65 no. 1, obr. 15, 1) (Fig. 15/4)

11. Brno-Rečkovice (H), okr. Brno-mešto (Salaš 2014: 65 no. 2, obr. 7, 10) (Fig. 6/5)

12. Jevičko (H), okr. Svítavy (Salaš 2014: 65 no. 3, obr. 15, 2) (Fig. 14/11)

13–15. Loučka 1–3 (H 2) (H), okr. Přerov (Salaš 2014: 65 no. 1. 5–7, obr. 15, 3. 4. 6) (Fig. 10/2. 3; 11/9)

16. Loučka 4 (SF), okr. Přerov (Salaš 2014: 65 no. 7, obr. 15, 5; 18) (Fig. 7/10)

Denmark (DK)

17. Damsholte (H), Frenderupgård, Vordingborg com., Møn (J 256 no. 370, pl. 68) (Fig. 16/7)

18. Sengeløse (H), Vasby, Københavns Amt (idem no. 35; J 256 no. 372, pl. 68) (Fig. 12/2)

19. Sulsted (H), Vestbjerg, Ålborg Amt (idem no. 36; J 256 no. 372, pl. 68) (Fig. 7/21)

France (F)

20. Alise-Sainte-Reine (R) (Canal de Bourgogne aux Laumes), Côte-d'Or (idem no. 21, fig. 2a; N/G 34 fig. 34; Thevenot 1998: 136, fig. 8,3 [see also Provenance unknown [no. 48]) (Fig. 13/2)

21. „Angerville” (R), Essonne (Mohen 1977: 251 [no. 91–1]; N/G 32, fig. 2) (Fig. 11/3)

22. Bardouville, Seine River (R), Seine-Maritime (idem no. 16; N/G 30, fig. 2) (Fig. 13/7)

23. „Calvados” (?) (idem no. 15) (no illustration)

24. Coray (Keranfinit) (H), Finistère (Mohen 1990: 130, fig. 38, 70) (Fig. 13/9)

Corbeil see Seine between Corbeil/Villeneuve-Saint-George (fig. 11/7)

25. Cuiry-les-Chaudardes (S; mould), Aisne (Blanchet 1984: 186, fig. 99, 18) (Fig. 12/10)

26. Fort-Harrouard (S; mould), Eure-et-Loir (Mohen/Bailloud 1987: 127, fig. 69) (Fig. 12/8)

27. Fresné-la-Mère (H), Calvados (idem no. 14 fig. 2d; N/G 29, fig. 1) (Fig. 13/10. 10a))

28. Gévelard 1 (H), Saône-et-Loire (Thevenot 1998: 130, fig. 4, 1) (Fig. 14/2)

29. Gévelard 2 (H), Saône-et-Loire (Thevenot 1998: 127, fig. 3, 3) (Fig. 9/7)

30. Gévelard 3 (H), Saône-et-Loire (Thevenot 1998: 127, fig. 3, 2) (Fig. 13/1)

31. Gévelard 4 (H), Saône-et-Loire (Thevenot 1998: 127, fig. 3, 1) (Fig. 9/6)

32. Gravelle-Sainte-Honorine (H), Seine-Maritime (O'Connor 1980: 398 no. 174; Dubus 1912: 14–24, pl. 5, 47; Watté 2010: 39, fig. 2, 47) (Fig. 8/2)

Gray see Saône near Chalon-sur-Saône (no. 44) (fig. 13/4)

Keranfinit see Coray (no. 24) (fig. 13/9)

33. La Lède-du-Gurp (SF; mould), Gironde (idem no. 13; Moreau 1971) (fig. 12/9)

34. Larnaud (H), Jura (N/G 35, fig. 1) (Fig. 14/3)

35. La Tour de Langin (SF), Haute-Savoie (idem no. 26, pl. 1; fig. 4a; N/G 25, fig. 1) (Fig. 11/4)

Laumes see Alise-Sainte-Reine (no. 20) (fig. 13/2)

36. Mâcon (R), Saône-et-Loire (idem no. 24, fig. 2c; N/G 22, fig. 2) (Fig. 10/7)

37. Nantes, Prairie de Mauves (H), Loire-Atlantique (N/G 24, fig. 7) (Fig. 16/10)

38. Ouroux-sur-Saône (R), Saône-et-Loire (idem no. 32, fig. 3c; N/G 23, fig. 4) (Fig. 10/6)

39. Paris, La Villette/Pont du Flandre (R) (idem no. 18; Mohen 1977: 159 f. [246 no. 75–21] 178, fig. 649) (Fig. 10/5)

40. Plainseau (H), Amiens, Somme (idem no. 17; N/G 22, fig. 3) (Fig. 8/1)

41. Pontpoint (SF), Oise (N/G 24 fig. 6) (Fig. 16/1)

42. Porcieu-Amblagnieu (H), Isère (Mortillet 1906; Coutil 1912; idem no. 25) (Fig. 12/5)

43. Questembert (H), Morbihan (idem no. 12) (Fig. 14/10)

44. Saône bei Chalon-sur-Saône or Gray (R), Saône-et-Loire (idem no. 22, fig. 3b; N/G 33 fig. 1; Thevenot 1998, 136, fig. 8, 2) (Fig. 13/4)

Seine, Paris (idem no. 20 = see „Angerville” [no. 21]) (fig. 11/3)

45. Seine between Corbeil/Villeneuve-St.-George (R) (idem no. 19; Mohen 1977: 159 f. [252 no. 91–12], 178 fig. 647) (Fig. 11/7)

46. St. Denis-de-Pile (H), Gironde (Coffyn 1969) (Fig. 7/2)

Tour de Langin see La Tour de Langin (no. 35) (fig. 11/4)

47. Trégorf-en-Surzur (H), Morbihan (Briard 1984: 163, fig. 13, 2; N/G 35, fig. 2) (Fig. 14/5)

48. „Provenance unknown” (Musée de la civilisation gallo-romaine Lyon) (Thevenot 1998: 136, fig. 8, 4) (modern copy of no. 20?) (Fig. 13/3)

Germany (D)

49. Altentreptow (SF?) Lkr. Mecklenburgische Seenplatte, Mecklenburg-Western Pomerania (Schoknecht 1974 [1975] : 166 [no illustr.; shape unknown])

50. Golchen, Lkr. Mecklenburgische Seenplatte, Mecklenburg-Western Pomerania (Schmidt 2014: 182, fig. 2, 5) (Fig. 9/5)

51. Lachen-Speyerdorf 1 (G), Stadt Neustadt an der Weinstraße, Rhineland-Palatine (Sperber 2000: fig. 2 (Fig. 14/1)

52. Lachen-Speyerdorf 2 (G), Stadt Neustadt an der Weinstraße, Rhineland-Palatine (Sperber 2000: fig. 10 (Fig. 16/7)

53. Maintal-Hochstadt (H), Main-Kinzig-Kreis, Hesse (Jockenhövel 1983: 587, fig. 1) (Fig. 16/4)

54. Murchin (H), Lkr. Vorpommern-Greifswald, Mecklenburg-Western Pomerania (Schoknecht 1974 [1975]: 163, fig. 10, 77; 359 no. E 314; 364 no. 363) (Fig. 11/8)

55. „Murnau” (H), Lkr. Rosenheim, Upper Bavaria (Nessel 2008: 58 no. 26, pl. 2, 26; 4, 26) (Fig. 13/5)

56. Oberwilflingen (H), Lkr. Ostalbkreis, Baden-Württemberg (Primas/Pernicka 1998) (Fig. 16/5. 5a)

57, 58. Ochtendung 1, 2 (H), Lkr. Mayen-Koblenz, Rhineland-Palatine (von Berg 2005) (Fig. 7/18; 12/1)

59. Plestlin (H), Gem. Bentzin, Lkr. Vorpommern-Greifswald, Mecklenburg-Western Pomerania (idem no. 34; Sprockhoff 1956: I 51; II 126, pl. 11, 6; J 364 no. E 364) (Fig. 11/5)

60. Ruthen (H), Lkr. Ludwigslust-Parchim, Mecklenburg-Western Pomerania (J 364 no. E 362; Sprockhoff 1956: I 31; II pl. 73, 17 [Holzendorf]; Hundt 1997: 63 no. 129, pl. 36, 17) (Fig. 9/3)

61. Steinkirchen (G; Grave 10), Gem. Stephansposching, Lkr. Deggendorf, Lower Bavaria (Müller-Karpe 1969: 89, fig. 3) (Fig. 7/21)

Hungary (H)

62. Biharugra (H), Kom Békés (Gallus/Horváth 1938, 92, pl. 19, B 8 [Ugra]; Kemenczei 2005: 131 f. B 6 (no. 95), pl. 16, A 95 („hammer”) (Fig. 9/8)

63. Esztergom (H), Kom. Komárom-Esztergom (Mozsolics 1985: 116 ff. 118 no. 91, pl. 138, 9) (Fig. 12/6)

64, 65. Lesenceistvánd 1, 2 (H), Kom. Veszprém (Mozsolics 1985: 144 no. 9, Pl. 270 A, 22. 24) (Fig. 7/16. 17)

66. Mátraszőlő-Kerekbükk, (H) Kom. Nógrád (Szabó 2011: 337, fig. 2, 3 [no illustration; „small anvil”)

67–69. Nadap 1–3 (H), Kom. Fejér (Makkay 2006: pl. 19, 166. 167; 20, 184) (Fig. 7/5–7)

70, 71. Tállya-Várhegy 1, 2 (H), Kom. Borsod-Abaúj-Zemplén (Szabó 2013: 812 f., fig. 18) (Fig. 6/8. 9)

72, 73. Velem-Szentvid 1, 2 (S), Kom. Vas (von Miske 1908: pl. 29, 7. 8) (Fig. 14/8)

74. Velem-Szentvid 3 (S; mould), Kom. Vas (von Miske 1908: pl. 22, 3) (Fig. 14/9)

Ireland (IRL)

75. Bishopsland 1 (H), Co. Kildare (Eogan 1983: 36 f. no. 16; 226, fig. 10, 11; idem no. 9) (Fig. 13/6)

76. Cullen (H), Co. Tipperary (Eogan 1983: 155 ff. no. 135 [no illustration])

77. „Ireland” (idem no. 11; Coffey 1913: 27 f., fig. 22 [Bronze Age?]) (no illustration)

78. Lusmagh (H), Co. Offaly (idem no. 10, fig. 3a; Eogan 1983: 192–193 no. 22; 321, fig. 105, B 6) (Fig. 15/5)

79. „Near Sligo”, Co. Sligo (Bronze Age?) (Milligan 1885–1886: 538, fig.; idem no. 8) (Fig. 6/1)

Omagh (123): see United Kingdom, Northern Ireland (fig. 11/1)

Italy (I)

80. Bologna-San Francesco 1 (H), Emilia-Romagna (idem no. 31; Iaia 2014: no. IB6; 103, fig. 9 [IB6]) (Fig. 9/2)

81. Bologna-San Francesco 2 (H), Emilia-Romagna (Iaia 2014: no. IB5; 103, fig. 9 [IB5]) (Fig. 16/11)

82. Bor di Pacengo (S), Verona (Iaia 2014: no. IB3; 103 fig. 9 [IB2]) (Fig. 15/8)

83. Contigliano (H), Rieti (Ponzi Bonomi 1970: 129, fig. 12, 4) (Fig. 9/2)

84. Falerii (G), Civita Castellana, Viterbo, Mazzano Romano (Montelius 1905/1910: pl. 329, 8 [iron]) (Fig. 7/19).

85. Frattesina (S), Rovigo (Iaia 2014: no. IB2; 103, fig. 9 [IB2]) (Fig. 11/13)

86. Gorzano (S), Modena (Iaia 2014: no. IB1; 103, fig. 9 [IB1]) (Fig. 14/6)

87. Monte Cavanero (Chiusa di Pesio) (H), Cuneo (Iaia 2014: no. IB7; Venturino Gambari 2009: 63, fig. 45; 60, fig. 42, 4) (Fig. 6/4)

88. Redù, Modena (Iaia 2014: no. IB4; 103, fig. 9 [IB4]) (Fig. 16/2)

Sardinia

89. Chiaramonti (S; Nuraghe Su Cobelciu) (Lo Schiavo 2018: 429 fig. 4. 5) (Fig. 15/1)

90, 91. Lei/Silanus-La Maddalena (H) (Lo Schiavo 2018: 429 fig. 4, 4. 9) (Fig. 6/2. 7)

92. Lotzorai-Genna Tramonti (Lo Schiavo 2018: 430 fig. 4, 8) (Fig. 6/6)

93. Lula-Savadde (H) (Lo Schiavo 2018: 429 fig. 4, 3) (Fig. 7/4)

94. Nuragus-Forraxi Nioi (H) (Lo Schiavo 2018: 428 fig. 4, 1) (Fig. 11/10)

95. Ozieri-Chilivani (H) (Lo Schiavo 2018: 428m fig. 4, 7) (Fig. 15/3)

96. „Provenance unknown” (Sardinia?) (Lo Schiavo 2018: 428 fig. 4, 2) (Fig. 11/11)

97. „Provenance unknown” (Sardinia?) (Lo Schiavo 2018: fig. 4, 6) (Fig. 15/2)

98. „Provenance unknown” (Sardinia) (Lo Schiavo 2018: fig. 4, 10) (no illustration)

Poland (PL)

99. Przemyśl (H) (Gedl 2004: 72 no. 251, pl. 18, 251) (Fig. 7/14)

100. Świnoujście-Międzyzdroje (H), Woj. Zachodniopomorskie (J 365 no. E 369; Blajer 1984: 54 no. 155, pl. 96, 30) (Fig. 9/4)

101. Witkowo (H), Woj. Pomorskie (idem no. 32; J 365 no. E 370; Gedl 2004: 72 no. 252, pl. 18, 252) (Fig. 7/11)

Romania (RO)

102. Fratelia (H), Timișoara (Medeleț 1995: fig. 3) (Fig. 7/3)

103. Gușterița (H), com. Sibiu (Gogâltan 2005: 31, pl. 12, 65b) (Fig. 16/3)

Serbia (SRB)

104. Velebit, Kanjiža, Severno-Banatski okrug (Fig. 4/3; 5/4, 5; 12/7)

Spain (E)

105. Valdevimbre (H), prov. León (Monteagudo 1977: 98 f. no. 607, 625, pl. 149, B 1) (Fig. 8/3)

Sweden (S)

106. Bromma, Ivetofta (W), Skåne (Oldeberg 1974: 17 no. 83; J 365 no. E 366) (Fig. 16/8)

107. Holmedal (SF), Varmland (Oldeberg 1974: 366 no. 2625; J 365no. E 367) (Fig. 16/9)

Switzerland (CH)

108. Auvernier 1 (S; mould), Kt. Neuchâtel (Gross 1883: pl. 29 12; Rychner 1979: pl. 134, 3) (Fig. 7/12)

109. Auvernier 2 (S), Kt. Neuchâtel 2 (idem no. 28; Rychner 1979: pl. 125, 9) (Fig. 7/13)

110. Grandson-Corcelettes (S; mould), Kt. Vaud (Musée cantonal vaudois 1896: pl. 30, 3; idem no. 27) (Fig. 14/3)

111. Riddes (SF), Kt. Valais (idem no. 26, fig. 2d; N/G 32, fig. 3; Wyss 1967: 10, pl. 3) (Fig. 12/4)

112, 113. Zürich-Wollishofen 1, 2 (S), Haumesser, Kt. Zürich (idem no. 29, fig. 4b; N/G 26, fig. 2; Wyss 1967: 10, pl. 2, 3) (Fig. 6/3; 11/6)

Ukraine (UA)

114. Nedilys'ka (H) [Неділіська, ehem. Niedzielska], Oblast Lwiw (Gedl 2001, 63: pl. 80, C 64 [iron]) (Fig. 7/9)

United Kingdom (GB)

England

115. Flax Bourton (H?), Somerset (idem no. 4; Pearce 1983: 514. no. 651a, pl. 74, 651a.) (Fig. 11/12)

116. Lakenheath, Suffolk (idem no. 2: „simple; gabled work-surface opposite spike”) (no illustration)

117. Lichfield (H), Knowle Farm, Staffordshire (Meeks/Needham 1993) (Fig. 8/4)

118. Netherhampton (H [„Salisbury Hoard”]), Wiltshire (MacGregor 1987: 109 [no. 11.67]; Stead 1998: fig. 6) (Fig. 8/5).

119. St. Leonards, Marina (H), Sussex, England (idem no. 3; Rowlands 1976: pl. 3, 7) (Fig. 10/1)

120. West Row, Suffolk (idem no. 1: „simple; T-shape with flat work surface; no additional features”) (no illustration)

Scotland

121. Inshoch Wood (H), Nairn (Childe 1945/46; idem no. 5, fig. 2b) (Fig. 11/2)

122. Kyle of Oykel („cairn”), Sutherland (Smith 1881; idem no. 6, fig. 1) (Fig. 13/8)

Northern Ireland

123. Omagh (H; mould), Co. Tyrone (Ó Faoláin 2004: 155 [no. 2], 208, fig. 12, 2) (Fig. 11/1)

Channel Islands, Jersey

124. Clos de La Blanche Pierre, St. Lawrence (Coombs 1988: 325, fig. 6, 69) (Fig. 7/15)

Socketed hammerheads used as anvils (?)

(selected examples: Fig. 17)

Deville-les-Rouen (H), Seine-Maritime, France (Verron 1971: 65 f., fig. 54) (no illustration)

Génélard 5 (H), Saône-et-Loire, France (Thevenot 1998: 125, fig. 1, 3) (Fig. 17/4)

Génélard 6 (H), Saône-et-Loire, France (Thevenot 1998: 126, fig. 2, 1) (Fig. 17/2)

Génélard 7 (H), Saône-et-Loire, France (Thevenot 1998: 126, fig. 2, 2) (Fig. 17/3)

Hallstatt (G; grave 469), Upper Austria (Kromer 1959: 110, fig. 91, pl. 82–84) (Fig. 17/10).

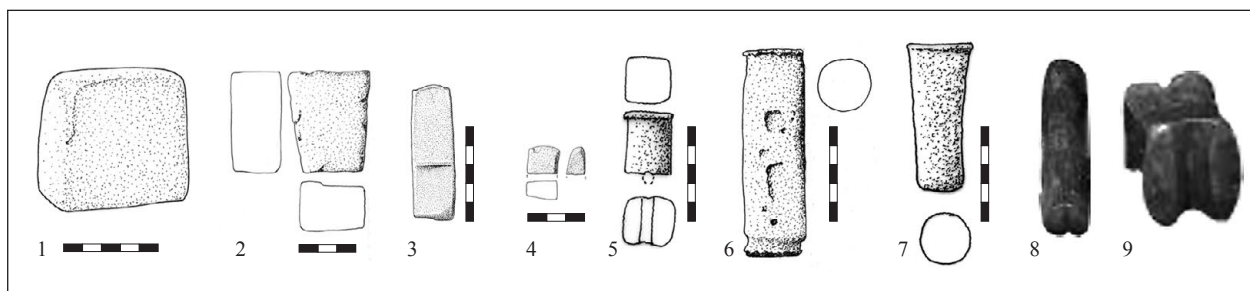


Fig. 6. Class 1, subclass 1a. Bench/block anvils: 1) “Near Sligo” (no. 71); 2, 7) Silanus (nos. 90, 91); 3) Zürich-Wollishofen (no. 113); 4) Monte Cavanero (Chiusa di Pesio) (no. 87); 5) Brno-Rečkovice (no. 11); 6) Lotzaroi-Genna Tramonti (no. 92); 8, 9) Tállya-Várhegy (nos. 70, 71). – Bronze. – M. 1:3 (8, 9 no scale)

Сл. 6. Класа 1, њојкласа 1а: њљоснањио-равни наковњњи, бронза, R 1 : 3

Rýdeč 1 (H), okr. Ústí nad Labem, Bohemia (Kytlicová 2007: 301 no. 207 [95: „fitting”], pl. 88, 95) (Fig. 17/5)

Rýdeč 2 (H), okr. Ústí nad Labem, Bohemia (Kytlicová 2007: 301 no. 207 [253], pl. 94, A 253) (Fig. 17/6)

Schiltern 1, 2 (H), Lower Austria (Girtler 1970; Hansen 1994: fig. 80, 1. 2) (Fig. 17/7. 8)

Tise (H), Hjørring amt, Denmark (Armbruster 2001: 11 fig. 2; J 242 no. 369, pl. 242) (Fig. 17/11)

Trenčianske Bohuslavice (H), okr. Nové Mesto nad Váhom, Slovakia (Novotná 1970: 99 no. 803, pl. 43, 803) (Fig. 17/1)

Zoggendorf (SF), com. Heiligenstadt, Lkr. Bamberg, Bavaria (Ausgrabungen und Funde in Oberfranken 11, 1997–1998: 20. 8, fig. 8, 5) (Fig. 17/9)

Terminology and classification

The English term *anvil* is currently used in archaeological literature mostly for pre-Iron Age tools. This refers to a blacksmith’s tool, whilst today, the smaller tools used by fine metalworkers are called *stakes*. However, considering how embedded this technical term is, we are using the term *anvil* in this paper.

Bronze Age metal anvils reveal different features and each functional group corresponds to a specific technical definition. When addressing function, anvils can be described as an inactive percussion tool or support for receiving hammer strikes. All anvils in this regard can be considered as two-piece tools because they consist of a metal and a wooden part in order to operate. The most important characteristic is the shape anvils have. The shape of an anvil can be pyramidal, truncated pyramidal, cylindrical, hollow cylindrical,

conical, truncated conical, spherical, hemispherical or barrel-shaped. Most anvils have a short or long spike (German: *Angel*; Serbian: *Трн*) for fitting to a wooden stump. Sometimes grooves and swages (German: *Sicken*, *Rillen*, *Kerben*, *Gesenk*; Serbian: *Шлape*) or hemispherical depressions are wrought into the working surface, which is called an anvil face (German: *Ambossbahn*; Serbian: *Лице наковња*). One or two lateral prolongations are named beaks but also spikes or tangs (German: *Horn/Stecken*; Serbian: *Поз*, *Pen*). Complex anvils can provide several working surfaces as well as beaks with round or rectangular cross sections. The central cavity in the anvil structure is called a punching hole (German *Nagelloch*, *Stanzloch*; Serbian: *Pyна*).⁵³

Considering the spectrum of various forms and functions, we can distinguish five main classes (and subsequent subclasses) of Bronze Age metal anvils.⁵⁴ Apart from certain exceptions with well-defined characteristics, we will not refer to „types” of anvils, because when considering the broader traits, each anvil can have an individual character.

Class 1: Bench, block and pyramidal (frustrum) flat anvils

Subclass 1a: Flat anvils (German: *Brettambosse*)

The block shaped flat anvils consist of a simple block of a more or less rectangular shape. The Bronze Age (?) anvil from „Near Sligo” (no. 79) in fact appears

⁵³ Jantzen 2008, 253, Abb. 90; Nessel 2009, 49, Abb. 12.

⁵⁴ Coutil 1912; Ohlhaver 1939; Drescher 1973, 250 fig. 34; Nicolardot/Gaucher 1975; Ehrenberg 1981; Eluère/Mohen 1993; Armbruster 2001; Jantzen 2008, 253–259, 326–333.

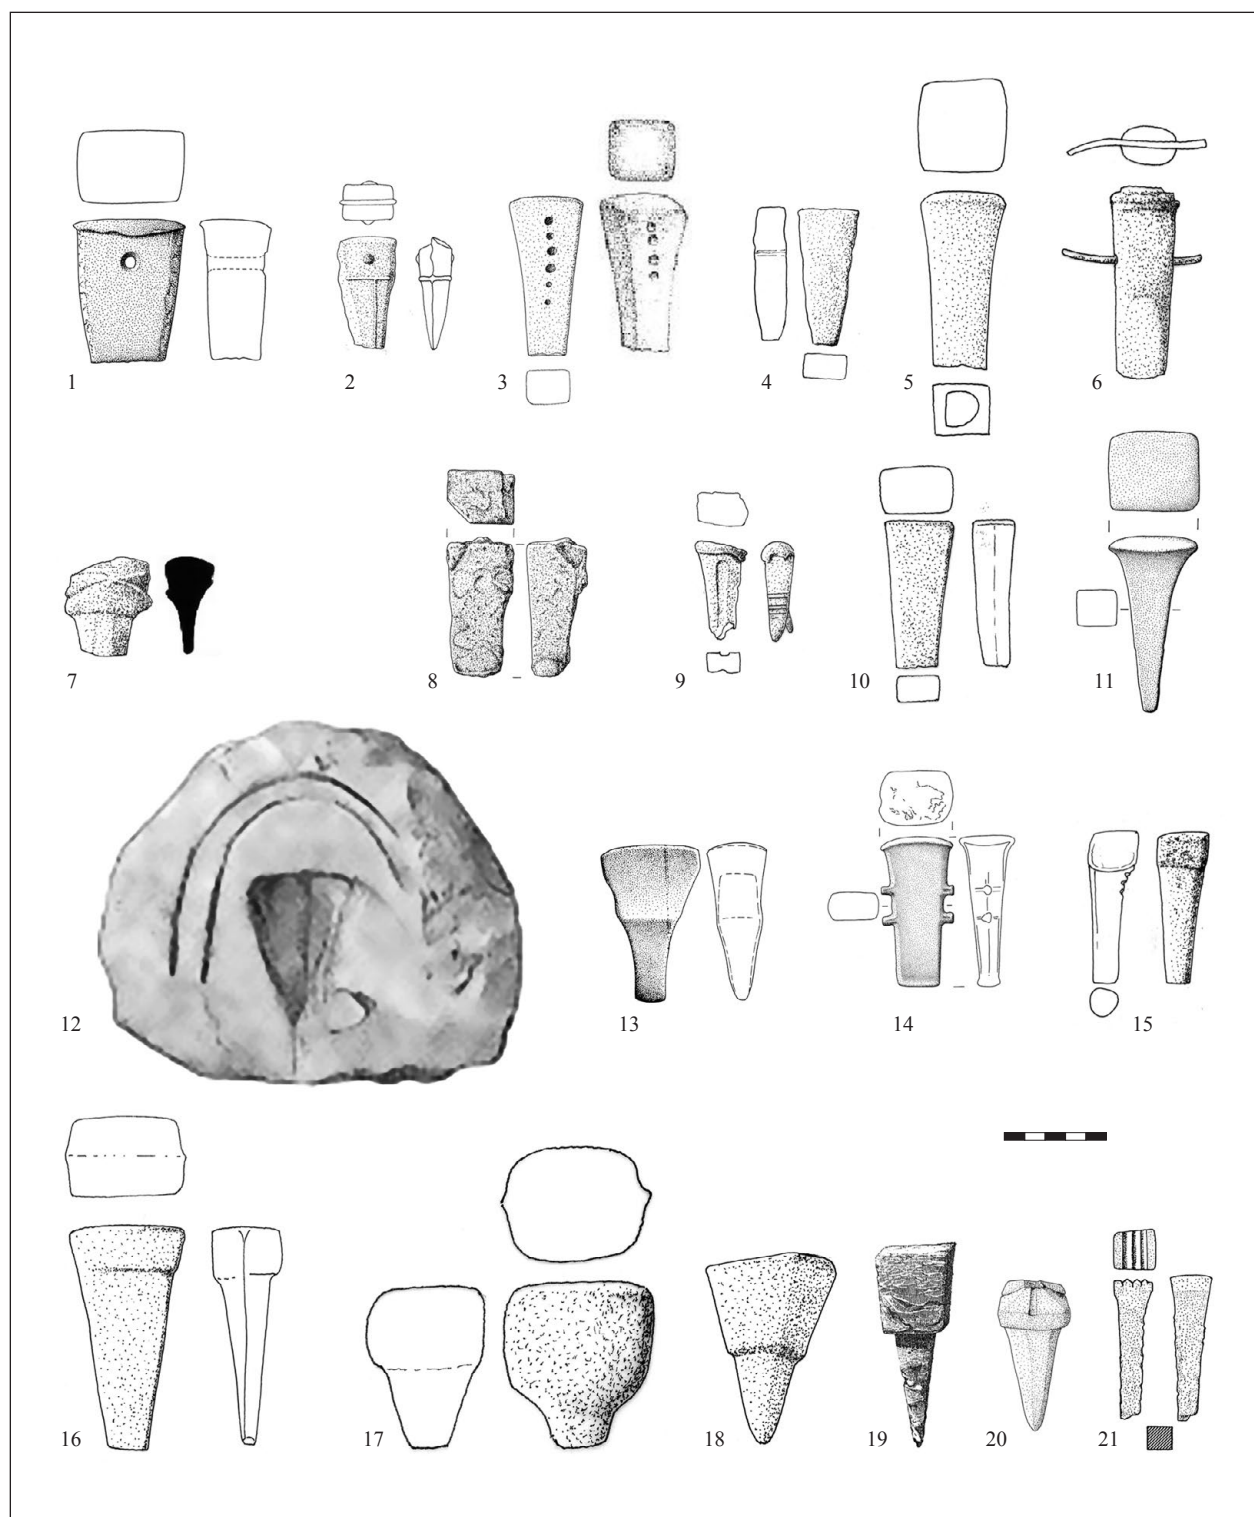


Fig. 7. Class 1, subclass 1b. Pyramidal (or frustrum) anvils: 1) Újezd (no. 8); 2) St. Denis-de-Pile (no. 46); 3) Fratelia (no. 102); 4) Lula-Savadde (no. 93); 5–7) Nadap (nos. 67–69); 8) Hallstatt (no. 2); 9) Nedilys'ka (no. 114); 10) Loučka (no. 16); 11) Witkovo (no. 101); 12, 13) Auvernier (nos. 108, 109); 14) Przemyśl (no. 99); 15) St. Lawrence, Jersey (no. 124); 16, 17) Lesenceistvand (nos. 64, 65); 18) Ochtendung (no. 57); 19) Falerii (no. 84); 20) Sulsted (no. 19); 21) Steinkirchen (no. 61). – Iron (8, 9, 19), all others Bronze. – M. 1:3

Сл. 7. Класа 1, пошкласа 1b: наковњи у облику пирамиде; 8, 9, 19) – њовжђе; остали – бронза, R 1 : 3

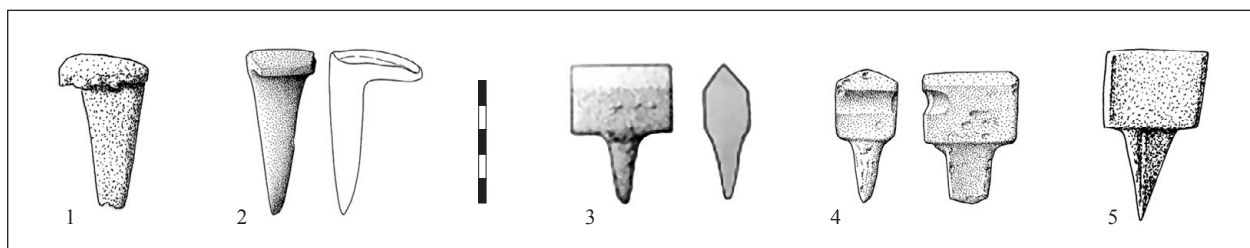


Fig. 8. Class 1, subclass 1c. Anvils with one lateral working surface: 1) Plainseau (Amiens) (no. 40); 2) Graville-Sainte-Honorine (no. 32). – Subclass 1d: Anvils with pentagonal body and a spike: 3) Valdevimbre (no. 105); 4) Lichfield (no. 117); 5) Netherhampton ("Salisbury Hoard") (no. 118). – Bronze. – M. 1:3

Сл. 8. Класа 1: 1–2) Пошкласа 1c: наковњи с једном радном површином; 3–5) Пошкласа 1d: наковњи пенијаоналног пресека са усадником, бронза, R 1 : 3

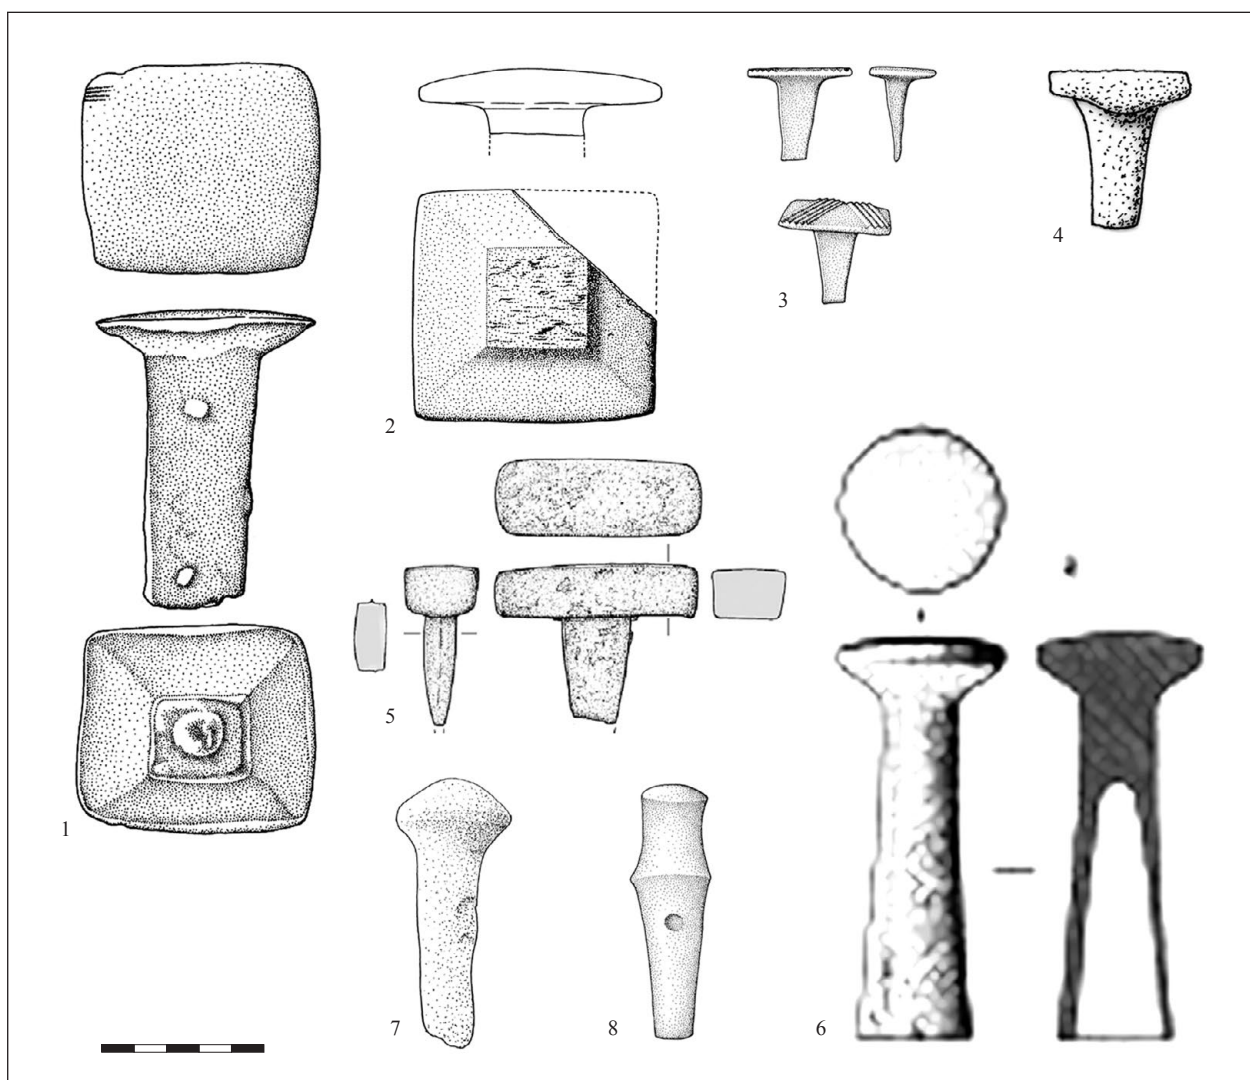


Fig. 9. Class 1, subclass 1e. Anvils with mushroom shaped working surface: 1) Contigliano (no. 83); 2) Bologna-San Francesco (no. 80); 3) Ruthen (no. 60); 4) Świnoujście-Międzyzdroje (no. 100); 5) Golchen (no. 50). – Subclass 1f. Anvils with plate shaped or hemispherical head: 6, 7) G nelard (nos. 31, 29); 8) Biharugra (no. 62). – Bronze. – M. 1:3

Сл. 9. Класа 1: 1–5) Пошкласа 1e: наковњи у облику њечурке; 6–8) Пошкласа 1f: наковњи са равном или калопасићом главом, бронза, R 1 : 3

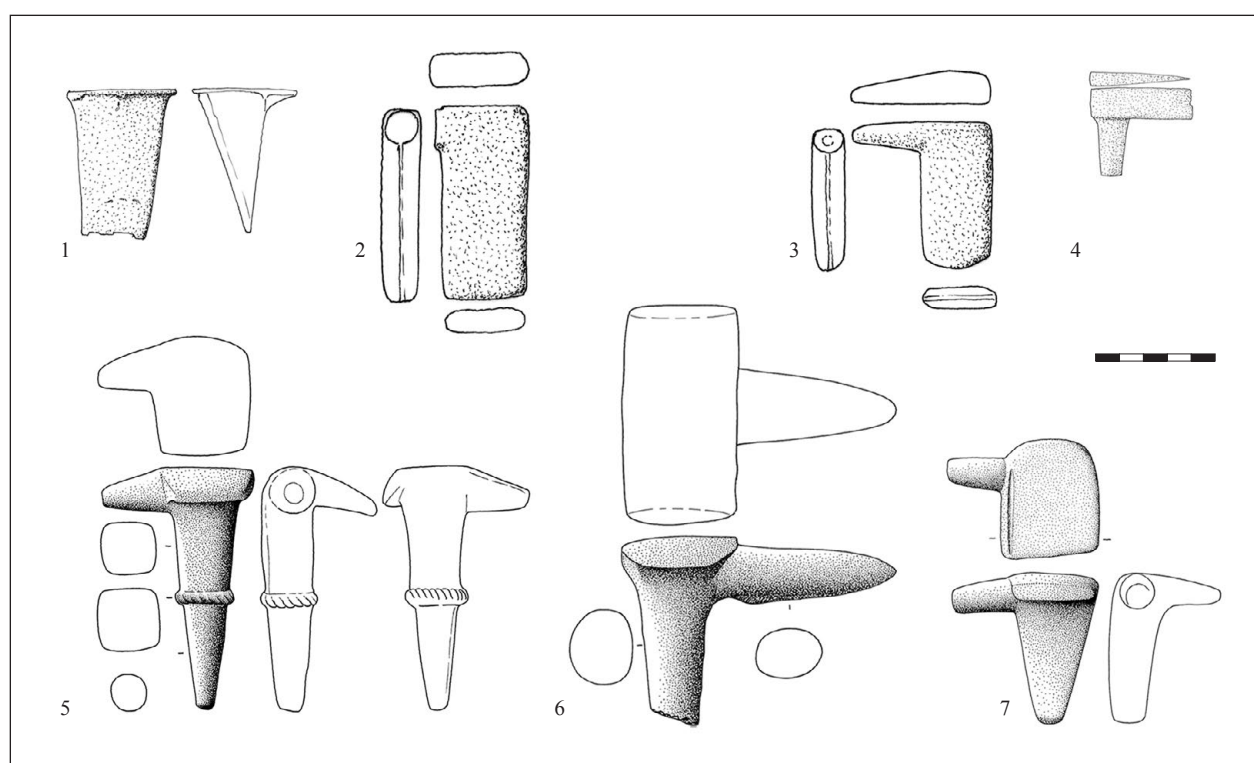


Fig. 10. Class 2, subclass 2a1: 1) St. Leonards, Marina (no. 119); 2, 3) Loučka (nos. 13, 15); 4) Velim (Bohemia) (no. 9); 5) Paris, La Villette/Pont du Flandre (no. 39); 6) Ouroux-sur-Saône (no. 38); 7) Mâcon (no. 36). – Bronze. – M. 1:3

Сл. 10. Класа 2, њојкласа 2a1: бронза, R 1 : 3

to be a „cushion stone” (Fig. 6/1). One block anvil has a gable shaped working surface (Fig. 6/4), and the flat anvil from Zürich-Wollishofen (no. 113) a horizontal feature for locking the anvil into a wooden surface (Fig. 6/3). Three other block anvils look like hammers. The anvil from Brno–Rečkovice (no. 11) has a rounded rectangular body with a punching hole (Fig. 6/5). Two Sardinian anvils (no. 92) have a cylindrical shape and two working surfaces (Lotzorai type according to Lo Schiavo) (Fig. 6/6). The two anvils (one with cylindrical, the other with a body like a hammer) with distinctive features from Tállya-Várhegy (no. 70–71) belong to this subclass (Fig. 6/8, 6/9).

Subclass 1b: Pyramidal (or frustum) anvils

Anvils of this kind have a truncated pyramid (frustum) body with or without a shaft and mostly a square, flat or slightly convex working surface (one anvil with a gable-roofed working surface [Fig. 7/2]) (Fig. 7). The frustum-anvil from Fratelia (no. 102) has a row of little bosses on two opposite faces of its body (Fig. 7/3). Two anvils have a punching hole in the body

(Fig. 7/1. 6). In one anvil from Nadap (no. 68) a bronze wire is pulled through the punching-hole (Fig. 7/6). The Late Bronze Age anvil from Nedilys’ka (Niedziel-ska) (no. 114) was made from iron and is decorated with two lines (no swages) on one side (Fig. 7/9). The hornless anvil from the hoard of Pryzmyśl (no. 99) has half way up the body on two opposite faces two adjacent small projections, which could have served as a rest for a wooden stump or to carry the tool (Fig. 7/14).⁵⁵ The stone mould from Auvernier (no. 108) belongs to this class (Fig. 7/12). Some anvils have significant wear marks from extensive forging (Fig. 7/1. 9. 14). The working surface of the small anvil from Steinkirchen (no. 61) is full of swages (Fig. 7/21). Three anvils (one in iron: from Falerii [no. 84]) are very similar to modern (German) *Steck-, Stock- or Stiftambosse* (Fig. 7/11. 18. 19).⁵⁶ The small (miniature?)

⁵⁵ Ohlhaver 1939: 23.

⁵⁶ Armbruster 2001: 17, fig. 12, 1.

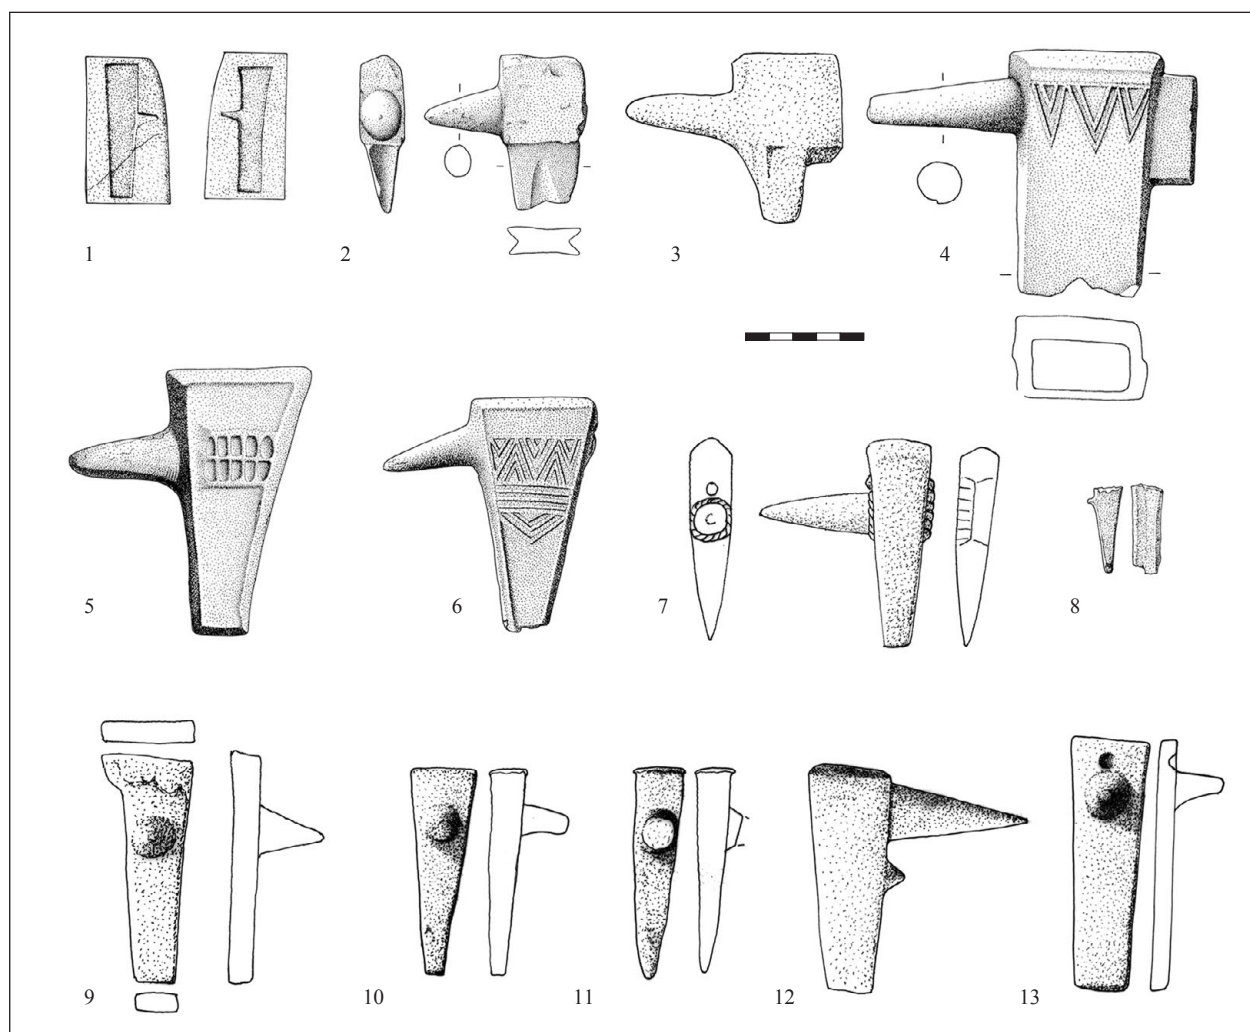


Fig 11. Class 2, subclass 2a2: 1) Omagh (no. 123); 2) Inshoch Wood (no. 121); 3) "Angerville" (no. 21); 4) La Tour de Langin (no. 35); 5) Plestin (no. 59); 6) Zürich-Wollishofen (no. 114); 7) Seine between Corbeil/Villeneuve-Saint-George (no. 45); 8) Murchin (no. 54); 9) Loučka (no. 14); 10) Nuragas-Forraxi Nioi (no. 96); 11) "Prov. unknown" (Sardinia?) (no. 96); 12) Flax Burton (no. 115); 13) Frattesina (no. 85). – Bronze. – M. 1:3

Сл. 11. Класа 2, њојкласа 2а2: бронза, R 1 : 3

anvil from Sulstedt (no. 19) has a pyramidal working surface with four crossing swages (Fig. 7/20).

Subclass 1c: Anvils with one lateral working surface

Two anvils of this subclass are characterised by one lateral working surface which is adjacent to the conical protrusion (Fig. 8/1. 2).

Subclass 1d: Block anvils with pentagonal body and a spike

Anvils without a beak have a spike for fitting and a pentagonal body with a gable-roofed working surface (Fig. 8/3–5).

Subclass 1e: Anvils with a mushroom-shaped working surface

These anvils have a flat rectangular body with a mushroom-shaped working surface⁵⁷ and a hollow-based and tapered shaft (Fig. 9/1–5). The anvil from Ruthen (no. 60) has two arrangements of grooves, shaped like chevrons, which are incorporated into the working surface of the anvil, probably for making plastic decorations on thin sheets (Fig. 9/3).

⁵⁷ Jantzen 2008, 330 (A 1): German: *pilzförmige Ambosse*.

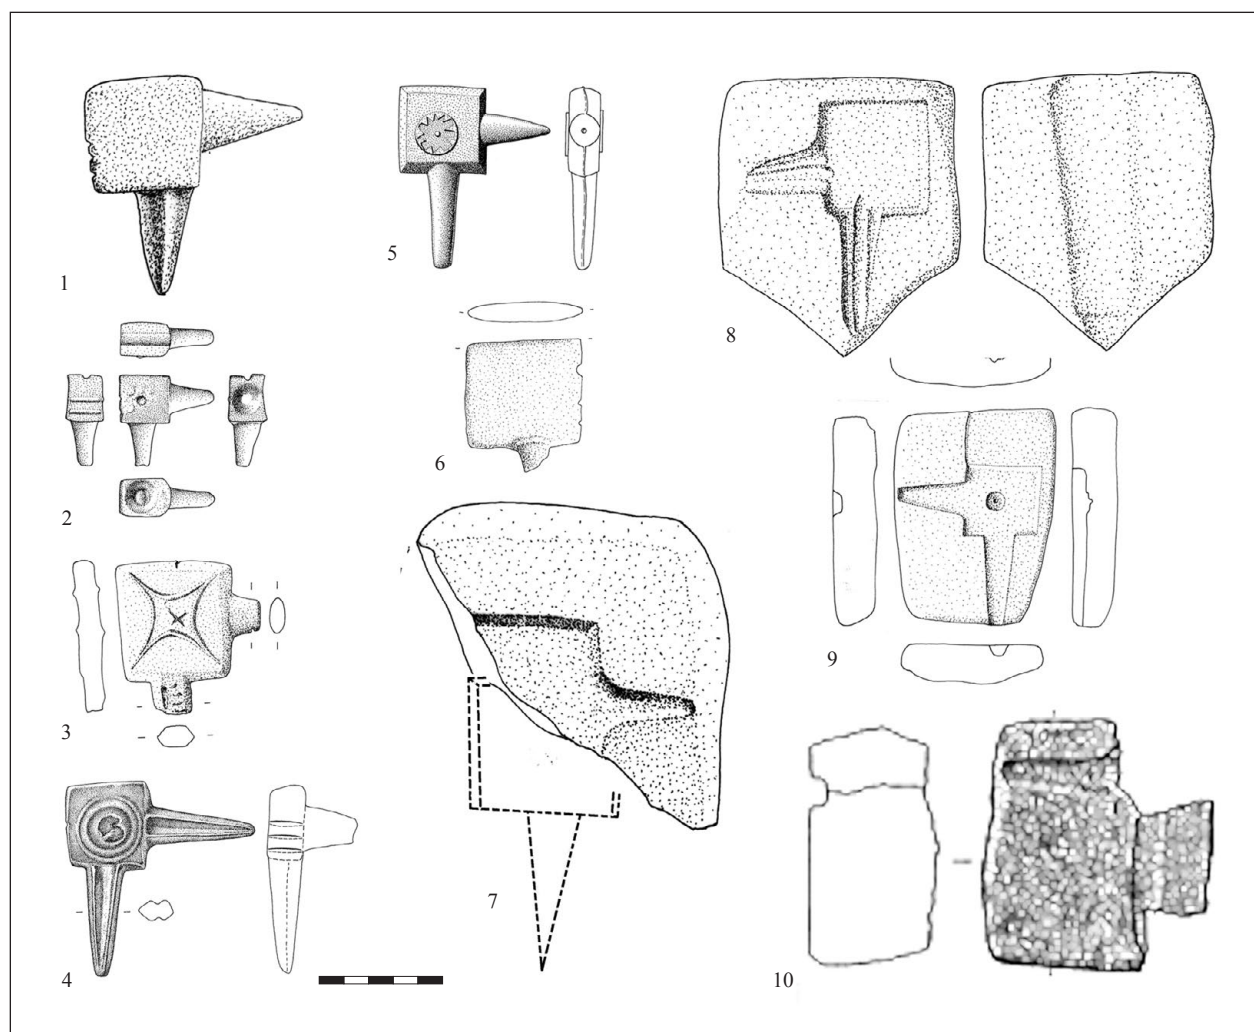


Fig. 12. Class 2, subclass 2b: 1) Ochtendung (no. 58); 2) Sengløse (no. 18); 3) Boljanić (no. 4); 4) Riddes (no. 111); 5) Porcieu-Amblagnieu (no. 42); 6) Esztergom (no. 63); 7) Velebit (reverse) (no. 104); 8) Fort-Harrouard (no. 26); 9) La Lède-du-Gurp (no. 33); 10) Cuiry-lès-Chaudardes (no. 25). – Bronze. – M. 1:3

Сл. 12. Класа 2, њојкласа 2b: бронза, R 1 : 3

Subclass 1f: Anvils with a plate-shaped or hemispherical working surface

Anvils of this kind are characterised by a plate-shaped or hemispherical working surface and a socketed shaft or hollow-based shaft with a round cross section (Fig. 9/6–8).

Class 2: Anvils with one or more beaks (German: Hornambosse)

Subclass 2a1: Anvils with one lateral beak fixed on the same level as the working surface

Anvils of this subclass have a beak which is fixed on the same level as the working surface either at one

corner (Fig. 10/5–7) or in the middle of the working surface. The anvil of Paris-La Villette/Pont du Flandre (no. 39) has a plastic rib, with twisted decorations for better hafting, in the middle of the round conical shaft (Fig. 10/5). The dimensions of the working surface range from approximately 4 to 8 cm.

Subclass 2a2: Anvils with one lateral beak fixed a little below the working surface

Anvils such as these have a long and narrow, usually gable shaped working surface and one lateral beak, fixed below the working surface. On the body of the anvil from the Seine between Corbeil/Villeneuve-Saint

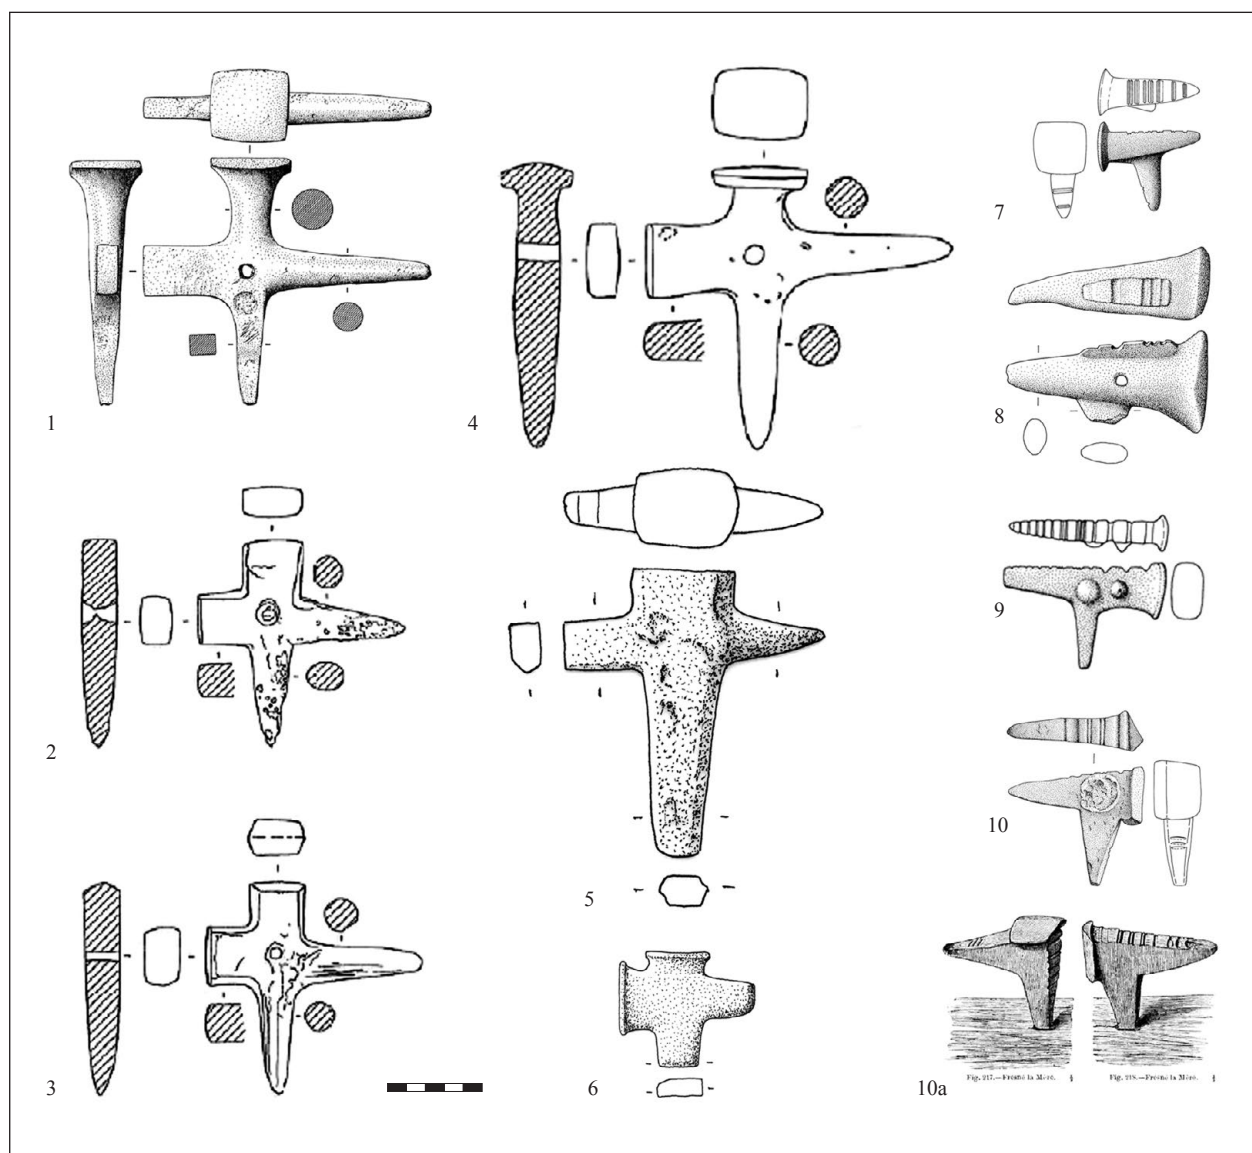


Fig. 13: Class 2, subclass 2c: 1) G nelard (no. 30); 2) Alise-Sainte-Reine/Laumes (no. 20); 3) Mus. Lyon (Prov. unknown) (no. 48); 4) Sa ne near Chalon-sur-Sa ne/Gray (no. 44); 5) "Murnau" (no. 55); 6) Bishopsland (no. 75). – Subclass 2d: 7) Seine bei Bardouville (no. 22); 8) Kyle of Oykel (no. 122); 9) Coray (Keranfinit) (no. 24); 10) Fresn -la-M re (no. 27) (10a hafting: Fresn  [after Evans 1881, 182 fig. 217, 218]). – Bronze. – M. 1:3

Сл. 13. Класа 2: 1–6) Поїкласа 2с; 7–10) Поїкласа 2д, бронза, R 1 : 3

George (no. 45) there is a ridge with swages (Fig. 11/7). The shaft is broad and has a rectangular cross-section. The anvil from La Tour de Langin (no. 35) has a socketed shaft instead of a solid shaft (Fig. 11/4). A remarkable feature is the plastic decoration some anvils have (Fig. 11/4–6). In that regard we can observe that both the hollow shaft and the plastic decoration are the result of casting using the lost wax technique.

Subclass 2b: Anvils with two lateral beaks fixed in the middle of the anvil block (Type Porcieu-Amblagnieu)

Anvils of this type (Type Porcieu-Amblagnieu) have an elongated, albeit relatively small, working surface (4 x 1.5–2.1 cm) and two conical beaks located in the middle of the rectangular or square block (Fig. 12). Some anvils are decorated with a cast plastic decoration

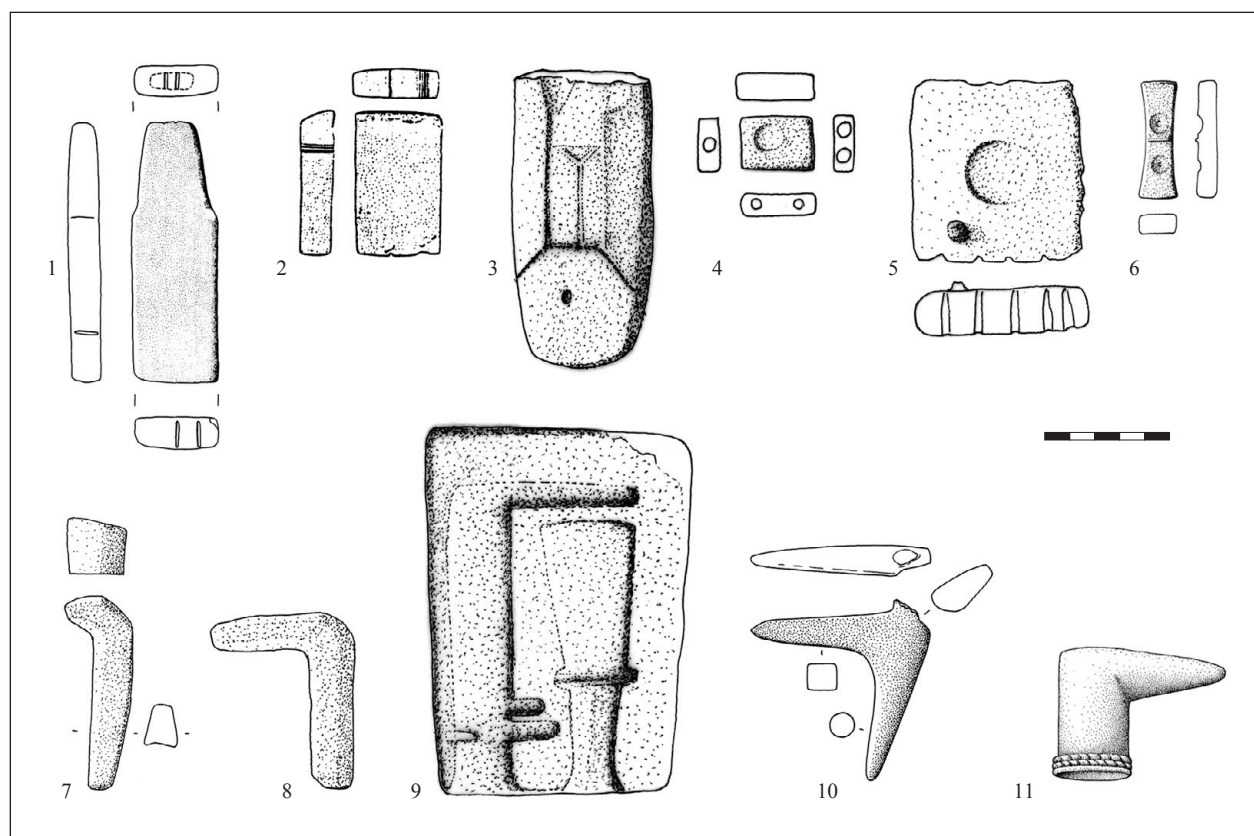


Fig. 14. Class 3. Bench anvils with swages and bosses: 1) Lachen-Speyerdorf (no. 51); 2) G  nelard (no. 28); 3) Grandson-Corcelettes (no. 110); 4) Larnaud (no. 34); 5) Tr  gorf-sur-Surzur (no. 47); 6) Gorzano (no. 86). – Class 4. Bent anvils: 7) Sipbachzell (no. 3); 8, 9) Velem-Szentvid (nos. 72, 73); 10) Questembert (no. 43); 11) Jevi  ko (no. 12). – Bronze. – M. 1:3

Сл. 14. Класа 3: 1–6) Равни наковњи са удубљењима и исц  пљењима; 7–10) Савијени наковњи, бронза, R 1 : 3

on each lateral side of the body featuring knobs, concentric ribs, rosettes, or an X shape nestled in a pillow-shaped rib (Fig. 12/3–5). The four stone moulds from Velebit (no. 104), Cuiry-l  s-Chaudardes (no. 25), Fort-Harrouard (no. 26) and La-L  de-du-Gurp (no. 33) all belong to this subclass.

Subclass 2c: Anvils with two working surfaces and two lateral beaks

(T-shaped anvils / Type Chalon-sur-Sa  ne/Gray)

Anvils of this subclass include three-armed anvils with a cruciform outline. They consist of a body with two working surfaces (1.5 to 4.5 cm) and two conical beaks. Swages are present only on the smaller working surface of the anvil from Murnau (no. 55) (Fig. 13/5). A common feature of four very similar anvils (Type Chalon-sur-Sa  ne/Gray) is a punching hole in the middle of the anvil block (Fig. 13/1–4). It is plausible

that the anvils from Alise-Sainte-Reine/Laumes (no. 20) and „Provenance unknown”/Mus. Lyon (no. 48) were cast in the same mould. This seems probable because of their identical features, dimensions and weights (Fig. 13/2.3) or another possibility is that the last one is a modern copy. We should also highlight that these multiple-armed anvils are multifunctional.

Subclass 2d: Anvils with one working surface, one beak as a shaft and one additional beak (Type Fresn  -la-M  re)

The four very similar anvils of this subclass (Type Fresn  -la-M  re) have one small rectangular working surface, a beak which can also be used as a shaft, as well as an additional beak (Fig. 13/7–10). It was possible to work on this anvil in two different positions (Fig. 13/10a). Several swages are on a ridge-shaped or comb-shaped elongation. One anvil has a punching hole (Fig. 13/8).

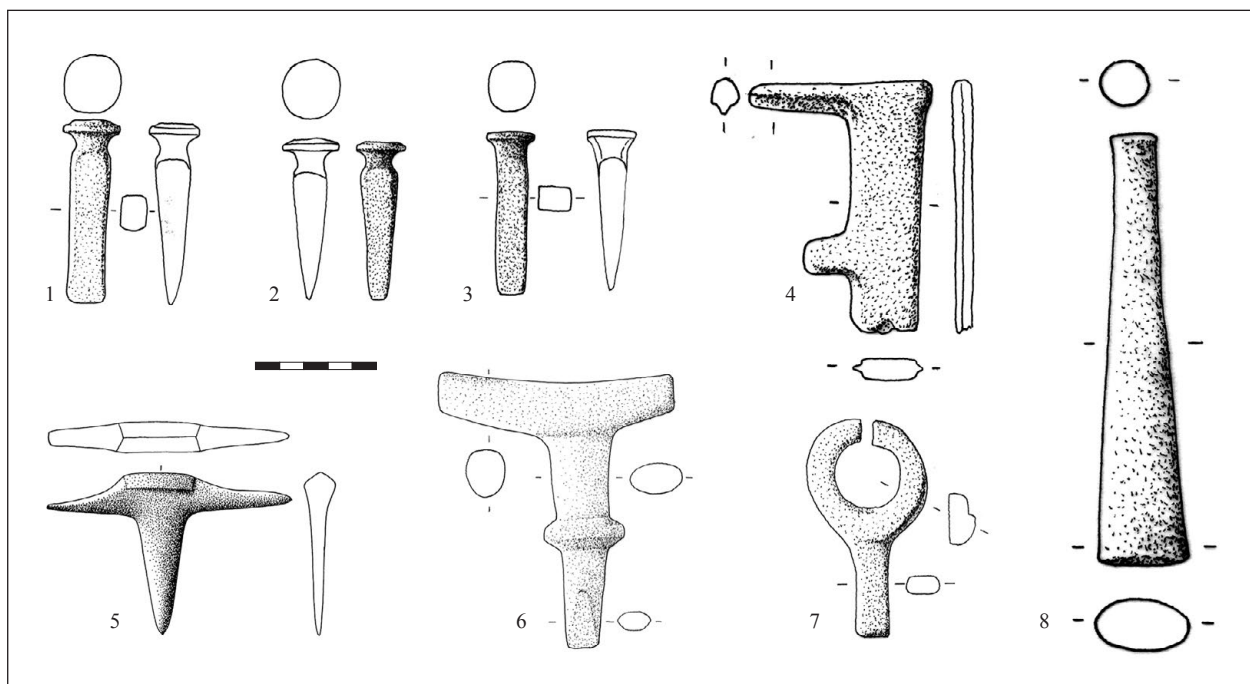


Fig. 15. Class 4. Beating fists: 1) Chiaramonti (no. 89); 2) “Prov. unknown” (Sardinia?) (no. 97); 3) Ozieri (no. 95). – Anvils with special features: 4) Blučina (no. 10); 5) Lusmagh (no. 78); 6, 7) Boljanić (nos. 5, 6); 8) Bor di Pacengo (no. 82). – Bronze. – M. 1:3

Сл. 15. Класа 4: 1–3) Наковњи за искуцавање; 4–8) Наковњи специфичних облика, бронза, R 1 : 3

Class 3: Bench anvils with swages and bosses

Some flat and rectangular bench anvils with an upper and lower working surface have one or more small sides with one or more swages (Fig. 14/1–6). These tools are named swage blocks (German: *Riefenanken*) (Fig. 14/1–3). The stone mould from Grandson-Corcelles belongs to this group of anvils (Fig. 14/3). The flat bench anvils could be mounted in different ways into depressions provided in a wooden stump. The flat anvil from Lachen-Speyerdorf has a broad shaft with two swages (Fig. 14/1). Another form, with massive flat plate-shaped bronze blocks with a rectangular or dovetail shape, is characterised by bosses and/or swages. These were used as swage blocks and doming blocks (German: *Kugelanken*) (Fig. 14/4–6).

Class 4: Bent anvils

Some anvils belong to the class of bent anvils (German: *Biegestöcke*) (Fig. 14/7–11). They are shaped as bent rods with a round, trapezoidal or D-shaped cross-section. Both parts of the bent rod could be used as a working surface. On the shorter part of the bent rod of the massive anvil from Sipbachzell (no. 3) there are

two pronounced working surfaces (Fig. 14/7). From Velem-Szentvid (no. 73) a casting mould for a bent anvil is known. This mould has two casting negatives, one for an anvil and the second for a socketed hammerhead (Fig. 14/9). The bent anvil from Jevičko (no. 12) has a socketed shaft decorated with a cord-like twisted plastic decoration (Fig. 14/11).

Class 5: Beating fists (Fig. 15/1–3)

Three Late Bronze Age anvils from Sardinia are very similar to each other (nos. 89, 95 and 97) (Fig. 15/1–3). F. Lo Schiavo named them Type Chiaromonti.⁵⁸ The wedged-shape anvils have a conical form with a rectangular cross-section. The body changes its cross-section from the shoulder to a round neck. The working surface is disc-shaped. These anvils are quite long (ca. 17–20 cm) and the dimensions of the round-convex working surface ranges between ca. 5–7 cm. These tools look very much like modern beating fists (German: *Treibfäuste*).

⁵⁸ Lo Schiavo 2018.

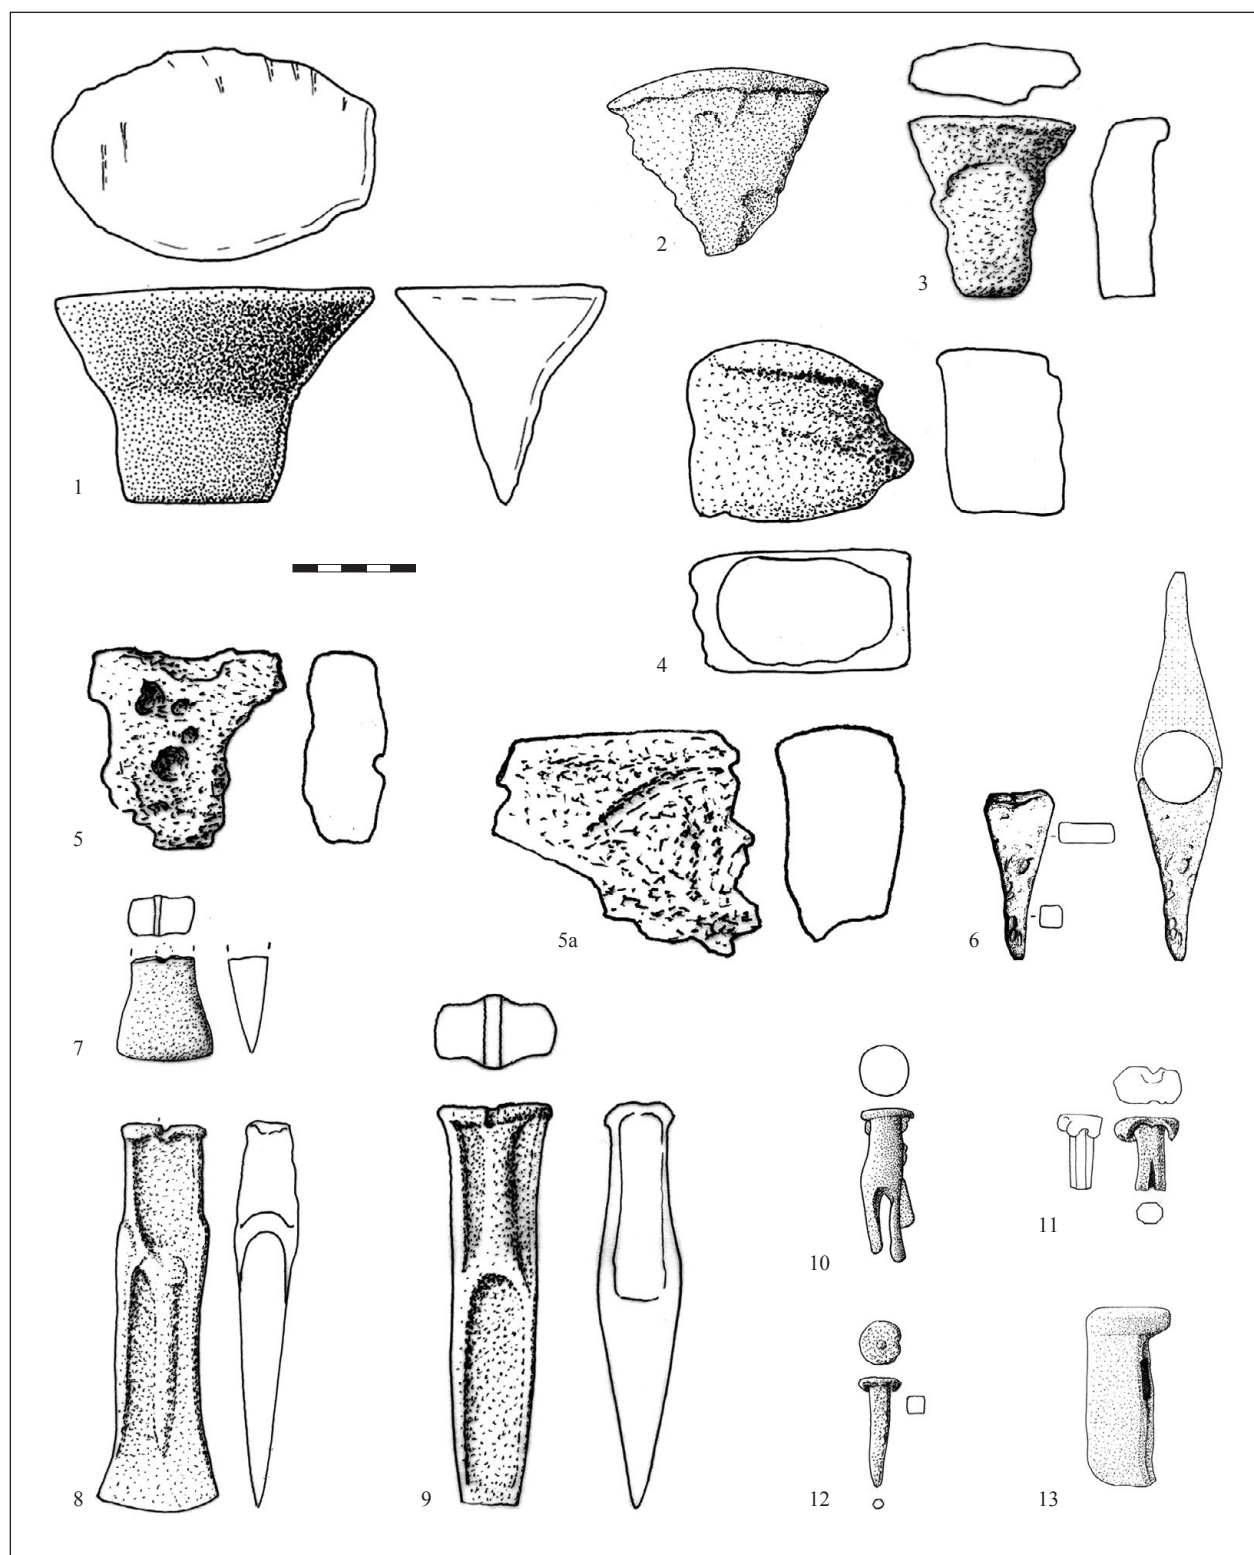


Fig. 16. Ad-hoc- anvils: 1) Pontpoint (no. 41); 2) Jarpice (no. 7); 3) Gușterița (no. 103); 4) Maintal-Hochstadt (no. 53); 5, 5a) Oberwilflingen (no. 56); 6) Lachen-Speyerdorf (no. 52); 7) Damsholte (no. 17); 8) Bromma (no. 106); 9) Holmedal (no. 107); 10) Nantes-Prairie de Mauves (no. 37); 11) Bologna-San Francesco (no. 81); 12) Redù (no. 88); 13) Augsdorf (no. 1). – Bronze. – M. 1:3

Сл. 16. Ad hoc наковњи, бронза, R 1 : 3

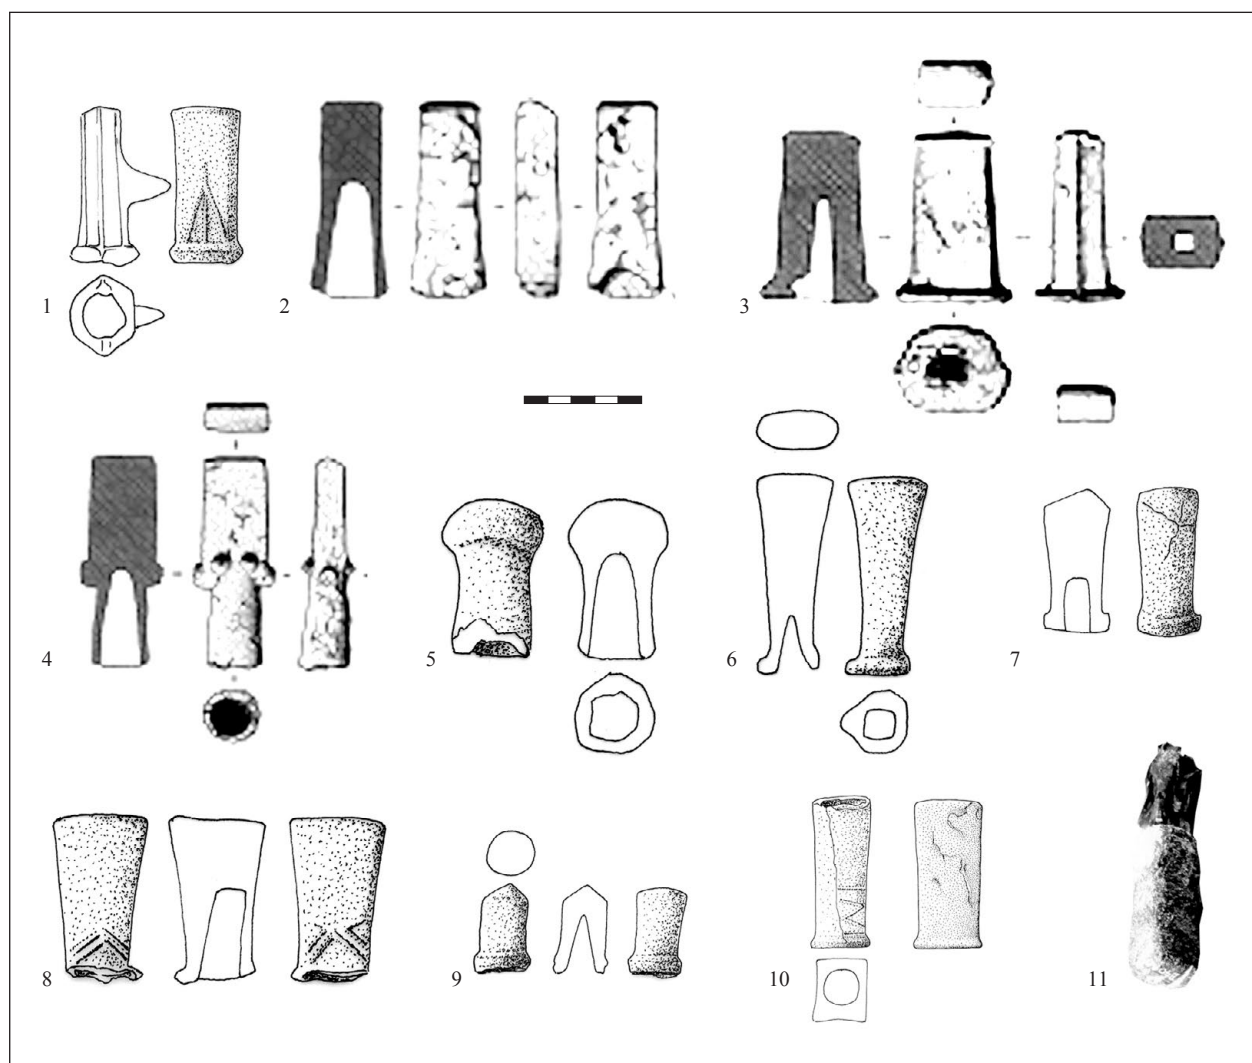


Fig. 17. Socketed hammerheads as anvils: 1) Trenčianske Bohuslavice; 2–4) G nelard; 5, 6) Ryde ; 7, 8) Schiltern; 9) Zoggendorf; 10) Hallstatt (Grave); 11) Tise. – Bronze. – M. 1:3

Сл. 17. Наковњи у облику чекића са усадником, бронза, R 1 : 3

Anvils with special features

Some anvils are characterised by special features (Fig. 15/4–8). The anvil from Blu ina (no. 10) with its long, small working surface and a lateral beak at the same level is similar to anvils of class 2a. In the middle of the rectangular shaft there is a short lateral beak, perhaps for better hafting (Fig. 15/4). The T-shaped goldsmith-anvil from Lusmagh (no. 78) of a narrow rectangular shape also has a long, small, gable-roofed working surface and two long beaks (one rectangular, the second one with a round cross-section) on the level of the working surface (Fig. 15/5). One anvil from „Sardinia” (no. 98, no illustration.) has a very similar

outline. Both anvils look like the so called (German) *Sperrhaken*. The T-shaped anvil from Boljani  (no. 6) with a collared shaft for better hafting in a wooden stump is similar to the Sardinian anvil (Fig. 15/6). The third exemplar from Boljani  (no. 7) looks like a clamp; and it was possible to work on the outside of the curved beaks (Fig. 15/7). A long (22.9 cm) and very heavy (1.8 kg!) bronze tool (composition with a high tin-content [13 %]) from the lake village of Bor di Pacengo (Upper Italy) (no. 82) has on both ends a round or oval working surface with clear traces of use. Perhaps it is an anvil or a pestle for a mortar to crush metal or other materials (Fig. 15/8).

Ad-hoc-anvils (Fig. 16)

Some Anvils were made from reused bronze material of different origin (Fig. 16). On the one hand, ingot fragments were used as flat anvils (plano-convex ingot: Maintal-Hochstadt [no. 53], Jarpice [no. 7], Pontpoint [no. 41], Gusterița [no. 103]; oxide-ingot:⁵⁹ Oberwilflingen [no. 56]; lead pick-ingot: Lachen-Speyerdorf [no. 53]) (Fig. 16/1 (Fig. 16/1–7)). On the other hand, finished products were transformed for their use as anvils, like palstaves and flat axes (Damsholte [no. 17], Bromma [no. 106], Holmedal [no. 107]), a hammer (Augsdorf [no. 1]) or (probably) a full hilted chisel (Bologna-San Francesco [no. 81]; Redù [no. 88]) (Fig. 16/8–9. 11–13). A unique object is the so called bugle-shaped object reused as a small anvil from the Bronze Age final III-hoard of Nantes-Prairie de Mauves [no. 37] (Fig. 16/10).⁶⁰ Of course, the number of these so called *ad-hoc* anvils⁶¹ will increase in the future if we pay more attention to this category, which is hard to find in Bronze Age metalwork.

Socketed hammerheads as anvils (German: Tüllenambosse) (Fig. 17)

A specific group of socketed hammerheads were probably used as anvils.⁶² The socketed hammerheads from Trenčianske Bohuslavice (Slovakia) and Devilleles-Rouen (France) have a short lateral beak in the middle of the body (Fig. 17/1). These objects combine features both of an anvil (beak) and a socketed hammer. The socketed hammerhead from Tise (Denmark) has a swage as a feature of an anvil on its working surface (Fig. 17/11). However, the best criteria to define socketed hammerheads as anvils are the much lower depth, the more irregular shape of the socket and/or the absence of a lateral loop. They were hafted over a straight wooden shaft.⁶³ Their body and their round, oval or square mouth is mostly rougher than in case of „normal” hammerheads. The flat, arched, hemispherical or gable-roofed striking surface (German: *Bahn*) of these tools is the same as that of the hammers for multi-purpose forging.⁶⁴ Hammerheads with a small flat, slightly rounded working surface could be used for hardening and sharpening blades of weapons (swords, daggers, spearheads, etc.) or tools (knives, razors, axes, sickles, etc.), for forging wires, belts, needles etc. or softer (organic) material (leather, bones or wood). For metalworking, especially to stretch, beat or thin sheet metal, socketed hammerheads with a gable-roofed or with a hemispherical striking surface (ball-peen hammer [German: *Kugelhammer*]; beating fist [German: *Treibfaust*];

reverse fixed) were especially suitable. In this study we present only a selection of these kinds of socketed hammerheads as anvils (German: *Tüllenamboss*) (Fig. 17 [all hammerheads Fig. 17 are in vertical reflection]).

Dating and Distribution

Dating

At the end of the European Early Bronze Age and the beginning of the Middle Bronze Age the rise copper-tin-technology laid the foundation for an almost explosive proliferation of all kinds of weaponry and tools. Casting provided the possibility of creating any individual form of objects. These include socketed implements and tools (spearheads, arrowheads, axes, hammers, chisels, etc.). Casting moulds for producing bronze tools and bronze anvils became specialised tools.

The history of metal anvils started in the Middle Bronze Age in different parts of Europe. One of the oldest bronze anvils, an anvil with a gable-roofed working surface (Fig. 8/3), was found in an early dated association from the hoard of Valdevimbre (no. 105) (Prov. Leon, Northwestern Spain) associated with a small saw, two argaroid flat axes, a socketed spearhead, a socketed ferrule and two dagger blades.⁶⁵ The hoard from Porcieu-Amblagnieu (no. 42) (Western Alps, France), which has also been dated to the advanced Middle Bronze Age (Bz B/C) includes an early Middle Bronze Age razor,⁶⁶ palstaves, knob-sickles, chisels, a socketed hammerhead and a plastic decorated complex anvil with a beak (Fig. 12/5). The anvil mould (for a similar anvil to that from Porcieu-Amblagnieu) from Cuiry-les-Chaudardes (no. 25) (Northern France) (Fig. 12/9) was associated with Late Early Bronze Age ceramic vessels and was dated into the early Middle Bronze Age.⁶⁷ The hoard of stone moulds from Omagh (no. 123) (Northern Ireland) includes moulds for Middle Bronze Age rapiers/dirks. On one mould a negative for casting a small pyramidal anvil with a beak is

⁵⁹ Lo Schiavo u. a. 2009.

⁶⁰ Jockenhövel 1972; Janas 2010: 391–394.

⁶¹ Term after Jockenhövel 1983.

⁶² Ohlhaber 1939: 25; Jockenhövel 1982; Gogâltan 2005; Nessel 2008; Dietrich/Ailincăi 2012; Dietrich/Dietrich 2013.

⁶³ See Tise (Fig. 17/11): Armbruster 2001: 11, fig. 2, a. b.

⁶⁴ Jockenhövel 1982.

⁶⁵ Monteagudo 1977: 98–99, no. 607 pl. 149, B 1; Armbruster et al. 2003: 258, fig. 1.

⁶⁶ Jockenhövel 1980: 55–56, no. 127, pl. 8.

⁶⁷ Letterlé 1982.

engraved. The small hoard with a fragment of a palstave and a complete small anvil with crossed swages on the small working surface from Sengeløse (no. 18) (Seeland, Denmark) can be dated to Period II of the Northern European Bronze Age (Fig. 12/2)⁶⁸. The Serbian anvil from Velebit (no. 104) can be dated to the same time (Fig. 4/3; 5/4. 5; 12/7). The hoard from Velim (no. 9) (Bohemia) with an anvil (Fig. 10/4), three bronze moulds and gold jewellery can be dated to the late Middle Bronze Age, which is also the same period of the hoard from Oberwilflingen (no. 56) (Württemberg, Germany) with an *ad-hoc*-anvil reused from an oxide-ingot (Fig. 16/5. 5a). The anvils from Inshoch Wood (Scotland) (no. 121; Fig. 11/2.), Flax Bourton (England) (no. 115; Fig. 11/12) and Bishopsland (Ireland) (no. 75; Fig. 13/6) can be dated to the later Middle Bronze Age and/or the beginning of the Late Bronze Age in Western Europe (Jockenhövel 1975).⁶⁹ From that time, there are, for anvils, specific components of tool kits in many Late Bronze Age hoards, which were also found in settlements all over Europe:

BzD/Ha A-Dating: Augsdorf (no. 1); „Murnau” (no. 55); Golchen (no. 50); Sipbachzell (no. 3); Újezd (no. 8); Blučina (no. 10); Loučka (nos. 13–16); Jevičko (no. 12); Fratelia (no. 102); Gusterița (no. 103); Nadap (nos. 67–69)

Ha A-Dating: Gênelard (nos. 28–31); Esztergom (no. 63); Lesenceistvánd (nos. 64 and 65); Tállya-Várhegy (nos. 70 and 71); Mátraszőlő-Kerekbükk (no. 66); Boljanić (nos. 4–6); St. Leonards (no. 119)

Ha A 2/B 1-Dating: Lachen-Speyerdorf (nos. 51 and 52); Steinkirchen (no. 61); Clos de La Blanche Pierre (Jersey) (no. 124); Fresné-la-Mère (no. 27); Nedilys’ka (Niedzielska) (no. 114); St. Denis-de-Pile (no. 46); Frattesina (no. 85); Contigliano (no. 83); Monte Cavanero (Chiusa di Pesio) (no. 87)

Ha B 3-Dating: Plestlin (no. 59); Ruthen (Holzen-dorf) (no. 60); Murchin (no. 54); Ochtendung (together with a Ha B1-bucket) (nos. 57 and 58); Witkovo (no. 101); Świnoujście-Międzyzdroje (no. 100); Przemyśl (no. 99); Gravelle-Sainte-Honorine (no. 32); Nantes-Prairie de Mauves (no. 37); Plainseau (Amiens) (no. 40); Bologna-San Francesco (nos. 80 and 81); Lusmagh (no. 117); Lichfield (no. 78)

Ha C/D-Dating: Hallstatt (no. 2)

Distribution

It should be noted that bronze anvils are an extremely rare class of tools in the European Bronze Age. To date only 124 bronze anvils have been recorded,

mainly from hoards, some from settlements and, exceptionally, from funerary contexts (see list). Of course, regional and chronological differentiations have to be made because bronze anvils are found from the beginning of the Middle Bronze Age to the Earlier Iron Age, over an extended period of time of ca. 1,000 years.

In general, anvils have a dispersed distribution over a wide area of Europe (Map 2). The densest concentrations are found in Western Europe (The British Isles and Ireland), France (Burgundy and the Seine basin) and the western parts of Switzerland, due to an especially favourable situation of finding in hoards, settlements and rivers (or other wetland areas). Minor concentrations are known from Upper Italy, Sardinia, the Eastern Alps, from regions along the middle Danube (Lower Austria; Moravia,), from Slovakia, Hungary and from the Pannonian and Western Carpathian regions (Romania [esp. Transilvania], Vojvodina).⁷⁰ Further anvils are known from other parts of Central Europe (Bohemia, Poland, Bosnia and Herzegovina and Germany) and Southern Scandinavia.⁷¹ The recently discovered Ha B1-hoard from Ochtendung (Middle Rhine) (Kr. Mayen-Koblenz, Rhineland-Palatinate) (nos. 57 and 58) with two anvils of different types (one beaked anvil and one block anvil [Fig 7/18; 12/1]) draws attention to regions which have long been considered rather empty of finds.⁷² The stone mould from Velebit (no. 104) is the first example of casting a bronze anvil in Serbia and it is the oldest one in the Pannonian region (Fig. 4/3; 5/4. 5; 12/7). In many regions, however, there have been no finds of anvils from the European Bronze Age, though they must have been in use there.

Several anvil traditions can be distinguished. Firstly a pan European tradition includes most of the simple anvils of Class 1 (bench, block and pyramidal anvils), *ad-hoc*-anvils and socketed hammerheads/anvils with a distribution in all European Bronze Age regions. Anvils of Class 2 and its subclasses have a more limited distribution (Map 3). Cruciform anvils were


⁶⁸ Aner/Kersten 1973: 112 Nr. 339, pl. 59; Jantzen 2008: 256 Nr. 371.

⁶⁹ Jockenhövel 1975.

⁷⁰ Iaia 2014; Lo Schiavo 2018; Höglinger 1996; Girtler 1970; Salaš 2014; Pančiková 2008: 116–117, fig. 10, l. 4; Mozsolics 1984: 42; Gogăltan 2005.

⁷¹ Kytlicová 2007: 160–161; Gedl 2004: 72–73 160; König 2004; Jantzen 2008: 253–256

⁷² von Berg 2005.

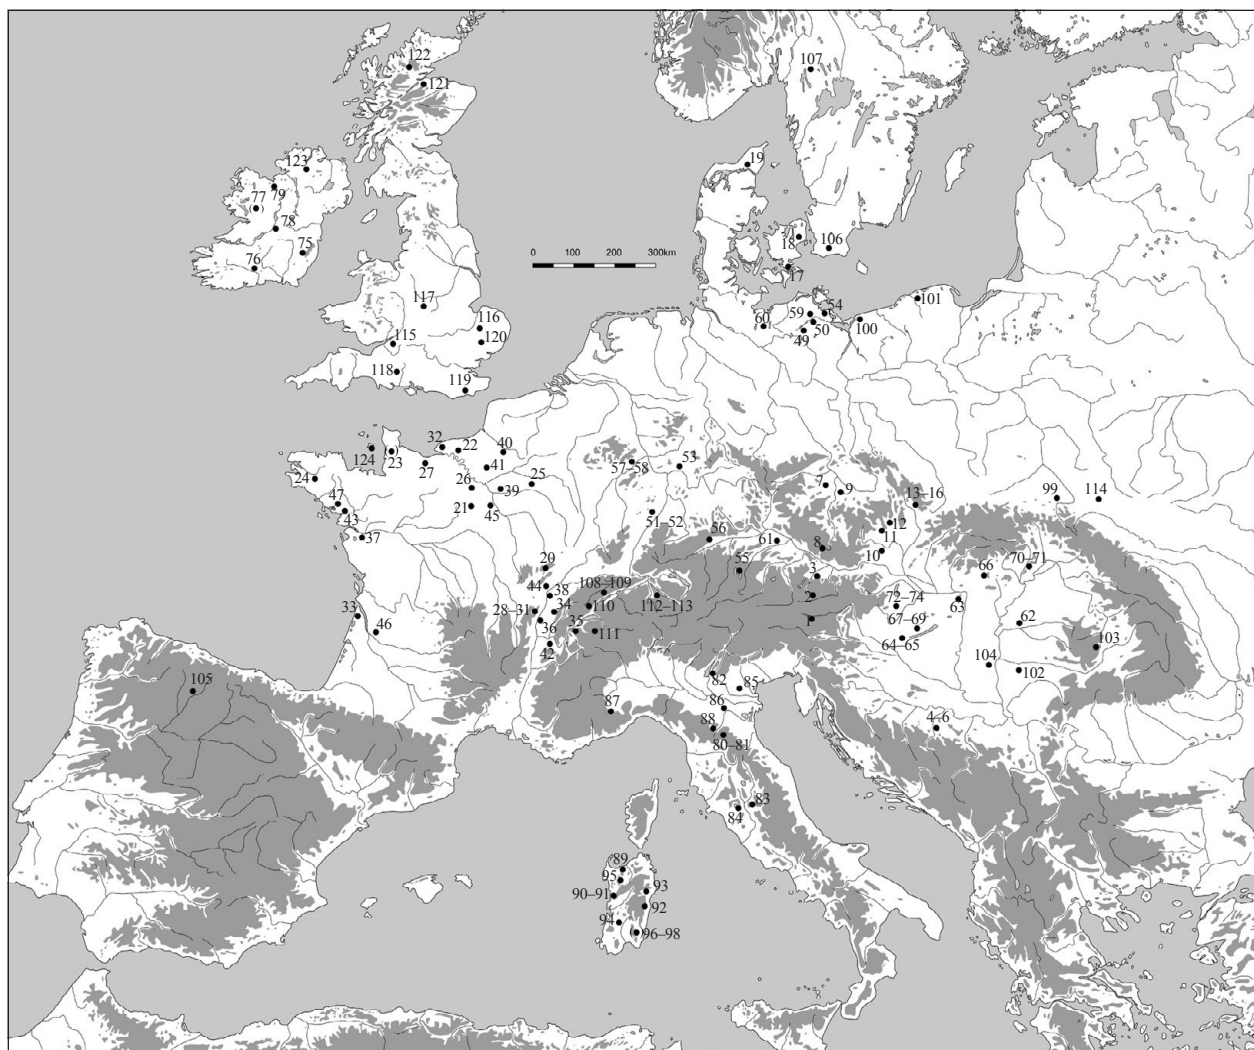

Map 2. Distribution of Bronze Age metal anvils in Europe (numbers correspond to the list)

Карта 2. Распространеності металних наковаля из бронзової доба
(бројеви одговарају приложеној листи у шексју)


distributed in Ireland, western France and, perhaps, in Southern Germany. Cruciform anvils of the type Chalon-sur-Saône/Gray were regionally limited to Burgundy (Eastern France)⁷³ and anvils of the type Chiaramonti were an endemic phenomena of the Sardinian island⁷⁴. Anvils of the type Porcieu de Amblagnieu are common and were produced in France (see the three moulds in its western part). The second Western European anvil tradition is represented by the anvils of the type Fresné-la-Mère with finds from Scotland, Brittany, Normandy and the Seine basin. Bent anvils of Class 3 prevail in the middle Danube region. The mould for bent anvils and a finished bent stake from the hill fort of Velem-Szentvid (no. 72, 74; Fig.

14/8. 9) together with some other moulds and tools for metalworking indicate local production (workshops) on this prominent site.⁷⁵ The two beaked anvils from Loučka (no. 13. 15) are very similar to the third anvil, a block anvil (no. 10), from the same hoard, all probably made for a tool kit for a local metalworker. The anvils from Plainseau (Amiens) (no. 40) and Gravelle-Sainte-Honorine (no. 32) are also very similar (Fig. 8/1. 2).

⁷³ Nicolardot/Gaucher 1975: 33; „Saônnois“: Thevenot 1998: 128.

⁷⁴ Lo Schiavo 2018: 429.

⁷⁵ von Miske 1908.

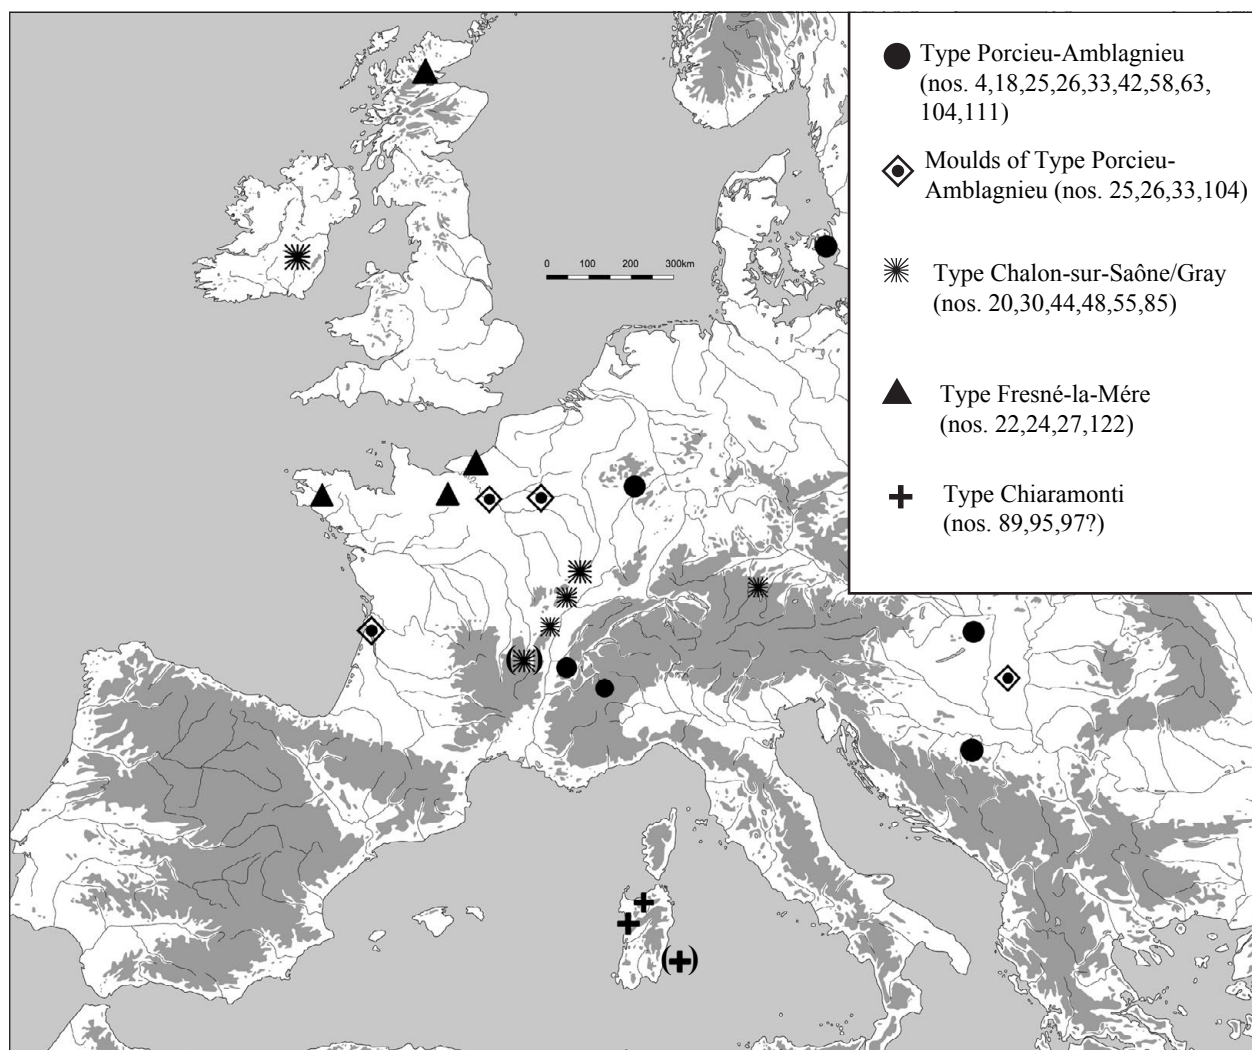

Map 3. Distribution of some types of Bronze Age anvils in Europe

Карта 3. Распространености отдельных типовых металлических наковаль в бронзовом добу

They are regional anvil forms in North Western France as are the two mushroom-headed anvils from Ruthen (no. 60) and Świnoujście-Międzyzdroje (no. 100) (Fig. 8/3. 4) in the Southern Baltic Sea region. Also, the two Italian mushroom-headed anvils from Bologna-San Francesco (no. 80) and Contigliano (no. 83) look very similar (Fig. 8/1. 2).

In summary, the chronology and distribution patterns of the bronze anvils show that there is no evidence of a typological evolution from simple to complex forms/types.⁷⁶ On the contrary: to begin with (Middle Bronze Age) there were more complex anvil shapes, while later on (Later Bronze Age) more simple forms prevailed. This again underlines the relationship between the formal character and the specific work

process. At the moment, any particular region of origin for metal anvils within a limited region in Europe cannot be identified.

The anvil mould from Velebit (no. 104) was discovered ca. 1,200–1,400 km from the next analogies in Western France (Map 3). The simultaneous emergence of the production and use of metal anvils demonstrates a supraregional innovation, a high mobility of people (perhaps also of „itinerant” metal workers) and a rapid exchange of technological knowledge and skills in the context of social, economic and religious networks. However, there is yet not enough evidence

⁷⁶ Ehrenberg 1981: 14.

to allow a final conclusion in this matter. The four moulds, probably all dating from the Middle Bronze Age, represent a standardised shape and unified workflow over a long distance. This might reflect a communication network of Bronze Age craftsmen and societies throughout Europe.

Function

Producing

The shape of metal anvils depends on their specific function in forging, and the desired shape of the final product. Therefore, generally, a great variety and diversity of anvils can be expected. Each artisan determined the final shapes („*The end justifies the means*”). In some cases, caster and smith might have been the same person.

All Bronze Age metal anvils were cast, most of them in two-piece stone moulds (sandstone, calcite etc.). Some socketed anvils (no. 31, 35; Fig. 9/6; 11/4) were been cast in multiple piece moulds, provided with a core, comparable with the casting of socketed hammerheads. To date, clay for anvils is unknown because the preservation conditions for fragile clay moulds are generally poor. Moreover, bronze moulds could have been melted down due to their high material value.

Compared to the number of ca. 120 metal anvils, only eight (!) casting moulds are known. This represents a very high ratio between finished anvils and their moulds (ca. 1:10). Stone moulds have been found in three lake villages in Central and Western Switzerland (Auvernier [no. 108]; Grandson-Corcelettes [no. 110]),⁷⁷ and a single find from South-Western France (La-Lède-du-Gurp [no. 33]),⁷⁸ from two Late Bronze Age settlements in Western and Northern France (Fort-Harrouard [no. 26]; Cuiry-lès-Chaudardes [no. 25]),⁷⁹ from a hoard of stone moulds in Ireland (Omagh [Ulster] [no. 123])⁸⁰ and from the a hill fort settlement in Transdanubia (Velem-Szentvid [no. 73]).⁸¹ The Serbian stone mould from Velebit (no. 104) is the first mould for anvils outside Western Europe.

List of moulds for Bronze Age metal anvils

1. Auvernier (no. 108), canton Neuchâtel, Switzerland. – Late Bronze Age lake village (mostly Ha B). – One half of a two piece stone mould for a pyramidal anvil and a sickle (Fig. 7/12). – Rychner 1979: pl. 135, 3.

2. Cuiry-lès-Chaudardes (no. 25), dép. Aisne, France. – Middle Bronze Age (Bz D–C) settlement, structure 55. – Fragment of a half of a two piece stone mould for an anvil with two beaks/spikes (Fig. 12/10). – Letterlé 1982: fig. 5; Blanchet 1984: 186, fig. 99, 18.

3. Fort-Harrouard (no. 26), com. Sorel-Moussel, dép. Eure-et-Loir, France. – Middle /Late Bronze Age (Bz C–Ha B) hill fort; pit B 157 (associations: ceramic vessels, spindle whorl, perforated dent of a dog/wolf). – Fragment of a half of a two piece stone (calcite) mould for an anvil with two beaks/spikes; on the back a negative for a socketed object (spearhead?) (Fig. 12/8). – Mohen/Bailloud 1987: 127, fig. 69; pl. 6, 11.

4. Grandson-Corcelettes (no. 110), canton Neuchâtel, Switzerland. – Late Bronze Age lake village (mostly Ha B). – Half of a two piece stone mould for a rectangular board anvil (?) (Fig. 14/3). – Gross 1883: pl. 29, 12.

5. La-Lède-du-Gurp (no. 33), com. Grayan-et-l'Hôpital, dép. Gironde, France. – Single find (1966) from beach of the Atlantic Sea. – One half of a two piece stone mould for an anvil with two beaks/spikes; traces of powder from the casting process (Fig. 12/9). – Moreau 1971: Gomez de Soto 1995: 101–102, fig. 32.

6. Omagh (no. 123), Co. Tyrone, Ulster/Northern Ireland. – Middle Bronze Age hoard of stone moulds. – Complete mould for a block anvil with a small beak on one side (Fig. 11/1); in combination with negatives for a rectangular ingot and bar-ingot; on the back a mould for a dirk. – Coghlan/Raftery 1961: 241–242, fig. 42.

7. Velem-Szentvid, Kom. Vas, Hungary. – Late Bronze Age (Ha B) settlement (hill fort). – Fragment of a half of a two piece stone mould for a bench anvil and a socketed hammer (Fig. 14/9). – von Miske 1908: pl. 22, 3.

8. Velebit, Serbia (Fig. 4/3; 5/4. 5; 12/7).

All metal anvils were cast in bronze. Some of them were made of a special alloy of copper with a high tin content ranging from 10 % to 30 %. This composition changes the mechanical and chemical properties of the alloy, such as hardness and colour, and makes the anvil harder than „ordinary” tin-bronze-alloy (10 % Sn). Hardness is required for percussion tools used for plastic shaping. A secondary effect of

⁷⁷ Wyss 1969: 10; Rychner 1979: pl. 135.3; Gross 1883: pl. 29, 12.

⁷⁸ Gomez de Soto 1995: 101–102, fig. 32.

⁷⁹ Mohen/Bailloud 1987: 127, fig. 69; pl. 6, 11; Blanchet 1984: 186, fig. 99, 18.

⁸⁰ Coghlan/Raftery 1961: 241–242, fig. 42.

⁸¹ von Miske 1908: pl. 22, 3 (right negative).

this special alloy is its whitish-silvery shiny colour.⁸² The Lachen-Speyerdorf (no. 51: Cu 76,81%, Sn 17,17%); Inshoch Wood (no. 121);⁸³ Kyle of Oykel (no. 122);⁸⁴ „Murnau” (no. 55);⁸⁵ La Tour de Langin (no. 35);⁸⁶ and the Clos de la Blanche Pierre, Jersey (no. 124) examples belong to this group.⁸⁷ The Late Bronze Age block anvil from Lichfield (no. 117) was made of a copper alloy containing lead (Pb 25%), antimony (Sb more than 5%) and „very little tin”.⁸⁸ Further systematic analyses of the elementary alloy composition of Bronze Age anvils is necessary for a better understanding of the technical choices of the artisans.

There is little data available concerning the weight of the anvils: (e. g.) G nelard (no. 30: Type Gray [927 g]); Sipbachzell (no. 3: 912 g), Lou ka 1–4 (no. 13–16: together ca. 800 g), Sa ne near Chalon-sur-Sa ne/Gray (no. 44: 754 g), Fratelia (no. 102: 660 g), Boljani  1–3 (no. 4–6: together > 430 g), Alise-Sainte-Reine/Laumes (no. 20: 410 g), „Murnau” (no. 55: 348 g). All metalworking tools (anvils, socketed hammerheads) from the G nelard hoard have a total weight of about 3 kg of bronze (Fig. 18)! When these tools are melted down (in a recycling process) a complete cuirass or ca. 300 pins could be gained. It can be presumed that anvils contained a large amount of bronze!

Hafting

Anvils were inactive percussion tools that had to be fitted in a wooden stump. This fitting had a twofold function: On the one hand, the wooden support provided a means to absorb the shock of the percussion. On the other hand, it served the fixing of the inactive tool during the striking of the active hammer. Some details of the mounting methods can be deduced. Bench and block shaped anvils which were not equipped with a spike could be inserted into a block of wood provided with a depression corresponding to the block’s dimensions. Anvils with beaks/spikes were also fitted in a wooden stump. The multiple use of certain complex anvils was possible: alternately on the beaks and/or on the working face (Fig. 13/10a).

Use

The generally small-size working surfaces of these anvils were mostly rectangular or square, rarely round-spherical or round-oval. The dimension of the working surfaces ranged from ca. 3 cm to 8 cm. According to the specific working purpose, the surfaces were flat, slightly domed or gable-roofed. Each surface shape had, in combination with the working face of the

hammer, a precise impact on the work piece that was to be deformed and shaped. The surfaces correlated largely with the striking faces of their counterparts, the bronze socketed hammerheads or other active percussion tools.⁸⁹ The working surfaces of the anvils had to be as smooth as possible, because even the slightest damage on them – as well as on the smith hammer – left a mark on the hammered object.

On the working surface or projecting beak there are sometimes slight or fine incised grooves or swages (German: *Sicken*) which appear in different shapes (half-round, V-shaped etc.), widths and depths. They were apparently intended for the shaping of bronze pins, needles, awl, rods or wire of round, quadrangular or triangular section, and probably also for small gold objects.

Some anvils have a perforation through the centre of their body, so-called punching holes (Fig. 6/1. 6; 13/1–4. 8). Their diameter ranges between 1–8 mm. Despite the term „punching hole”, the function of this hole might rather have been to bend rods and wires than to perforate objects. The frustrum-anvil from Fratelia (no. 102) has a row of little bosses on two sides of its body (Fig. 7/3).

Due to the size and different nature of the working surfaces, of the beaks/spikes and swages, a differentiated use of the anvils can be postulated. It ranges from coarser to finer forging.⁹⁰ Some anvils have clear traces of a long lasting use in the form of deformation (German: *Bart*), hammer marks and scratches (par example: Fig. 7/1. 6. 9. 11. 14; 8/1; 10/1; 11/11; 16/3. 4. 10–13).⁹¹

Anvils as an essential element of the Bronze Age metalworker’s tool kits

It can be assumed that anvils (of stone or metal) were part of the basic equipment of every specialised metalworker’s tool kit or workshop. Anvils can be found wherever forging of metal objects was practiced on a

⁸² Sala  2014: 73–74, fig. 21. 23 for eight anvils (range: 78–88% Cu, 10, 5–20, 2% Sn) (one anvil of copper!).

⁸³ Childe 1945/46 (70% Cu, 30 % Sn).

⁸⁴ Smith 1881: 24: (70, 4% Cu; 26, 4% Sn).

⁸⁵ Silvery shining: Nessel 2009: 56.

⁸⁶ Ohlhaver 1939, 110 (B 52 „Genf”) (84% Cu, 16% Sn).

⁸⁷ Coombs 1988: 325 (Cu ca. 79%; Sn 19,04%).

⁸⁸ Needham/Meeks 1993: 127.

⁸⁹ Jockenh vel 1982.

⁹⁰ Ohlhaver 1939: 23; Armbruster 2001: 17.

⁹¹ Lou ky (Moravia): Sala  2014: 71 fig. 18.



Fig. 18. G nelard (Burgundy, France). Late Bronze Age tool kit (Photograph B. Armbruster)

Сл. 18. G nelard (Бурјундуја, Француска): њруја алајки из касној бронзаној доба (фојто: В. Armbruster)

smaller or larger scale. It is impossible to mention all finds in our study, especially all hoards with elements of a metalworker's tool kit. Mainly in large European hoards with numerous objects there is often a combination of anvils with socketed hammerheads and other tools for metalworking.⁹²

The most complete tool kit is known from the Ha A 2-hoard of G nelard (no. 28–32) (Burgundy, France). It consists of anvils of different kinds, socketed hammer heads, a swage block, chisels, a set of five punches with concentric circles (German: *Ringpunzen*) and four other punches, one half of a little bronze mould for small rings and some other tools.⁹³ In addition to the bronze tools, a stone hammer that might also have been used as an anvil was associated to this outstanding assemblage (Fig. 18). Another significant eastern French tool assemblage, belonging to the Larnaud hoard (Jura, France), consists of a doming block (no. 34) (Fig. 14/4), a socketed hammerhead and several punches for plastic

decorations. Assuming that it is a closed find, in the Bz D-hoard from „Murnau” (Upper Bavaria) an anvil (no. 55) (Fig. 13/5) is associated with 18 punches, also specialised punches for sheet decoration (German: *Ringpunzen*, *Faulenzerpunzen* [„faineant”-punches], a wheel-shaped punch) and two small hammers for fine forging.⁹⁴ From the West Balkans, in the Ha A-hoard from Boljani  (no. 4–6) (Bosnia and Herzegovina) are incorporated three anvils of different shapes which are associated with three socketed hammerheads, a small blade of a saw, two chisels (for wood-working) and five metal cores for casting socketed tools.⁹⁵ We can also mention

⁹² Hansen 1994:127–129. 140, fig. 77; Nessel 2009; Medelet 2005; Jockenh vel 2019.

⁹³ Thevenot 1998; Armbruster 2008.

⁹⁴ Nessel 2008.

⁹⁵ K nig 2004.

the combination of three anvils (no. 13–15) and three socketed hammerheads from the Ha A-hoard of Loučka (Moravia) (Fig. 10/2. 3; 11/9).⁹⁶ Some other hoards with an anvil and its counterpart, the socketed hammerhead, are known from the Danube Region, e. g. Fratelia (no. 102) (Romania), Nadap (no. 67–69) (Hungary), and Schiltern (Austria), from Central and Western Europe, e. g. Porcieu-Amblagnieu (no. 42) (Eastern France), Fresné-la-Mère (no. 27) (Normandy), Inshoch Wood (no. 121) (Scotland), Lusmagh (no. 78) and Bishopsland (no. 75) (both Ireland). The Middle Bronze Age casting stone moulds from Omagh (no. 123) (Northern Ireland) demonstrate which objects could be cast together: a small beak anvil, a dirk blade, a bar and a flat piece of metal (probably another bar). This is a combination of weapons and semi-finished products or crude metal.

Anvils and gold working

Bronze Age anvils are typical tools for copper, bronze and gold working. Consequently, these small fine metal working tools could have been used for both precious metals and copper based alloys (bronze).⁹⁷ Their use in gold working⁹⁸ has been evidenced in several cases, as on the working face of some anvils tiny gold particles were detected: „North Sligo” (no. 79); Lusmagh (no. 78) (both Ireland); Lichfield (no. 117) (England) and Fresné-la-Mère (no. 27) (Normandy, France).⁹⁹ On the surfaces of the bronze bench block with a high content of tin from Lachen-Speyerdorf (no. 51) (Southwestern Germany) traces both of gold and bronze were found (Fig. 14/1). In the Bronze Age hoards from Fresné-la-Mère (Normandy) and Velim (no. 9) (East Bohemia, Czechia) anvils are associated with gold jewellery.¹⁰⁰ This combination suggests the use of some anvils by goldsmiths as well. The socketed hammerhead and the anvil provided with a work face angle below 90° from the Fresné-la-Mère hoard (fig. 13/10) are particularly well suited to producing flange twisted gold torcs, the large ornament they were associated with. A special investigation of anvils by means of a high-resolution microscope might increase the number of Bronze Age anvils for gold and silversmiths in the future.

Summarising we can realise that Bronze Age bronze anvils were mainly used for lightweight fine metal-working of small objects (i.e. ornaments, rods, wire, thin plates or sheets, plastic decoration, etc.) of bronze, gold or silver. Larger anvils might also have been used for hammering and sharpening blades of weapons (i.e.

swords, daggers, spearheads) or tools (i.e. sickles, knives or razors). However, these bronze anvils with mostly very limited working surface tools seem to be less appropriate for shaping larger and heavier bronze sheet objects (i.e. helmets, shields, cuirasses and vessels).

Social context

Almost all Bronze Age anvils were found in bronze hoards and settlements. Some of them were river finds, perhaps offerings. In the contexts of many hoards, anvils represent an integral component of a metalworker's tool kit. In some settlements, they were found together with other archaeometallurgical tools (moulds, hammerheads, chisels, punches, etc), and thus represent more or less workshops. Only six anvils were found in graves.

Which persons owned these anvils?

Graves with bronze anvils

Hallstatt, Pol. Bez. Gmunden, Upper Austria, Austria. – Grave 469; incineration. – Bronze socketed hammerhead (anvil); bronze alloy with high content of tin (white-shiny), ribs on the mouth, marks on one side (owner marks?); flat rectangular working surface (Fig. 17/10). – Associations: *bronze* – parts of a cuirass, file/rasp, two pins, six small rings; *iron* – long sword, short sword, three socketed spearheads, two socketed hammerheads, socketed chisel, knife, fragments of unidentified iron objects. – Dating: Ha C. – Kromer 1959: 110, fig. 91, pl. 82–84.

Lachen-Speyerdorf (nos. 51. 52), com. Neustadt an der Weinstraße, Rhineland-Palatinate, Germany. – Grave 3; cremation. – Two anvils; *anvil 1* (no. 51): bench shaped anvil; fahlore-based bronze with high content of tin (Cu 76.81%, Sn 17.17%; Pb 1.15%, As 0.57%; Ni 0.34%, Sb 0.60%, Co 0.04%, Zn 0.07%, Au <0.01, Bi <0.025%, Cd <0.001); swages (German: *Sicken*) on three (of four) working faces; length 6.9 cm; weight 155 g; on four sides traces of forging; after REM-investigation traces of *gold* (on one working face) and *bronze* (on another surface) (Fig. 14/1). *Anvil 2* (no. 52): Half of a „pick-ingot”; lead (!); length 13.2 cm

⁹⁶ Salaš 2014.

⁹⁷ Jockenhövel 2003.

⁹⁸ Oldeberg 1943: 16–17; Eluère 1987: 19–20; Armbruster 1995: 181; idem 2001.

⁹⁹ Ehrenberg 1981: 15; Maryon 1938: 249, fig. 17; Meeks/Needham 1993; Taylor 1980: 12.

¹⁰⁰ Eluère 1987: 20; Kytlicová 2007: 312 Nr. 251, pl. 159. 160).

(Fig. 16/7). – Associations (only metal objects preserved): two knives, fragments of two razors (Type Eschborn after Jockenhövel 1971: 145). – Dating: Ha B 1. – Müller-Karpe 1959: 316, pl. 11, K; Jockenhövel 1971: 146, no. 274. 279; Jockenhövel 1973: 23, fig. 2; Sperber 2000; Bachmann u. a. 2003: 92, fig. 12.

Steinkirchen (no. 61), Lkr. Deggendorf, Lower Bavaria, Germany. – „Steinfeld”; grave 10, cremation. – Bronze block-anvil with three swages on the working face; length 1.6 cm (Fig. 7/21). – Associations: razor, fragment of a knife, shaft of a pin, five ceramic vessels. – Dating: Ha A 2. – Müller-Karpe 1969; Jockenhövel 1971: 100, no. 132, pl. 70, A.

Graves with iron anvils

Hallstatt (no. 2), Pol. Bez. Gmunden, Upper Austria, Austria. – Grave 283; cremation. – *Iron* block anvil; length 7 cm (Fig. 7/9). – Associations: *bronze* – five *phalerae* (from a cuirass?), pins; *iron* – socketed spearhead, winged axe, four fittings; ceramic sherds, animal bones. – Dating: Ha C. – Kromer 1959: 82, fig. 50, pl. 44, 1–8.

Falerii (no. 84), Civita Castellana, Viterbo, Lazio, Italy. – Mazzano Romano; from a grave (unknown associations). – *Iron* pyramidal (frustrum-) anvil; length ca. 10.5 cm (Fig. 7/19). – Montelius 1905/1910: pl. 329, B.

Boddin, Lkr. Güstrow, Mecklenburg-Vorpommern, Germany. – Grave 4; cremation (woman? [ca. 30–40 years old]). – *Iron* block anvil; length 2.7 cm (no illustration). – Associations: small iron belt hook. – Dating: Early Jastorf Culture (ca. La Tène A/B). – Keiling 1972.

The grave of Lachen-Speyerdorf can be addressed as a metalworker's grave.¹⁰¹ Both anvils show intense traces of use (fig. 14/1; 16/). The tin-rich bronze anvil was used for forging bronze *and* gold. Apart from the two anvils, this grave is characterised by the association of two razors and a knife. Razors are considered typical adult-male accessories.¹⁰² As pointed out by H. Müller-Karpe, the small anvil with swages on the working surface (fig. 7/21) from the razor/knife-grave of Steinkirchen (Lower Bavaria) could have been used as a „*Toreutengesek*” i.e. a special tool used to produce plastic ribs on sheet bronzes, like the ribs on buckets or vessels.¹⁰³ If a bronze vessel as a finished product had been included in this grave, it would undoubtedly have been one of the most important and highest ranking graves in Lower Bavaria during the earlier Urn-field period.

Grave No. 469 at Hallstatt is characterised by the extraordinarily rich warrior equipment and can be compared with other similar graves of the well known Early Iron Age (Ha C) salt miner cemetery. The anvil there is associated with other tools: a file/rasp and a chisel. The union of a warrior's and a metalworker's or other craftsman's (wood-worker?) profile is comparable with that of other rich warrior graves in the Eastern Alpines.¹⁰⁴ In contrast, grave No. 283 at Hallstatt is different from grave No. 469 as it contains only a spearhead and a winged axe, whereas the fittings (*phalera*) of a cuirass (?) connect this grave with other Eastern Alpine warrior graves of Hallstatt nobility. These male graves have their counterparts in some rich female graves with utensils from the extensive textile production of that time.¹⁰⁵

The very small iron block anvil of Boddin (Mecklenburg) was the burial gift for a 30–40 year-old person, probably a woman. If the anthropological investigation was correct – based on weak muscle marks on the long bones and skull – it would be one of the few female graves to include a metalworking tool.¹⁰⁶ However, on the anvils of the Northern German Jastorf Culture, according to H. Keiling, „delicate iron objects were made, such as the small tongue belt hooks from the same grave or the characteristic bronze *Segelohrringe* earrings and iron pins” (translation: A. J.).¹⁰⁷

However, similarly to other tools, anvils as grave goods deviate from the canonical associations special gifts have in Bronze Age graves. They emphasise the special position of the deceased and/or the significance of the craftsmanship. Regardless of whether the anvil was the property of a craftsman or a general sign of his community's appreciation of that profession, represented by anvils and their physical characteristics (form and weight), metal anvils were held in high esteem, which was conferred on their owners – craftsmen working with copper, bronze and gold.

This may explain why they are very rarely encountered as grave goods. Such special tools, and perhaps even the associated complementary tools (the

¹⁰¹ Sperber 2000.

¹⁰² Jockenhövel 1971: 247.

¹⁰³ Jacob 1995: 98.

¹⁰⁴ Teržan 1994; idem 2003.

¹⁰⁵ Eibner 2005; idem 2014.

¹⁰⁶ Jockenhövel 2018, 274–275.

¹⁰⁷ Keiling 1972, 179.

counterpart socketed hammerheads), were likely handed on to successors, within the family, clan or tribe, or they were melted down when their usability had significantly diminished.

Anvils and symbolism

Like other tools, some of the anvils are decorated with plastic decorations (Fig. 10/5; 11/2–7. 9; 11/3. 5; 13/10; 14/11). This relates them to comparable ornaments on socketed hammerheads and socketed axes.

The plastic decoration in the form of a rosette („belle marguerite”)¹⁰⁸ on the body of the Early Middle Bronze Age anvil from Porcieu-Amblagnieu (no. 42) (Eastern France) makes it a singular object (Fig. 11/5). The outline and plastic decoration on the socketed hammerhead/anvil of G nelard has female features (Fig. 17/8; 18). This pattern underlines a symbolic embedding of this special type of metalworking tool.

Translated by Stefan Milo ević

Starinar is an Open Access Journal. All articles can be downloaded free of charge and used in accordance with the licence Creative Commons – Attribution-NonCommercial-NoDerivs 3.0 Serbia (<https://creativecommons.org/licenses/by-nc-nd/3.0/rs/>).

Часопис *Старинар* је доступан у режиму отвореног приступа. Чланци објављени у часопису могу се бесплатно преузети са сајта часописа и користити у складу са лиценцом Creative Commons – Ауторство-Некомерцијално-Без прерада 3.0 Србија (<https://creativecommons.org/licenses/by-nc-nd/3.0/rs/>).

¹⁰⁸ Moreau 1971, 267.

BIBLIOGRAPHY:

- Aner, Kersten 1973** – E. Aner, K. Kersten, *Frederiksborg und Københavns Amt. Die Funde der älteren Bronzezeit des nordischen Kreises in Dänemark, Schleswig-Holstein und Niedersachsen I*, Neumünster 1973.
- Armbruster 1995** – B. Armbruster, Traditionelles Goldschmiedehandwerk in Westafrika und bronzezeitliche Metallverarbeitung in Europa. Technologien im ethnoarchäologischen Vergleich. *Beiträge zur Allgemeinen und Vergleichenden Archäologie* 15, 1995, 111–201.
- Armbruster 2001** – B. Armbruster, Zu bronzezeitlichen Werkzeugen der plastischen Verformung im nördlichen und westlichen Europa. In: W. H. Metz, B. L. van Beek, H. Steegstra (eds.), *Patina. Essays presented to Jay Jordan Butler on the occasion of his 80th birthday*, Groningen-Amsterdam 2001, 7–26.
- Armbruster 2006** – B. Armbruster, Steingeräte des bronzezeitlichen Metallhandwerks. *Ethnographisch-Archäologische Zeitschrift* 47, 2006, 163–191.
- Armbruster 2008** – B. Armbruster, Outillage de métallurgiste de l'âge du Bronze: les dépôts de Larnaud (Jura) et Gélénard (Saône-et-Loire), *Bulletin de l'APRAB* 5, 2008, 38–41.
- Armbruster 2010** – B. Armbruster, Lithic technology for Bronze Age metal working, in: B. Eriksen (ed.), *Lithic technology in metal using societies, Proceedings of a UISPP Workshop in Lisbon*, Aarhus 2010, 9–22.
- Armbruster 2012** – B. Armbruster, Feinschmiedewerkzeuge vom Beginn der Metallurgie bis in die Römische Kaiserzeit, in: A. Pesch, R. Blankenfeldt (eds.), *Goldsmith mysteries. Archaeological, pictorial and documentary evidence from the 1st millennium AD in northern Europe, Papers presented at a workshop organized by the Centre for Baltic and Scandinavian Archaeology (ZBSA), Schleswig*, Neumünster 2012, 59–85.
- Armbruster et al. 2003** – B. Armbruster, B. Comendador Rey, A. Perea, M. Pernot, Tools and tool marks. Gold and bronze metallurgy in Western Europe during the Bronze and Early Iron Ages, in: “*Archaeometallurgy in Europe*”, *Proceedings of the International Conference in Milano Vol. 1*, Milano 2003, 255–265.
- Bachmann et al. 2003** – H. G. Bachmann, A. Jockenhövel, U. Spichal, G. Wolf, Zur bronzezeitlichen Metallversorgung im mittleren Westdeutschland: Von der Lagerstätte zum Endprodukt. *Berichte der Kommission für Archäologische Landesforschung in Hessen* 7, 2002/03 (2003), 67–120.
- Bader 1978** – T. Bader, *Epoca bronzului în nord-vestul Transilvaniei. Cultura pretracică și tracică*, Editura științifică și enciclopedică, București 1978.
- Bátora 2002** – J. Bátora, Contribution to the problem of craftsmen graves at the end of Aeneolithic and the Early Bronze Age in central, western and eastern Europe, *Slovenská Archaeologica* 50, 2002, 179–228.
- Berg 2005** – A. von Berg, Ein späturnenfelderzeitlicher Bronzehort vom Karmelenberg bei Ochtendung, Kreis Mayen-Koblenz, *Archäologie in Rheinland-Pfalz* 2005, 2005, 31–34.
- Bertemes 2004** – F. Bertemes, Frühe Metallurgen in der Spätkupfer- und Frühbronzezeit. In: H. Meller (ed.), *Der geschmiedete Himmel. Die Welt im Herzen Europas vor 3600 Jahren*, Stuttgart 2004, 144–149.
- Blajer 1984** – W. Blajer, *Die Arm- und Beinbergen in Polen*, PBF X, 2, München 1984.
- Blanchet 1984** – J.-C. Blanchet, *Les premiers métallurgistes en Picardie et dans le Nord de la France: chalcolithique, âge du bronze et début du premier âge du fer*, Paris 1984.
- Brandherm 2010** – D. Brandherm, Frühe „Metallurgengräber“ von der Iberischen Halbinsel. Aussagemöglichkeiten zum sozialen Kontext. In: B. Horejs, T. L. Kienlin (eds.), *Siedlung und Handwerk. Studien zu sozialen Kontexten in der Bronzezeit, Beiträge zu den Sitzungen der Arbeitsgemeinschaft Bronzezeit auf der Jahrestagung des Nordwestdeutschen Verbandes für Altertumsforschung in Schleswig 2007 und auf dem Deutschen Archäologenkongress in Mannheim 2008*, UPA 194, Bonn 2010, 317–330.
- Briard 1965** – J. Briard, *Les dépôts Bretons et l'Age du Bronze Atlantique*, Nantes 1965.
- Briard 1984** – J. Briard, L'outillage des fondeurs de l'Age du Bronze en Armorique, in: J. Briard (ed.), *Paléometallurgie de la France 1*, Rennes 1984, 139–166.
- Butler, van der Waals 1966** – J. J. Butler, J. D. van der Waals, Bell Beakers and early metalworking in the Netherlands, *Palaeohistoria* 12, 1966, 41–139.
- Булатовић, Филиповић и Глигорић 2017** – А. Булатовић, В. Филиповић, и Р. Глигорић, *Лозница, културна старијинарскија праисторијских локалитета у Јадру, Рађевини и Азбуковици*, 2017, Београд-Лозница, (А. Bulatović, V. Filipović, R. Gligorić, *Loznica, Kulturna stratigrafija praistorijskih lokaliteta u Jadru, Rađevini i Azbukovici*, Beograd-Loznica 2017).
- Chantre 1875** – E. Chantre, *Études paléoethnologiques dans le Bassin du Rhône I. Age du Bronze, recherches sur l'origine de la métallurgie en France*, Paris 1875.
- Childe 1945/46** – V. G. Childe, A bronze worker's anvil and other tools recently acquired by Inverness Museum, with a note on another Scottish anvil, *Proc. Soc. Antiq. Scot.* 70, 1945/46, 8–11.

- Coffey 1913** – G. Coffey, *The Bronze Age in Ireland*, Dublin-London 1913.
- Coffyn 1969** – A. Coffyn, Le dépôt de Saint-Denise-de-Pile et la Bronze Final girondin. *Revue Hist. et Arch. de Liburnais* 36, 1969, 2–14.
- Coghlan, Raftery 1961** – H. H. Coghlan, J. Raftery, Irish prehistoric casting moulds. *Sibrium* 6, 1961, 223–244.
- Coombs 1988** – D. Coombs, The Late Bronze Age hoard from Clos de la Blanche Pierre, St Lawrence, Jersey, Channel Isles. *Oxford Journal of Archaeology* 7, 1988, 313–342.
- Coutil 1912** – L. Coutil, Énclumes de l'Âge du Bronze. *L'homme Prehist.* 10, 1912, 97–104; 181–186.
- Dietrich, Ailincăi 2012** – O. Dietrich, S.-C. Ailincăi, A group of Bronze Age socketed hammers/beating fists from the lower Danube and northern Black Sea area, *Peuce* 10, 2012, 9–19.
- Dietrich, Dietrich 2013** – O. Dietrich, L. Dietrich, Tüllen-hämmer als funktionale Bestandteile von Depotfunden des Karpatenbeckens. Das Beispiel Șpălnaca II, in: B. Rezi, R. E. Németh, S. Berecki (eds.), *Bronze Age crafts and craftsmen in the Carpathian Basin, Proceedings of the International Colloquium from Târgu Mureș, Târgu Mureș* 2013, 191–206.
- Drescher 1973** – H. Drescher, Amboss. *RGA* I, 1973, 250–252.
- Dubus 1912** – Dubus, Époque du Bronze. Carte et tableau analytique de la répartition du Bronze dans la Seine-Inférieure, *Bulletin de la Société Géologique de Normandie* 31, 1911 (1912), 93–127.
- Durman 1997** – Tin in Southeastern Europe?, *Opuscula archaeologica* 21, 1997, 7–14.
- Ehrenberg 1981** – M. R. Ehrenberg, The anvils of Bronze Age Europe, *Ant. Journal* 61, 1981, 14–28.
- Eibner 2005** – A. Eibner, Wie wertvoll ist eine Frau? Gedanken zum Stellenwert des Spinnens und Webens in der Gesellschaft. In: E. M. Feldinger (ed.), *Scherben bringen Glück. Festschrift für Fritz Moosleitner zum 70. Geburtstag*, Salzburg 2005, 31–38.
- Eibner 2014** – A. Eibner, Arbeitsdarstellungen im Umfeld der Situlenkunst. *Mitt. Anthr. Ges. Wien* 144, 2014, 35–60.
- Eluère 1987** – C. Eluère, *Gold der Kelten*, München 1987.
- Eluère, Mohen 1993 – C. Eluère, J.-P. Mohen, Problèmes des enclumes et matrices en bronze de l'âge du bronze en Europe occidentale. In: C. Eluère (ed.), *Outils et ateliers d'orfèvre des temps anciens, Antiquités Nationales, mém.* 2, 1993, 13–22.
- Eogan 1983** – G. Eogan, *The hoards of the Irish Later Bronze Age*, Dublin 1983.
- Evans 1881 – J. Evans, *The Ancient Bronze implements, weapons and ornaments of Great Britain and Ireland*, London 1881.
- Fabian 2006** – O. Fabian, Die Schmiedegeräte der älteren Bronzezeit Skandinaviens und Schleswig-Holsteins, *Mitteilungen der Gesellschaft für Anthropologie, Ethnologie und Urgeschichte* 27, 2006, 23–40.
- Falkenstein 1998** – F. Falkenstein, *Feudvar II. Die Siedlungsgeschichte des Titeler Plateaus*, Kiel 1998.
- Fitzpatrick 2011** – A. P. Fitzpatrick, *The Amesbury Archer and the Boscombe Bowmen. Bell Beaker burials at Boscombe Down, Amesbury, Wiltshire*, Wessex Archaeological Report 27, 2011.
- Gallus, Horváth 1939** – S. Gallus, T. Horváth, *Un peuple cavalier préscythique en Hongrie. Trouvailles archéologiques du Premier Âge du Fer et leurs relations avec L'Eurasie*, Budapest 1939.
- Gazdapusztai 1959** – Gy. Gazdapusztai, Der Gussformfund von Soltvadkert, *Acta Archaeologica Academiae Scientiarum Hungaricae* 9, 1959, 265–288.
- Gedl 2001** – Marek Gedl, *Die Bronzegefäße in Polen*, PBF II, 15, Stuttgart 2001.
- Gedl 2004** – M. Gedl, *Die Beile in Polen IV (Metalläxte, Eisenbeile, Hämmer, Ambosse, Meißel, Pfrieme)*, PBF IX, 24, Stuttgart 2004.
- Girtler 1970** – R. Girtler, Ein urnenfelderzeitlicher Verwahrfund aus Schiltern, p. B. Korneuburg, G. B. Langenlois, NÖ. *Archaeologia Austriaca* 48, 1970, 1–7.
- Gligorić, Filipović, Bulatović 2016** – R., Gligorić, V. Filipović, A. Bulatović, An AMS dated Late Bronze Age grave from the mound necropolis at Paulje, *Starinar* LXVI, 2016, 103–110.
- Gogâltan 2005** – Fl. Gogâltan, Zur Bronzeverarbeitung im Karpatenbecken. Die Tüllenhammer und Tüllenambosse aus Rumänien, in: T. Soroceanu (ed.), *Bronzefunde aus Rumänien II. Beiträge zur Veröffentlichung und Deutung bronze- und älterhallstattzeitlicher Metallfunde im europäischen Zusammenhang (Descoperiri de bronzuri din România II. Contribuții la publicarea și interpretarea descoperirilor de metal din epoca bronzului și din prima varstă a fierului în context European)*, Bistrița-Cluj-Napoca 2005, 343–386.
- Gomez de Soto 1995** – J. Gomez de Soto, *Le Bronze Moyen en Occident. La culture des Duffaits et la civilisation des tumulus. L'Âge du Bronze en France* 5, Paris 1995.
- Gross 1883** – V. Gross, *Les Protohelvètes ou les premiers colons sur les bords des Lacs de Bienne et Neuchâtel*, Paris 1883.
- Hampel 1886** – J. Hampel, *A bronzkor emlékei Magyarhonban I (Altértümer der Bronzezeit in Ungarn)*, Budapest 1886.

Hänsel 1968 – B. Hänsel, *Beiträge zur Chronologie der Mittleren Bronzezeit im Karpatenbecken*, Bonn 1968.

Hansen 1994 – S. Hansen, *Studien zu den Metalldeponierungen während der älteren Urnenfelderzeit zwischen Rhônetal und Karpatenbecken*, UPA 21, Bonn 1994.

Hänsel, Kalicz 1986 – B. Hänsel, N. Kalicz, Das bronzezeitliche Gräberfeld von Mezöcsát, Kom. Borsod, Nordostungarn, *Bericht der Römisch-Germanischen Kommission* 67, 1986, 5–75.

Höglinger 1996 – P. Höglinger, *Der spätbronzezeitliche Depotfund von Sipbachzell/OÖ*, Linz 1996.

Horejs, Mehofer, Pernicka 2010 – B. Horejs, M. Mehofer, E. Pernicka, Metallhandwerker im frühen 3. Jt. v. Chr. – Neue Ergebnisse vom Çukuriçi Höyük, *Inst. Mitt.* 60, 2010, 7–37.

Hundt 1997 – H.-J. Hundt, *Die jüngere Bronzezeit in Mecklenburg*, Schwerin 1997.

Iaia 2014 – C. Iaia, Ricerche sugli strumenti da metallurgo nella protostoria dell'Italia Settentrionale: Gli utensili a percussione, *Padusa* 50, 2014, 65–109.

Jacob 1995 – C. Jacob, *Die Metallgefäße der Bronze- und Hallstattzeit in Nordwest-, West- und Süddeutschland*, PBF II, 9, Stuttgart 1995.

Janas 2010 – A. Janas, Drei urnenfelderzeitliche Hortfunde, *Fundberichte aus Hessen* 50, 2010, 383–516.

Jantzen 2008 – D. Jantzen, *Quellen zur Metallverarbeitung im Nordischen Kreis der Bronzezeit (Güßzeugnisse in Schleswig-Holstein und Dänemark)*, PBF XIX, 2, Stuttgart 2008.

Jockenhövel 1972 – A. Jockenhövel, Westeuropäische Bronzen aus der späten Urnenfelderzeit in Südwestdeutschland, *Archäologisches Korrespondenzblatt* 2, 1972, 103–109.

Jockenhövel 1975 – A. Jockenhövel, Zum Beginn der Jungbronzezeitkultur in Westeuropa. *Jahresber. Inst. Vorgesch.*, Frankfurt a. M. 1975, 134–181.

Jockenhövel 1980 – A. Jockenhövel, *Die Rasiermesser in Westeuropa (Westdeutschland, Niederlande, Belgien, Luxemburg, Frankreich, Großbritannien und Irland)*, PBF VIII, 3, München 1980.

Jockenhövel 1982 – A. Jockenhövel, Zu den ältesten Tülnhämmern aus Bronze, *Germania* 60, 1982, 459–467.

Jockenhövel 1983 – A. Jockenhövel, Ein bemerkenswerter späturnenfelderzeitlicher Amboß, *Germania* 61, 1983, 586–588.

Jockenhövel 2003 – A. Jockenhövel, Querverbindungen in Handwerk und Symbolik zwischen Gold- und Bronzetoreutik, in: Germanisches Nationalmuseum Nürnberg (ed.), *Gold und Kult der Bronzezeit*, Nürnberg 2003, 106–118.

Jockenhövel 2017 – A. Jockenhövel, Casting and forging in the Bronze Age Bulgaria, in: S. Alexandrov, Y. Dimitrova, H. Popov, B. Horejes, K. Chukalev (eds.) *Gold & Bronze: metals, technologies and interregional contacts in the Eastern Balkans during the Bronze Age*, NAIM-BAN, Sofia 2017, 53–60.

Jockenhövel 2018 – A. Jockenhövel, Alteuropäische Gräber der Kupferzeit, Bronzezeit und Älteren Eisenzeit mit Beigaben aus dem Gießereiwesen (Gießformen, Düsen, Tiegel), in: M. Overbeck, *Die Gießformen in West- und Süddeutschland (Saarland, Rheinland-Pfalz, Hessen, Baden-Württemberg, Bayern)*, PBF XIX, 3, Stuttgart 2018, 213–317.

Jockenhövel 2019 forthcoming – A. Jockenhövel, Bronzezeitliche Werkzeugsets als Anzeichen spezialisierter Handwerker, *Plattform. Jahrb. Ver. Pfahlbau- und Heimatkunde* 25/26, 2019.

Jones 1931 – S. J. Jones, Note on an anvil and a palstave found at Flax Bourton, Somerset, *Proc. Bristol Univ. Spelaol. Soc.* 4, 1931, 43–44.

Kapuran 2014 – A. Kapuran, *Praistorijski lokaliteti u severoistočnoj Srbiji*, Beograd, 2014.

Kapuran 2018 – A. Kapuran, Jewellery made of bronze sheet from the prehistoric necropolis at village of Velebit, near Kanjiža, *Starinar* LXVIII, 2018, 33–46.

Keiling 1972 – H. Keiling, Ein eiserner Amboß aus einem Grab der Jastorf-Kultur von Boddin, Kr. Hagenow, *Ausgr. u. Funde* 17, 1972, 176–179.

Kemenczei 2005 – T. Kemenczei, *Funde ostkarpatenländischen Typs im Karpatenbecken*, PBF XX, 10, Stuttgart 2005.

König 2004 – P. König, *Spätbronzezeitliche Hortfunde aus Bosnien und der Herzegowina*, PBF XX, 11, Stuttgart 2004.

Kromer 1959 – K. Kromer, *Das Gräberfeld von Hallstatt*, Firenze 1959.

Kovács 1975 – T. Kovács, *Tumulus Culture cemeteries of Tiszafüred*, Budapest 1975.

Kytlicová 2007 – O. Kytlicová, *Jungbronzezeitliche Hortfunde in Böhmen*, PBF XX, 12, Stuttgart 2007.

Letterlé 1982 – F. Letterlé, Un site de l'Age du Bronze à Cuiry-lès-Chaudardes (Aisne), *Revue archéologiques de Picardie, num. special* 1, 1982, 175–185.

Lo Schiavo 2018 – F. Lo Schiavo, La strumentazione per la lavorazione dei metalli nella Sardegna nuragica / The metal-working tools in Nuragic Sardinia, in: A. Giumlia-Mair, F. Lo Schiavo (eds.), *Bronze Age metallurgy in the Mediterranean islands. In honour of Robert Maddin and Vassos Karageorgis*, Monographies Instrumentum 56, Montignac 2018, 413–453.

- Lo Schiavo et al. 2009** – F. Lo Schiavo, J. Muhly, R. Mad-din, A. Giunilia-Mair, *Oxhide ingots in the central Mediter-ranean*, Roma 2009.
- MacGregor 1987** – *Antiquities from Europe and the Near East in the collection of Lord McAlpine of West Green*, Oxford 1987.
- Makkay 2006** – J. Makkay, The late Bronze Age hoard of Nadap, *A Nyíregyházy Jósza András Múzeum évkönyve* 48, 2006, 135–184.
- Mayer 1977** – E. F. Mayer, *Die Äxte und Beile in Österreich*, PBF. IX, 9, München 1977.
- Medeleț 1995** – F. Medeleț, Ein urnenfelderzeitlicher Depot-fund von bronzenen Werkzeugen in Fratelia bei Timișoara, Kr. Timiș, in: T. Soroceanu (ed.), *Bronzefunde aus Rumänien*. Prähistorische Archäologie in Südosteuropa 10, Berlin 1995, 229–236.
- Meeks, Needham 1993** – N. Meeks, S. P. Needham, A Bronze Age goldworking anvil from Lichfield, Staffordshire, *Ant. Journal* 73, 1993, 125–132.
- Milligan 1885–1886** – S. T. Milligan, Notes and queries, *The Journal of the Royal Historical and Archaeological Asso-ciation of Ireland* 18, 1885–86, 538.
- von Miske 1908** – K. von Miske, *Die prähistorische Ansie-delung Velem St. Vid I. Beschreibung der Raubbaufunde.*, Wien 1908.
- Mohen 1977** – J.-P. Mohen, *L'Âge du Bronze dans la région de Paris, Catalogue synthétique des collections conservées au Musée des Antiquités Nationales*, Paris 1977.
- Mohen 1990** – J.-P. Mohen, *Métallurgie préhistorique, In-troduction à la paléométallurgie*, Paris 1990.
- Mohen, Bailloud 1987** – J.-P. Mohen, G. Bailloud, *La vie quotidienne: Les fouilles du Fort-Harrouard, L'Âge du Bronze en France* 4, Paris 1987.
- Monteagudo 1977** – L. Monteagudo, *Die Beile auf der Ibe-rischen Halbinsel*, PBF IX, 6, München 1977.
- Montelius 1905/1910** – Oscar Montelius, *La civilisation primitive en Italie depuis l'introduction des métaux, sér. B. Italie centrale*, Stockholm 1905/1910.
- Moreau 1971** – Jacques Moreau, Un moule d'enclume de l'Âge du Bronze trouvé à La Lède-du-Gurp (Gironde), *Gallia préhistoire* 14, 1971, 267–269.
- Mortillet 1906** – A. de Mortillet, Cachette de l'Âge du Bronze de Porcieu-Amblagnieu, Isère. *L'Homme Préhisto-rique* 4, 1906, 129–140.
- Mozsolisc 1973** – A. Mozsolisc, *Bronze- und Goldfunde des Karpatenbeckens, Depotfundhorizonte von Forró und Ópályi*, Budapest 1973.
- Mozsolics 1984** – A. Mozsolics, Ein Beitrag zum Metall-handwerk der ungarischen Bronzezeit. *Bericht der Römisch-Germanischen Kommission* 65, 1984, 19–72.
- Mozsolics 1985** – A. Mozsolics, *Bronzefunde aus Ungarn. Depotfundhorizonte von Aranyos, Kurd und Gyermely*, Bu-dapest 1985.
- Müller 1920** – S. Müller, Nye Fund og Former, *Aarbøger* 1920, 27–40.
- Müller-Karpe 1959** – H. Müller-Karpe, *Beiträge zur Chro-nologie der Urnenfelderzeit nördlich und südlich der Alpen*, Berlin 1959.
- Müller-Karpe 1969** – H. Müller-Karpe, Das urnenzeitliche Toreutengrab von Steinkirchen, Niederbayern, *Germania* 47, 1969, 86–91.
- Müller-Karpe 1980** – H. Müller-Karpe, *Handbuch der Vorgeschichte IV, Bronzezeit*, München 1980.
- Müller-Karpe 1994** – A. Müller-Karpe, *Anatolisches Metall-handwerk*, Neumünster 1994.
- Musée cantonal vaudois 1896** – Musée cantonal vaudois. *Album publié par la Société d'histoire de la Suisse romande*, Lausanne 1896.
- Needham, Meeks 1993** – S. P. Needham with a contribution from N. Meeks, A Bronze Age goldworking anvil from Lich-field, Staffordshire, *Ant. Journal* 73, 1993, 125–132.
- Nessel 2008** – B. Nessel, Zu Gliederung und Verwendungs-möglichkeiten bronzener Tüllenhammer der jüngeren Bronze-zeit im Karpatenbecken, *Mitt. Berl. Ges. Anthr. Ethn. Urgesch.* 29, 2008, 71–81.
- Nessel 2009** – B. Nessel, Bronzenes Spezialgerät. Ein Metall-handwerkerdepot im Berliner Museum für Vor- und Früh-geschichte, *Acta Praehist. et Arch.* 41, 2009, 37–65.
- Nessel 2010** – B. Nessel, Schmiede und Toreuten in den ur-nenfelderzeitlichen Depotfunden des Karpatenbeckens? Funktionsanalyse von Handwerksgerät und soziale Implika-tionen, in: B. Horejs, T. L. Kienlin (eds.), *Siedlung und Handwerk. Studien zu sozialen Kontexten in der Bronzezeit. Beiträge zu den Sitzungen der Arbeitsgemeinschaft Bronze-zeit auf der Jahrestagung des Nordwestdeutschen Verban-des für Altertumsforschung in Schleswig 2007 und auf dem Deutschen Archäologenkongress in Mannheim 2008*, UPA 194, Bonn 2010, 373–386.
- Nessel 2013** – B. Nessel, The 'absence' of smiths and found-ers. Why tools are rare in Bronze Age burials?, in: B. Rezi, R.E. Németh, S. Berecki (eds.), *Bronze Age crafts and crafts-men in the Carpathian Basin. Proceedings of the Interna-tional Colloquium from Târgu Mureș, Târgu Mureș* 2013, 139–148.

Nicolardot, Gaucher 1975 – J.-P. Nicolardot, G. Gaucher, *Outils*. Typologie des objets de l'Age du Bronze en France 5, Paris 1975.

Novotná 1970 – M. Novotná, *Die Äxte und Beile in der Slowakei*, PBF IX, 3, München 1970.

Pančiková 2008 – Z. Pančiková, Metalurgia v období popelnicových polí na Slovensku (Urnenfelderzeitliche Metallurgie in der Slowakei), *Pam. Arch.* 99, 2008, 93–160.

Pearce 1983 – S. M. Pearce, *The Bronze Age metalwork of South Western Britain*, BAR 120, Oxford 1983.

Petrescu-Dîmbovița 1978 – M. Petrescu-Dîmbovița, *Die Sicheln in Rumänien mit Corpus der jung- und spätbronzezeitlichen Horte Rumäniens*, PBF XVIII, 1, München 1978.

Ponzi Bonomi 1970 – L. Ponzi Bonomi, Il ripostiglio di Contigliano, *Bull. Paletn. Ital.* 79, 1970, 95–156.

Powell et al. 2018 – W. Powell, A. Bankoff, A. Mason, R. Mathur, A. Bulatović, V. Filipović, Tin sources and regional trade in the Bronze age of southeast Europe: evidence from tin isotopes, in: S. Alexandrov, Y. Dimitrova, H. Popov, B. Horejes, K. Chukalev (eds.) *Gold & Bronze: metals, technologies and interregional contacts in the Eastern Balkans during the Bronze Age*, NAIM-BAN, Sofia 2018, 141–150.

Primas, Pernicka 1998 – M. Primas, E. Pernicka, Der Depotfund von Oberwilflingen. Neue Ergebnisse zur Zirkulation von Metallbarren, *Germania* 76, 1998, 25–65.

Rowlands 1976 – M. J. Rowlands, *The production and distribution of metalwork in the Middle Bronze Age in Southern Britain*, BAR 31, Oxford 1976.

Rychner 1979 – V. Rychner, *L'âge du Bronze final à Auvergnier (Lac de Neuchâtel, Suisse)*. Typologie et chronologie des anciennes collections conservées en Suisse 1–2, Lausanne 1979.

Salaš 2014 – M. Salaš, Kovadlinky, kladívka a přílby doby popelnicových polí na Moravě na pozadí depotu z Brna-Řečkovice (Urnenfelderzeitliche Ambosse, Hämmer und Helme in Mähren vor dem Hintergrund des Hortfundes von Brno-Řečkovice), *Pam. Arch.* 105, 2014, 47–86.

Sánta 2013 – G. Sánta, Metal analysis of Koszider and Tumulus Culture Bronzes: contents, similarities and the question of source Area, in: B. Rezi, R.E. Németh, S. Berecki (eds.), *Bronze Age crafts and craftsmen in the Carpathian Basin, Proceedings of the International Colloquium from Târgu Mureș*, Târgu Mureș 2013, 77–90.

Sava et al. 2011 – V. Sava, G. Pascu Hurezan, F. Mărginean, Late Bronze Age metal artifacts discovered in Șagu, Site "A1_1", Arad-Timișoara Highway (km 0+19.900–0+20.620), *Ziridava Studia Archaeologica* 26, 2012, 83–108.

Sava, Andreica 2013 – V. Sava, L. Andreica, Social identity in the Lower Mureș Valley during the Late Bronze Age: Two

seal-headed pins from Pecica „Site 14“ cemetery, in: J. V. Ferencz (ed.), *Archaeological Small Finds and their Significance*, 2013, 49–76.

Schmidt 2014 – J.-P. Schmidt, Der älterbronzezeitliche Werkzeughort von Golchen, Lkr. Mecklenburgische Seenplatte, in: D. Jantzen, J. Orschiedt, J. Piek, T. Terberger (eds.), *Tod im Tollensetal. Forschungen zu den Hinterlassenschaften eines bronzezeitlichen Gewaltkonfliktes in Mecklenburg-Vorpommern I. Die Forschungen bis 2011*, Schwerin 2014, 181–190.

Schoknecht 1974 – U. Schoknecht, Ein bronzezeitlicher Hortfund der Periode V von Murchin, Kr. Anklam, *Jahrb. Bodendenkmalpf.* 1974 (1975), 145–172.

Sekeres 1971 – L. Sekeres, Zenta és környéke története a régészeti leletek fényében, in: *Građa za monografiju Sente*, Senta 1971, 46–50.

Smith 1881 – J. A. Smith, Notice of a large copper-like or brass anvil, stated to have been found in the south of Scotland: also of a small ancient bronze anvil, found in Sutherland, *Proc. Soc. Antiq. Scotland* 16, 1881, 15–25.

Sperber 2000 – L. Sperber, Zum Grab eines spätbronzezeitlichen Metallhandwerkers von Lachen-Speyerdorf, Stadt Neustadt a. d. Weinstraße, *Archäologisches Korrespondenzblatt*. 30, 2000, 383–402.

Sprockhoff 1956 – E. Sprockhoff, *Jungbronzezeitliche Hortfunde der Südzone des nordischen Kreises Periode V*, Mainz 1956.

Stead 1998 – I. M. Stead, *The Salisbury hoard*, Stroud 1998.

Szabó 2011 – G. Szabó, Spätbronzezeitliche Bronzehortfunde im Siedlungskontext – Neue Forschungsergebnisse aus Ostungarn, in: S. Berecki, R. E. Németh, B. Rezi (eds.), *Bronze Age rites and rituals in the Carpathian Basin*, Târgu Mureș 2011, 335–356.

Szabó 2013 – G. Szabó, Late Bronze Age stolen. New data on the illegal acquisition and trade of Bronze Age artefacts in the Carpathian Basin, in: A. Anders, G. Kulcsár (eds.), *Moments in time, Papers presented to Pál Raczky on his 60th birthday*, Budapest 2013, 793–815.

Šimek 2004 – M. Šimek, Grupa Martinajec-Kaptol, in: D. Balen-Letunić (ed.), *Ratnici na razmeđu istoka i zapada, starije željezno doba u kontinentalnoj Hrvatskoj*, 2004, 79–130.

Tasić 1974 – N. Tasić, Bronzani dobai in: B. Brukner, N. Tasić, B. Jovanović (eds.), *Praistorija Vojvodine*, Novi Sad 1974, 185–256.

Tacuh 1983 – Н. Тасић, Југословенско Подунавље од Индоевропске сеобе до прозора Скита, Нови Сад–Београд 1983. (N. Tasić, *Jugoslovensko Podunavlje od Indoevropske seobe do prodora Skita*, Novi Sad–Beograd 1983).

Tasić 2003–2004 – N. Tasić, Historical picture of development of Bronze Age cultures in Vojvodina, *Starinar* LIII–LIV/2003–2004, 23–36.

Taylor 1980 – J. J. Taylor, *Bronze Age goldwork of the British Isles*, Cambridge 1980.

Teržan 1994 – B. Teržan 1994, Überlegungen zum sozialen Status des Handwerkers in der frühen Eisenzeit Südosteuropas, in: C. Dobiat (ed.), *Festschrift für Otto-Herman Frey zum 65. Geburtstag*. Marburger Stud. Vor- u. Frühgesch. 16, Marburg 1994, 659–669.

Teržan 2003 – B. Teržan, Bronasta žaga, Prispevek k prazgodovini rokodelskega orodja (Bronzesägen. Zur Frühgeschichte eines Werkzeuges), *Opuscula Arch.* 27, 2003, 187–197.

Thevenot 1998 – J.-P. Thevenot, Un outillage de bronzier: Le dépôt de la Petite Laugère, à Gênelard (Saône-et-Loire, F), in: C. Mordant, M. Pernot, V. Rychner (eds.), *L'atelier du bronzier en Europe du XX^e au VIII^e siècle avant notre ère II: Du minerai au métal, du métal à l'objet, Actes du colloque international "Bronze '96"*, Neuchâtel – Dijon 1996, Paris 1998, 123–144.

Tylecote 1987 – R.F. Tylecote, *The early history of metal-lurgy in Europe*, London – New York 1987.

Valera, Valera 2003 – R. G. Valera, P. G. Valera, Tin in the Mediterranean Area: History and Geology, in: A. Giumlia-Mair, F. Lo Schiavo (eds.) *The problem of early tin, Acts of the XIVth UISPP Congress, University of Liège, Belgium 2011, Section 11, Bronze Age Europe and the Mediterranean*,

Symposium 11.2., BAR International Series 1199, Oxford 2011.

Vasić 2003 – R. Vasić, *Die Nadeln im Zentralbalkan (Vojvodina, Serbien, Kosovo und Makedonien)*, PBF XIII, Band 11, Stuttgart 2003.

Vasić 2010 – R. Vasić, *Die Halsringe im Zentralbalkan (Vojvodina, Serbien, Kosovo und Mazedonien)*, PBF XI, Band 7, Stuttgart 2010.

Васић, Ерцеговић-Павловић, Минић 1984 – Р. Васић, С. Ерцеговић-Павловић, Д. Минић, Велесница, извештај о сондажним рекогносцирањима у 1980. години, *Ђердапске свеске* II, 1984, 125–132. (R. Vasić, S. Ercegović-Pavlović, D. Minić, Velesnica, izveštaj o sondažnim rekonosciranjima u 1980. godini, *Ђердапске свеске* II, 1984, 125–132).

Venturino Gambari 2009 – M. Venturino Gambari (ed.), *Il ripostiglio del Monte Cavanero di Chiusa di Pesio (Cuneo)*, Alessandria 2009.

Verron 1971 – G. Verron, *Antiquités préhistoriques et protohistoriques. Musée Départemental des Antiquités de la Seine-Maritime*, Rouen 1971.

Wattè 2010 – J.-P. Wattè, A propos d'une hache du Musée Royal de Toronto et du dépôt du Bronze Final de Gravelle-Sainte-Honorine (Le Havre, Seine-Maritime, France), *Bulletin de la Société Géologique de Normandie et des Amis du Muséum du Havre* 96, 2009 (2010), 37–42.

Wyss 1967 – R. Wyss, *Bronzezeitliches Metallhandwerk*, Aus dem Schweizerischen Landesmuseum 21, Bern 1967.

Резиме: БАРБАРА АМБРУСТЕР, Универзитет у Тулузу
АЛБЕРТ ЖОКЕНХОВЕЛ, Универзитет у Мунстеру
АЛЕКСАНДАР КАПУРАН, Археолошки институт, Београд
РАШКО РАМАДАНСКИ, Градски музеј Сента

ЛИВАЧКИ КАЛУПИ ИЗ ВЕЛЕБИТА И МЕТАЛНИ НАКОВЊИ ИЗ БРОНЗАНОГ ДОБА У ЕВРОПИ

Кључне речи – Бронзано доба, Карпаташки басен, Култура гробних хумки, наковњи, калупи, наковњи, металургија

Пре скоро пола века изведена су систематска истраживања некрополе из бронзаног доба и касне антике / раног средњег века на једном локалитету који се налазио на улазу у село Велебит код Кањиже. Том приликом откривена је једна праисторијска остава камених калупа за ливење предмета од бронзе, међу којима се издвајао један тип за који је професор А. Јокенховел потврдио да припада калупу за израду наковања.

Старији хоризонт сахрањивања на овој некрополи припадао је Култури гробних хумки средњег бронзаног доба у централној Европи, а наведени калуп из тог контекста представља за сада једини налаз који се повезује с постојањем наковања на територији централног Балкана у бронзаном добу, тако да је циљ овога рада да укаже на везе које је овај простор имао са развојем продукције бронзаних предмета на целој територији Европе.

Историја истраживања наковања из праисторије почиње у 19. веку првим радовима на ту тему чији је аутор В. Г. Чајлд, а настављају је својим радовима Ј. Николард, Г. Гушер, М. Р. Еренберг и Д. Јанцен. Испрва су наковње представљали примерци од камена, као уосталом и остале алатке за обраду бронзаних полупроизвода током периода Културе звонастих пехара и раног бронзаног доба у Европи, као и у Çukuriçi Höyük у Анадолији, а њихова употреба се продужава кроз целокупно трајање бронзаног доба. Чак се у појединим контекстима заједно може наћи камени и метални алат за обраду метала, као што је пример на локалитету Gélénard у Француској.

Због термиолошких разлика у називу за наковње, у овом раду је коришћен термин *anvil*, који подразумева различите врсте статичних подлога, сачињених од дрвеног и металног дела, које се користе у процесу искуцавања. Наковње смо поделили у следеће категорије и поткатегорије:

Категорија 1: Пљоснати и пирамидални наковњи (*frustrum*) – равни наковњи Brett-, Blockambosse);

Поткатегорија 1a: Пљоснато-равни наковњи (Brettambosse), сл. 6;

Поткатегорија 1b: Пирамидални (*frustum*) наковњи (сл. 7);

Поткласа 1c: Наковњи с једном радном површином (сл. 8);

Поткласа 1d: Пљоснати наковњи петоугаоног пресека са усадником (сл. 8);

Поткласа 1e: Наковњи у облику „печурке” (сл. 9);

Поткласа 1f: Наковњи са равном или калотастом главом (сл. 9);

Класа 2: Наковњи с једним или два рожаста испупчења (Hornambosse);

Поткласа 2a1: Наковњи с једним латералним клинастим испупчењем које се налази на истом нивоу са радном површином (сл. 10);

Поткласа 2a2: Наковњи с једним латералним клинастим испупчењем које се налази близу радне површине (сл. 11);

Поткласа 2b: Наковњи са два латерална клинаста испупчења која су фиксирана на средишњем делу (сл. 12);

Поткласа 2c: Наковњи са две радне површине и са два латерална клинаста испупчења (наковњи у облику слова „Т” / тип Chalon-sur-Saône/Gray), сл. 13/1–6;

Поткласа 2d: Наковњи с једном радном површином, једним клинастим испупчењем и једним усадником (тип Fresnè-la-Mère), сл. 13/7–10;

Класа 3: Равни наковњи са испупчењима и удубљењима (Riefenanken, Kugelanken), сл. 14/1–6;

Класа 4: Наковњи савијени под углом (Biegestöcke), сл. 14/7–11;

Класа 5: Наковњи за искуцавање (Treibfäuste), сл. 15/1–3;

Наковњи специфичних облика (сл. 15/5–8);

Ad hoc наковњи (сл. 16);

Наковњи у облику чекића са усадником (Tüllenambosse), сл. 17.

До сада је констатовано око 124 предмета што су имала функцију наковања, и то претежно у бронзаним оставама, док су поједини налази и на локалитетима као и у контексту сахрана. Највећа количина ових предмета потиче са британских острва и из Ирске, Француске као и појединих делова Швајцарске. Мање количине су констатоване у Италији, Источним Алпима, Подунављу, Панонији и западном Карпатском басену. Калуп за израду наковања са Велебита представља први примерак у Србији и најстарији у Панонији, док у многим крајевима Европе такви калупи нису уопште нађени. Занимљиво је да се слични типови наковања налазе тек на удаљености од 1200 км до 1400 км на западу у Француској. Хронолошки гледано, најсложеније форме јављају се током средњег бронзаног доба, док на крају тог доба доминирају једноставнији облици. Сви су изливени од бронзе (CuSn), а поједини су направљени од

посебне легуре бакра с високом концентрацијом калаја од 10% до 310%, док су неки садржали и олово (Pb 25%), антимон (Sb мање од 5%) или веома малу количину калаја.

Из претходне расправе можемо закључити да су наковњи представљали незаобилазне делове ковачке опреме за израду металних предмета мањих или већих димензија. Најбоља илустрација за опрему једног ковача јесте остава Génélard из Француске (Fig. 18), са сетом алата за израду различитих врста употребних предмета и накита. У суседству Србије најзначајнија је остава Бољанић (БиХ), а нашу везу са Подунављем представљају оставе Nadar (у Мађарској) и Fratelia (у Румунији).

Током бронзаног доба наковњи су такође били неопходни и приликом стварања и обраде предмета од злата, о чему у неколико случајева сведоче налази: „North Sligo” (no. 79); Lusmagh (no. 78, Ирска); Lichfield (no. 117, Енглеска) и Fresné-la-Mère (no. 27, Нормандија). То потврђују

трагови златних честица откривени на наковњу из Lachen-Speyerdorf-a (no. 51, Југозападна Немачка), али се сматра да су примерци из остава Fresné-la-Mère (Нормандија) и Velim (no. 9, Источна Чешка) такође имали везе са обрадом злата.

На крају можемо закључити да су представљени наковњи из бронзаног доба претежно коришћени за обраду мањих предмета, израду орнамената и за моделовање предмета у облику жице, трака и пластичне декорације од бронзе, сребра и злата. На њима су се могле не само правити оштрице алата и оружја већ и додатно оштрити. Највећи број наковања нађен је у оквиру остава, а само шест у контексту гробова. Они су услед веће количине бронзе, од које су морали да буду направљени, вероватно имали већу вредност, па су се преносили наследством са оца на сина. У том би смислу требало посматрати и налаз са некрополе Велебит, односно – да је са ковачем из бронзаног доба похрањен само фрагментовани калуп, а не цео наковањ.

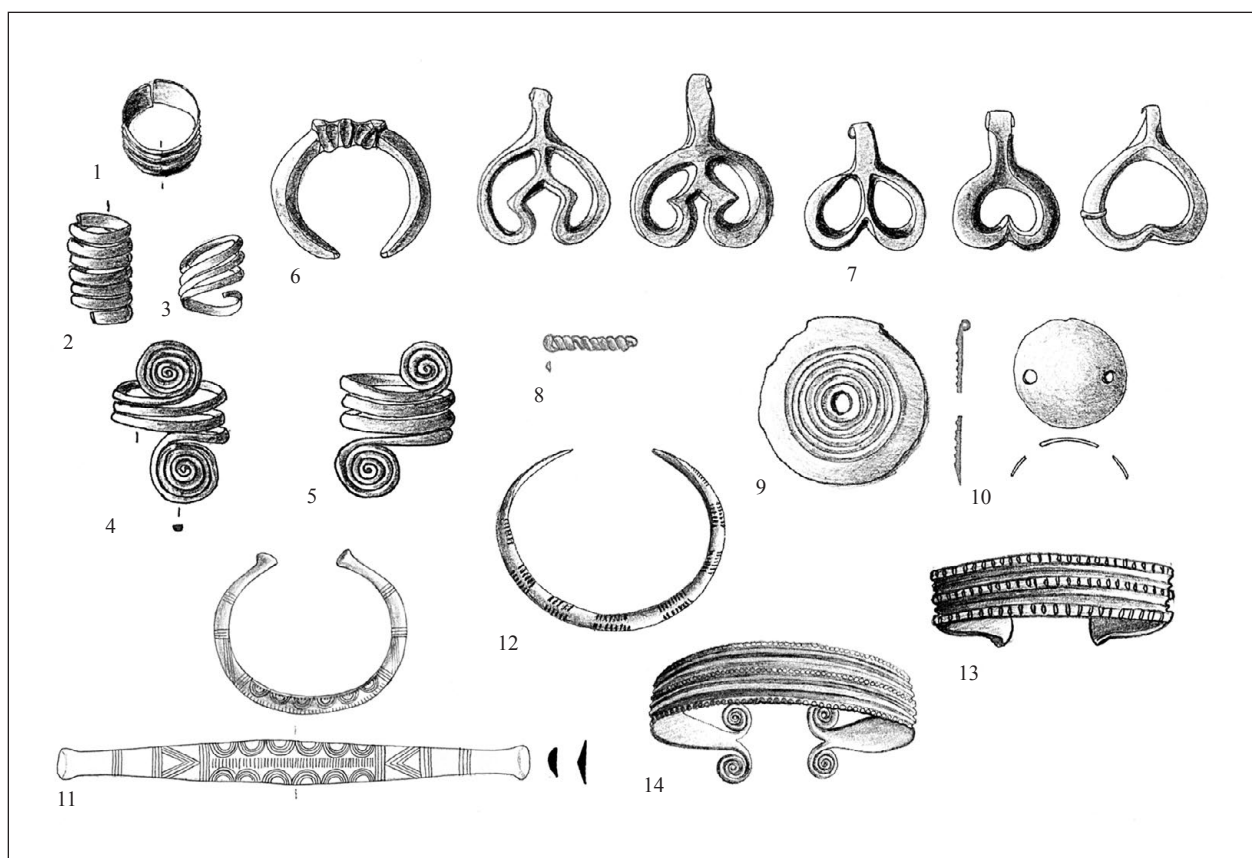


Plate I – Velebit. Bronze finds from the cemetery

Табела I – Велебиг: налази бронзе са некрополе

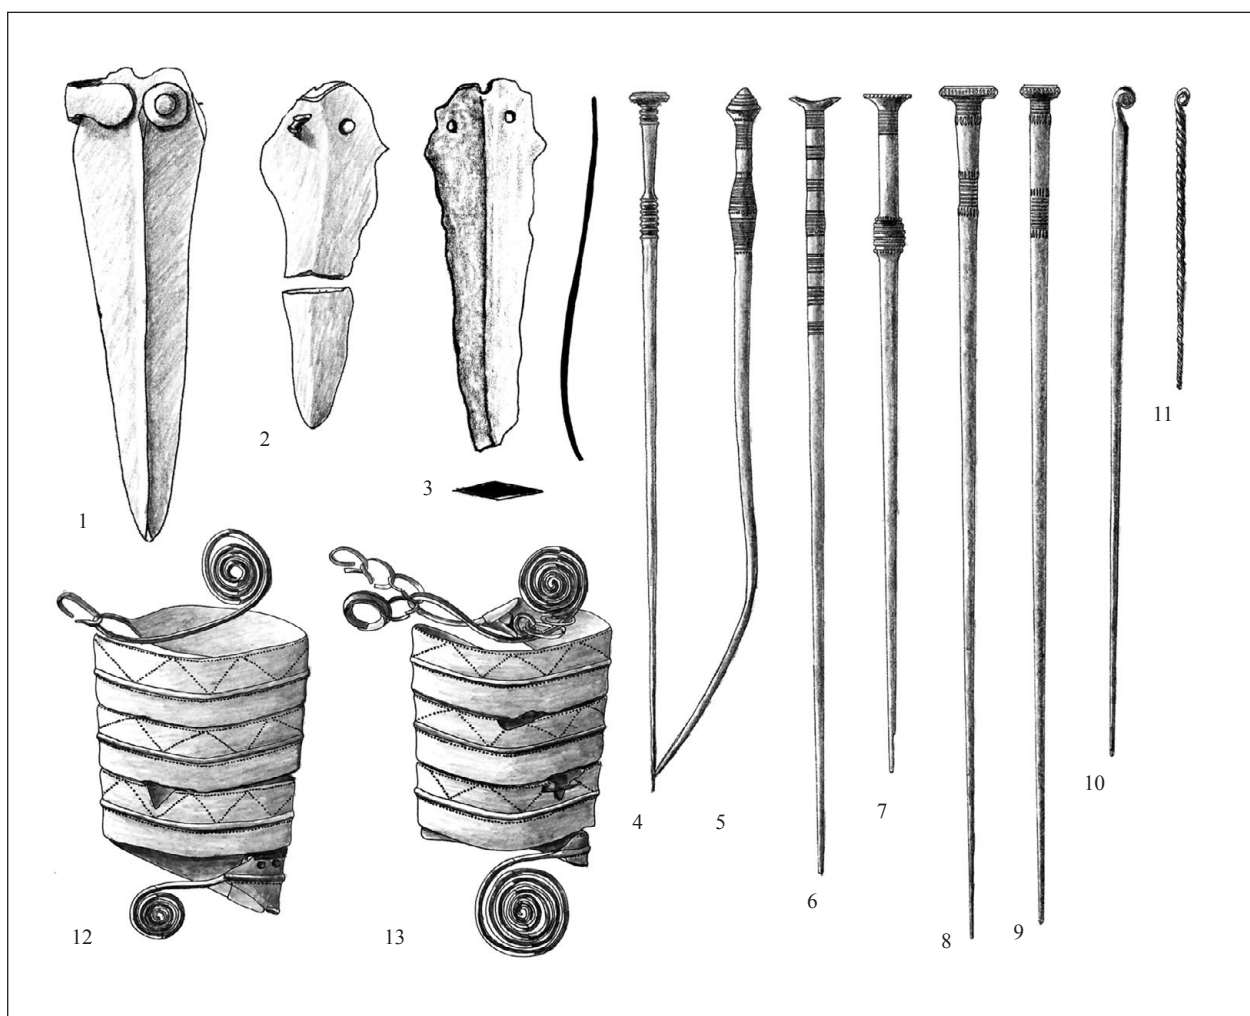


Plate II – Bronze finds from the Velebit necropolis

Табела II – Велебиги: налази бронзе са некрополе

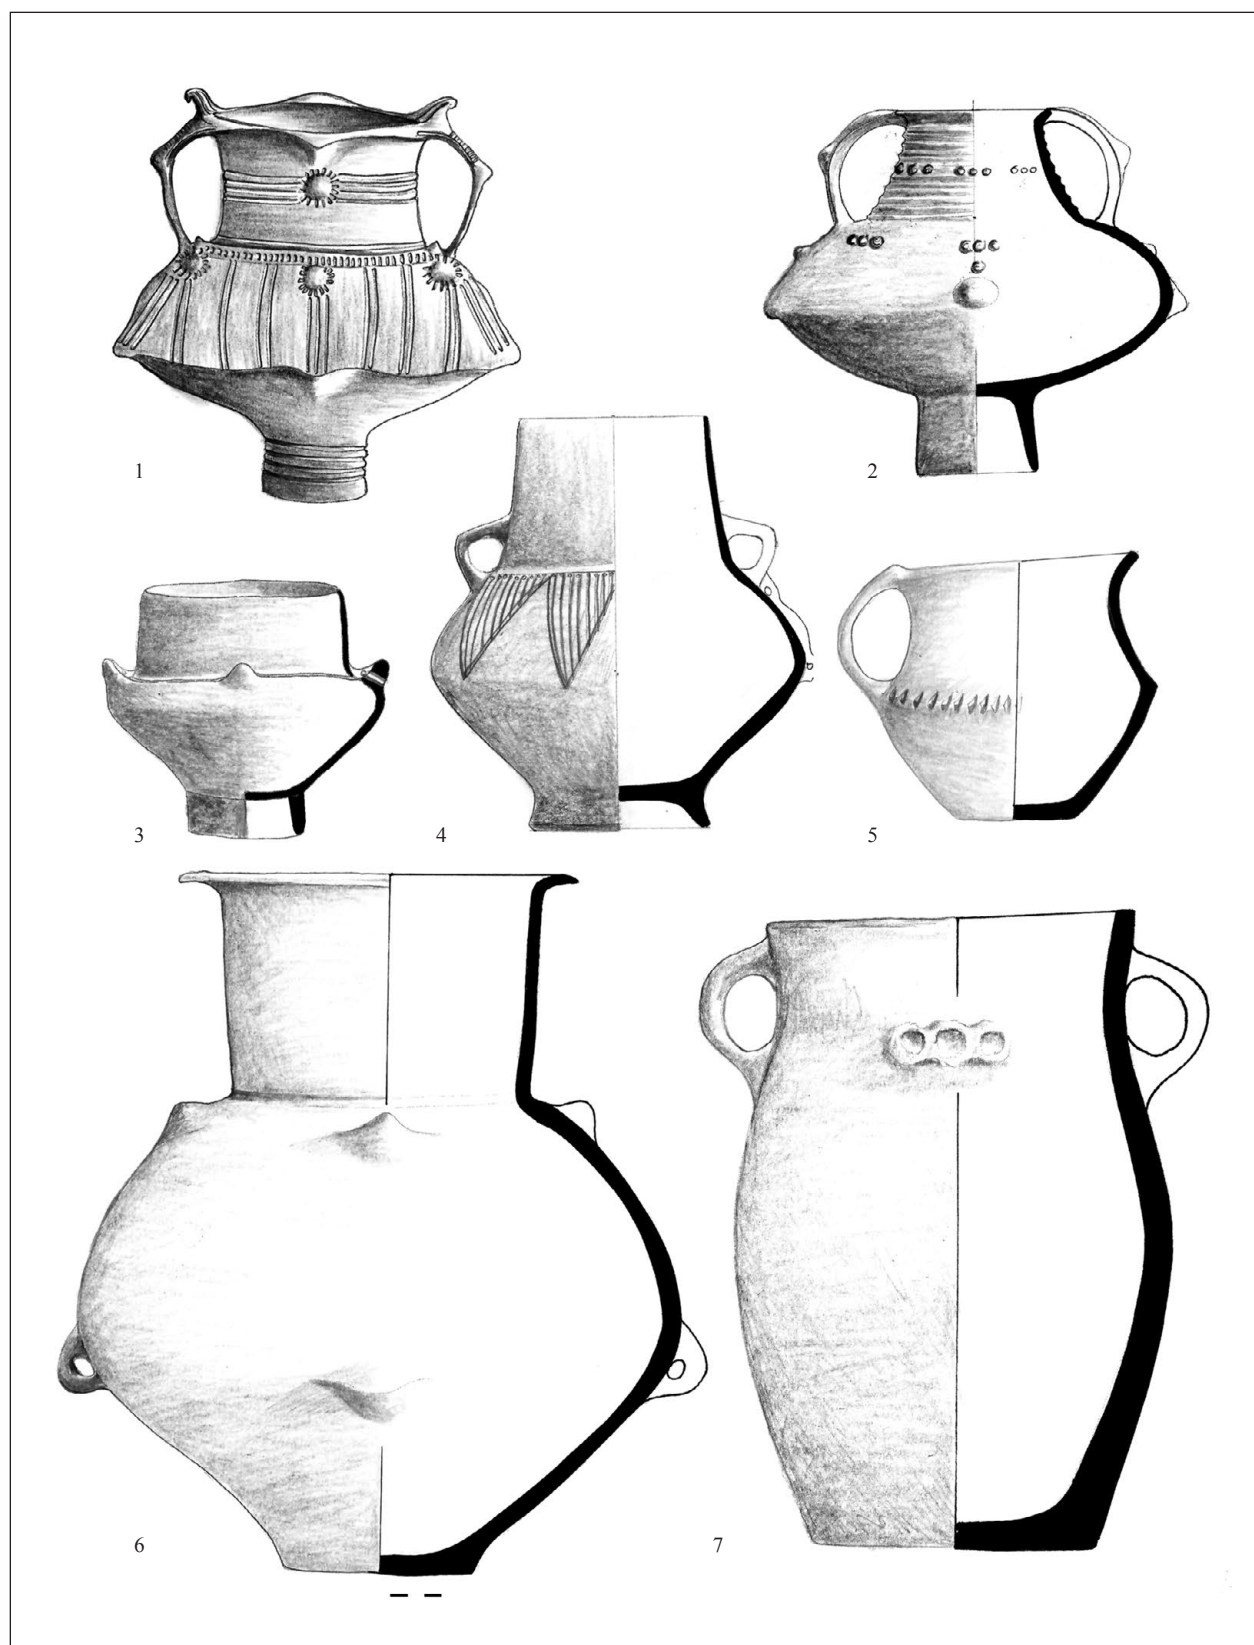


Plate III – Pottery finds from the Velebit necropolis

Табела III – Налази керамике са некрополе Велебиги

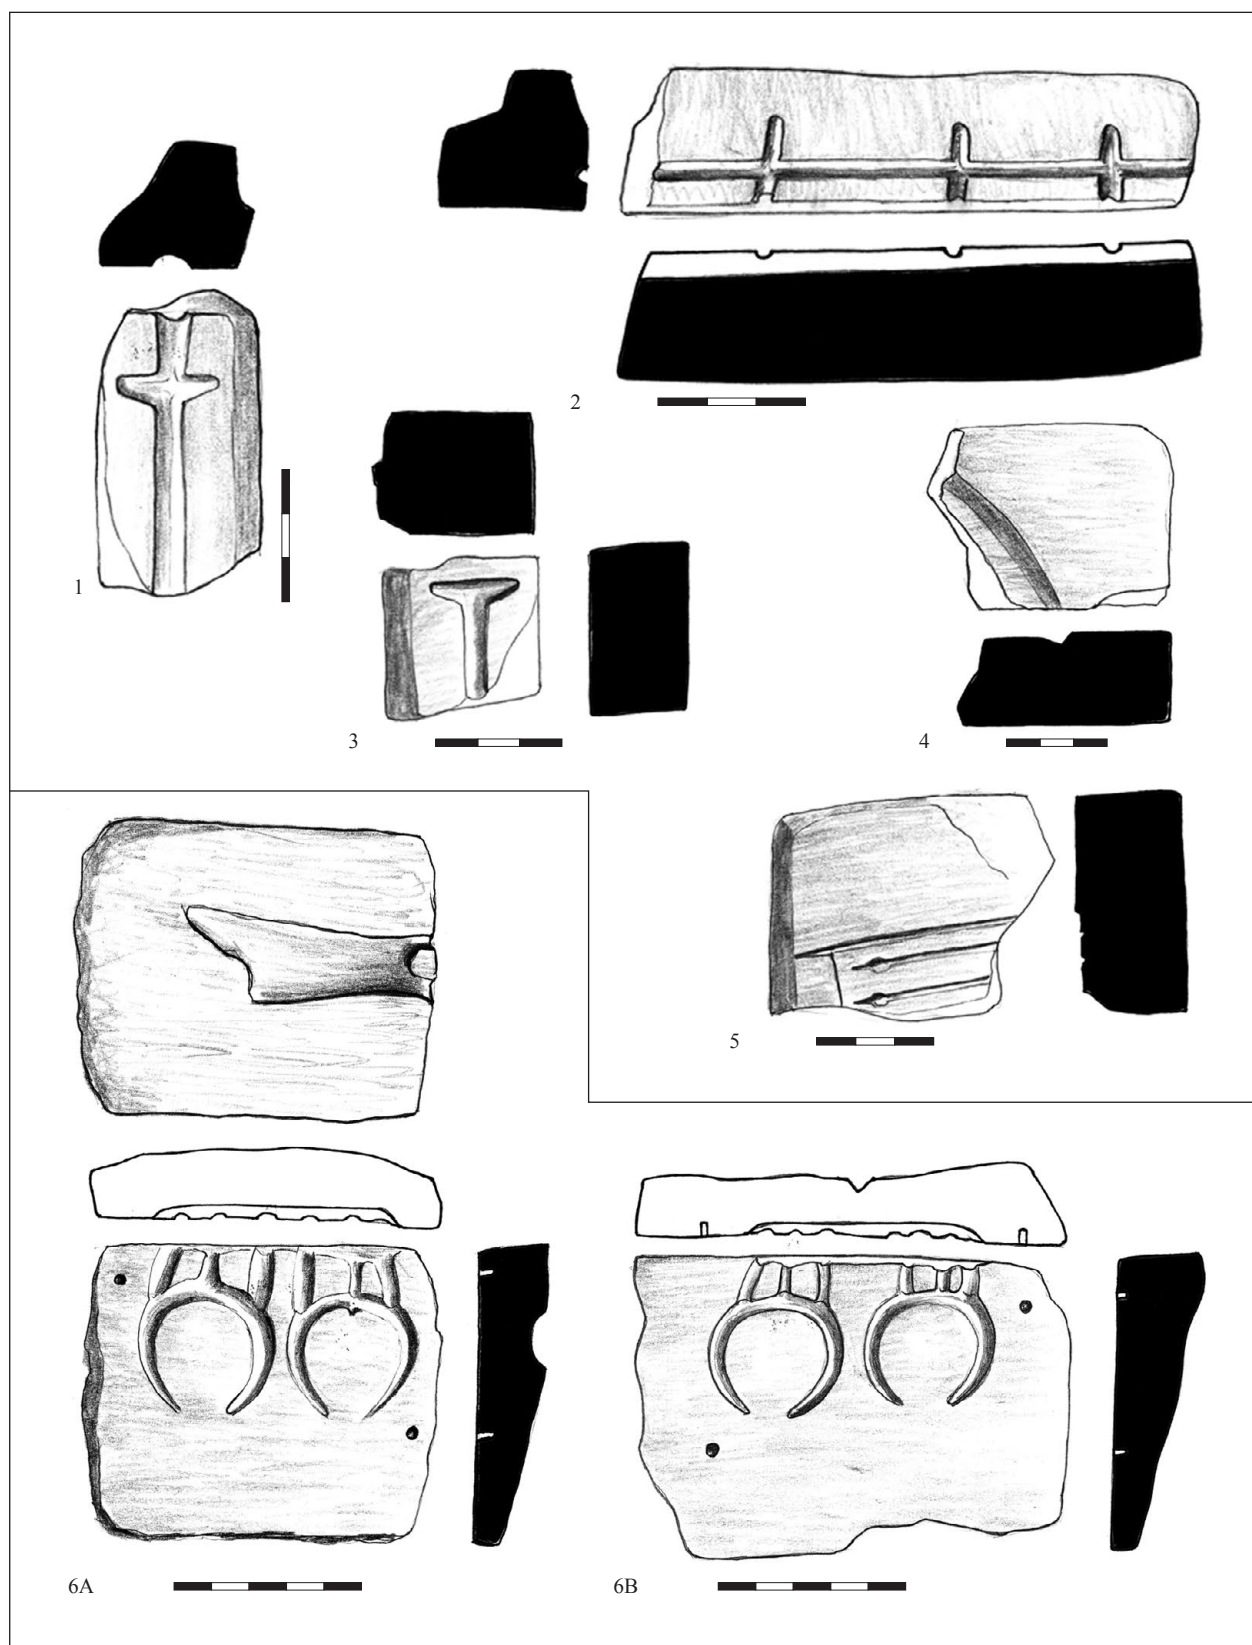


Plate IV – Moulds from the Velebit necropolis

Табла IV – Велебiiй: камени калуи са некројоле

STARINAR



ISSN 0350-0241



9 770350 024001